

Intrinsic electronic superconducting phases at 60 K and 90 K in double-layer $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$

T. Honma¹ and P.H. Hor²

¹*Department of Physics, Asahikawa Medical College, Asahikawa, Hokkaido 078-8510, Japan*

²*Department of Physics and Texas Center for Superconductivity and Advanced Materials,
University of Houston, Houston, TX 77204-5005, U.S.A.*

(Dated: March 23, 2022)

We study superconducting transition temperature (T_c) of oxygen-doped double-layer high-temperature superconductors $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ ($0 \leq \delta \leq 1$) as a function of the oxygen dopant concentration (δ) and planar hole-doping concentration (P_{pl}). We find that T_c , while clearly influenced by the development of the chain ordering as seen in the T_c vs. δ plot, lies on a universal curve originating at the critical hole concentration (P_c) = 1/16 in the T_c vs. P_{pl} plot. Our analysis suggests that the universal behavior of $T_c(P_{pl})$ can be understood in terms of the competition and collaboration of chemical-phases and electronic-phases that exist in the system. We conclude that the global superconductivity behavior of $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ as a function of doping is electronically driven and dictated by pristine electronic phases at magic doping numbers that follow the hierarchical order based on P_c , such as $2 \times P_c$, $3 \times P_c$ and $4 \times P_c$. We find that there are at least two intrinsic electronic superconducting phases of $T_c = 60$ K at $2 \times P_c = 1/8$ and $T_c = 90$ K at $3 \times P_c = 3/16$.

PACS numbers: 74.25.Fy, 74.25.Dw, 74.62.Dh, 74.72.Bk

It has become clear in recent years that various physical properties of high temperature superconductors (HTS) are manifestations of a complex electronic texture of intrinsic electronic inhomogeneities due to dopants and, more importantly, electronic phase separation (EPS). In this report we show that the key to understand the underlying electronic texture and the corresponding superconducting properties are electronic phases that exist at magic planar doping concentrations (hole content per CuO_2 plane, P_{pl}) $P_{pl} = m/n^2$, where both m and n are positive integers with $4m \leq n^2$ and P_{pl} is determined based on a universal hole scale. Studies of the electronic phase diagram under ambient and high-pressure in cation (Sr) and anion (O) co-doped polycrystalline $\text{La}_{2-x}\text{Sr}_x\text{CuO}_{4+\delta}$ (CD-La214) revealed that there are two intrinsic electronic superconducting phases with superconducting transition temperature $T_{c1} = 15$ K and $T_{c2} = 30$ K.¹ The far-infrared charge dynamics studies on the T_{c1} and T_{c2} phases indicated that they are very peculiar electronic phases which have very small amount ($< 1\%$ of total doped hole) of free holes moving in otherwise pinned two-dimensional (2D) electronic lattice. The T_{c1} and T_{c2} phases start at the critical “magic” planar hole-doping levels $P_{pl} = 1/16 \equiv P_c$ and $P_{pl} = 1/8 = 2 \times P_c$, respectively.² The existence and the clear competition of T_{c1} and T_{c2} phases observed in the pure cation (Sr)-doped polycrystalline $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (SrD-La214) indicated that, independent of the nature of the dopants, these intrinsic T_c ’s phases are energetically favored electronic phases that exist in the CuO_2 planes.³ Most recently magnetic studies of SrD-La214 single crystals confirmed the existence of the T_{c1} and T_{c2} transitions and the onset of the superconducting transition temperature were surprisingly robust with little field dependence up to 5 T.⁴ These “2D square electronic lattices” formed at magic doping concentrations are the most fundamental

building blocks of electronic states, the pristine electronic phase (hereafter PEP), for the understanding of both normal and superconducting properties of HTS. While three-dimensional ordered PEP’s seem to be firmly established in single-layer La214 system,⁴ it is not clear how will PEP manifest themselves in other HTS. In this report we show that, indeed, in pure anion (O) doped double-layer $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ (OD-Y123) system there exist at least two intrinsic T_c ’s of $T_c = 60$ K and $T_c = 90$ K that are based on PEP’s at $P_{pl} = 2/16 = 2P_c$ and $3/16 = 3P_c$, respectively. Furthermore we find that the famous “60 K-plateau” in the electronic phase diagram of OD-Y123 can be naturally explained by the EPS of PEP’s

In order to sort out the PEP’s in OD-Y123 system we need to take care of the complications due to sensitive dependences of T_c on both the amount and arrangement of oxygen dopants.^{5,6} The oxygen dopants tend to form long Cu-O chain ordering along b -axis that results in energetically favored meta-stable superstructures consisting of alternative arrangements of full Cu-O chain (full-chain) and O-vacancy chain (empty-chain).⁷ It was proposed that there are, starting from complete full-chain-ordering ortho-I phase, ortho-II (-II), -III (-III*) and -IV (-IV*) chemical phases will have single, double and triple full-chains (empty-chains) between any two empty-chains (full-chains), respectively.⁷ It is well known that in the T_c vs. P_{pl} phase diagram of OD-Y123 there are two prominent plateaus located at $T_c \sim 60$ K (60K-plateau) and ~ 90 K (90K-plateau). It was generally assumed that 60 K and 90 K phases corresponded to the ortho-II and ortho-I chemical phases, respectively.^{8,9} There were two possible origins of 60K-plateau proposed: one is the chemical phase separation¹⁰ and the other is purely electronic in origin.¹¹ Recent theoretical study indicated that chemical phase arguments based on chain ordering alone

can not account for the observed 60K-plateau. In stead, a chain-ordering induced charge imbalance model was used to account for the 60K-plateau.¹² The electronic scenario attributed 60K-plateau to the well-known 1/8 anomaly identified in the SrD-La214.¹³ However the analysis was, unfortunately, based on a questionable planar hole scale.^{14,15,16} The problem concerning the origin of the $T_c = 60$ K and 90 K phases and the associated plateaus in OD-Y123 are still unresolved. In this report we show that the electronic phase diagram of OD-Y123 can be understood in terms of the competition and the collaboration among the chemical phases and the PEP's.

A universal hole scale based on the thermoelectric power at 290 K (S^{290}) was constructed and used for comparing various physical properties in HTS.¹⁶ It was shown that both normal and superconducting properties can be compared consistently with systematic doping dependences among different HTS.^{16,17} We analyze the reported $T_c(\delta)$ data of OD-Y123 as a function of P_{pl} determined by the universal scale. We find that $T_c(P_{pl})$ lies on one universal curve originating at the critical hole concentration $P_c = 1/16$, while $T_c(\delta)$ lies on several curves which strongly depend on the development of the chain ordering. Further, we also find that the robust 60K- and 90K-plateaus appear at $P_{pl} \sim 1/8 = 2P_c$ and $\sim 3/16 = 3P_c$, respectively and the superconductivity is always suppressed beyond $P_{pl} = 1/4 = 4P_c$. We extracted the T_c data from the published paper, irrespective of the definition of T_c .^{5,11,13,18,19,20,21,22,23,24,25,26,27,28} A sample's P_{pl} was directly determined from the reported S^{290} data by using the universal scale.^{11,13,14,18,23,24,25,26,27,28,29} For samples with either δ or T_c reported but not S^{290} , the P_{pl} of the sample were determined from the P_{pl} vs. δ or the P_{pl} vs. T_c relation as discussed below.^{19,20,21,22,30,31,32}

In figure 1(a) we plot T_c vs. δ for OD-Y123. The $T_c(\delta)$ behavior can be roughly separated into two curves with small loop structures for $\delta < 0.47$ and $0.7 < \delta < 0.8$. Curve-1 is $T_c(\delta)$ behavior corresponding to the polycrystals,^{5,13,20,23,24} crystals^{21,22,26} and *c*-axis oriented films.²⁵ Curve-2 is $T_c(\delta)$ behavior as observed in the crystals detwinned by a uniaxial pressure of 100 MPa^{11,27} applied along *a(b)*-axis. For all the curve-1 samples, the T_c appears at $\delta \sim 0.35$, reaches the 60K-plateau for $0.47 < \delta < 0.65$ and reaches the 90K-plateau for $0.82 < \delta < 0.92$. Finally, the T_c slightly decreases for $\delta > 0.92$. For the curve-2 samples, the T_c appears at $\delta \sim 0.4$, exhibits the 60K-plateau at $0.6 < \delta < 0.75$ and reaches the 90K-plateau at $\delta \sim 0.9$. The $T_c(\delta)$ -curve of the detwinned crystals is lower than that of the curve-1 samples. However, the $T_c(\delta)$ -curve of crystals detwinned by the uniaxial pressure of 10 MPa^{22,36,37} follows that of the curve-1 samples. This indicates that the artificially prepared very long chain ordering actually suppresses the superconductivity. All of above are intrinsically consistent with the facts that the PEP's are 2D square lattice. Furthermore the report that the highest T_c in $\text{La}_{2-x}\text{M}_x\text{CuO}_4$ ($\text{M} = \text{Nd, Ca, Sr}$) system is always observed in the tetragonal phase with flat and square CuO_2 planes is also consis-

tent with the above picture.³³ Clearly superconductivity of OD-Y123 is greatly affected by the level of the chain ordering and no systematic universal behavior can be inferred from the T_c vs. δ phase diagram depicted in figure 1(a).

We plot P_{pl} vs. δ in figure 1(b). Starting from $\delta \sim 0.35$ where $P_{pl} \sim 1/16 = P_c$, the $P_{pl}(\delta)$ curve separated into three curves that merge into a common curve

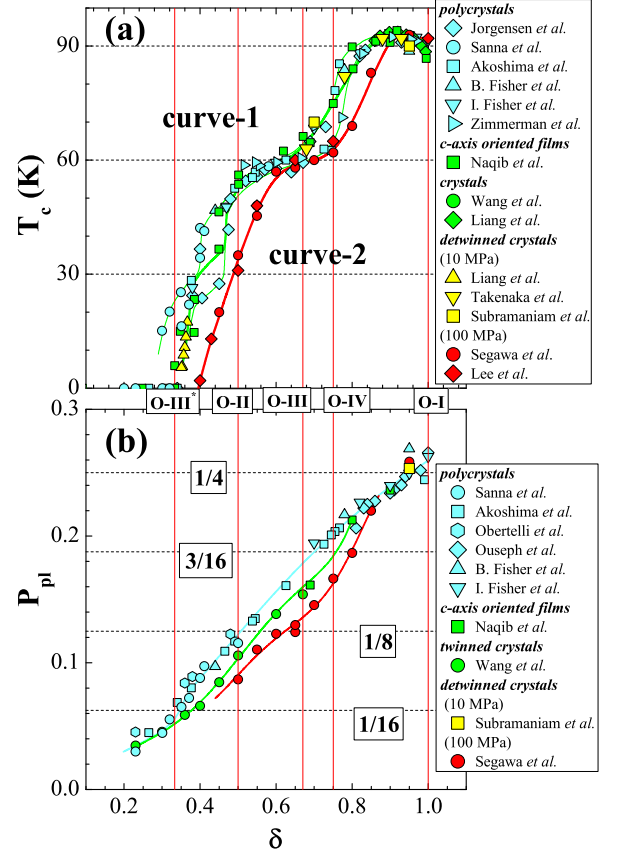


FIG. 1: (Color online) (a) Superconducting transition temperature (T_c) as a function of excess oxygen content (δ) for $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$.^{5,11,13,18,20,21,22,23,24,25,26,27,36,37} The solid curves are guide to the eyes. The solid and dotted vertical lines show the idealized chemical phases of the ortho-I (O-I), -II (O-II), -III (O-III), -IV (O-IV) and ortho-III* (O-III*). (b) Hole concentration (P_{pl}) as a function of δ for $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$.^{11,13,14,18,23,24,25,26,27,29} The dotted horizontal lines show the magic number of the hierarchy of $P_c = 1/16$. The vertical lines show the idealized chemical phases of the ortho-I (O-I), -II (O-II), -III (O-III), -IV (O-IV) and ortho-III* (O-III*). P_{pl} of all data, except of Akosima *et al.*'s work, are directly determined from the reported S^{290} by using of the universal scale in ref. 16. Akoshima *et al.* reported the δ vs. the hole concentration determined from their own S^{290} by using the scale of ref. 34. We plotted the re-determined P_{pl} by converting their used scale into our scale. The solid curves are guide to the eyes.

for $\delta > \sim 0.85$, where $P_{pl} \sim 2/9$. The upper, middle and lower curves are determined from the S^{290} of polycrystals,^{13,14,18,23,24,29} the in-plane S^{290} of twinned crystals including c -axis oriented films,^{25,26} and the S^{290} measured along a -axis (S_a^{290}) of crystals detwinned by the uniaxial pressure of 100 MPa,¹¹ respectively. P_{pl} increases monotonically with oxygen doping. The contin-

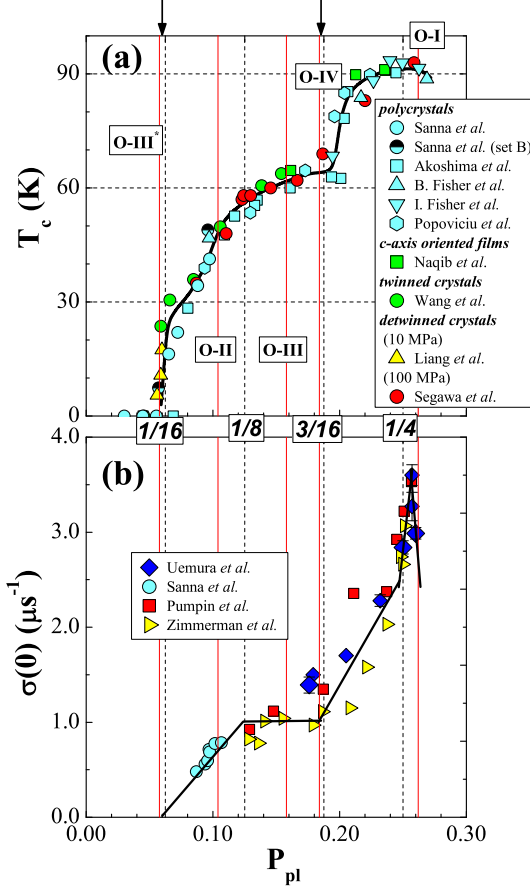


FIG. 2: (Color online) (a) T_c vs. P_{pl} for $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ (OD-Y123).^{11,13,18,19,21,23,24,25,26,27,28} The P_{pl} for T_c data with δ value alone by Liang *et al.*²¹ was determined from the P_{pl} vs. δ plot of Fig. 1(b). The second data set by Sanna *et al.* (set B) was reported in ref. 19. According to ref. 19, we can extract the lower and upper bound of δ and T_c for their OD-Y123 samples. The (δ, T_c) are (0.32, 7 K) and (0.42, 49 K). We plotted these two points by determining P_{pl} from the δ value. All other P_{pl} were directly determined from the reported S^{290} . (b) N_s vs. P_{pl} for the OD-Y123.^{19,30,31,32} P_{pl} for $\sigma(0)$ data with T_c value alone by Sanna *et al.*¹⁹ were determined from the P_{pl} vs. T_c plot of Fig. 2(a). All other P_{pl} for $\sigma(0)$ with δ and T_c ^{30,31,32} were determined from the P_{pl} vs. δ plot of Fig. 1(b). In the Fig. 2(a) and 2(b), the vertical broken lines show the magic number of the hierarchy of $P_c = 1/16$. The vertical lines show the idealized chemical phases of the ortho-I (O-I), -II (O-II), -III (O-III), -IV (O-IV) and ortho-III* (O-III*). The solid curves guide to the eyes.

uous increase in P_{pl} is not consistent with the chemical phase separation.³⁵ The common P_{pl} curve for $\delta > 0.85$ suggests, in contrast to the charge imbalance model,¹² that chain ordering has no influences on hole concentration in the CuO_2 planes. Accordingly, the S^{290} scale in ref. 16 can also be used for $\delta > 0.85$ in OD-Y123. In the δ -range from ~ 0.35 to ~ 0.85 , the planar hole concentration at the same δ values is successively suppressed in the order of the polycrystals, twinned crystals and detwinned crystals with increasing length of chain ordering. Therefore, in contrast to the common belief, the perfect chemical phase with long chains does not favor the electronic state of HTS. Hereafter, if we only know the value of δ in the OD-Y123, we estimate the P_{pl} for the polycrystals, twinned crystals and artificially detwinned crystals from the corresponding curve of P_{pl} vs. δ plot in Fig. 1(b)

In figure 2(a) we plot T_c vs. P_{pl} for OD-Y123.^{11,13,18,19,21,23,24,25,26,27,28} Surprisingly, T_c data of all samples collapsed into a single universal curve in the T_c vs. P_{pl} plot. The superconductivity appeared at $P_{pl} \sim 0.06$ ($\sim P_c$) that exhibits an extremely sharp T_c -jump to ~ 30 K followed by a broad T_c increase to 60 K at $P_{pl} \sim 0.1$. The 60K-plateau is observed between 0.12 ($\sim 2P_c$) $< P_{pl} < 0.19$ ($\sim 3P_c$). Further, the T_c suddenly jumps to ~ 90 K over ~ 0.19 ($\sim 3P_c$) and goes into the 90K-plateau for $0.21 < P_{pl} < 0.25$ ($\sim 4P_c$). Finally, the T_c decreases for $P_{pl} > 0.25$ ($\sim 4P_c$). The phase diagram is characterized by fast T_c -jumps and much flatter T_c regions in between. Noted that the sharp T_c -jumps occurred whenever the P_{pl} of a chemical phase is almost identical to that of a PEP (See two arrows in Fig. 2(a)). In contrast, the broad T_c -increase at $\sim 1/8$ seems to come from the mismatch between the P_{pl} of chemical phases to $2P_c$. The above observations suggest that the global behavior of the electronic phase diagram is dictated by the EPS of PEP's under the influences of chemical phases: the jump in T_c is due to the matching of a PEP and a chemical phase and the flat region is a two PEP's region. There are some fine structures in the T_c vs. P_{pl} plot; a “hint” of a 30 K intrinsic phase and a 30K-plateau around $P_{pl} = P_c$ and a small T_c -jump to $T_c \sim 45$ K occurred when ortho-II matched with magic doping concentration at $P_{pl} \sim 1/9$. It is also interesting to note that the intrinsic T_c 's increase as integer multiples of 30 K in the double-layer OD-Y123 in contrast to that of 15 K in the single-layer La214 system.

The above EPS picture for the 60K-plateau is further collaborated by the observation of a clear plateau of another intrinsic property, the superfluid density (N_s), of a superconductor in the same two phase region. We used N_s estimated from the low temperature muon-spin relaxation (μSR) rate $\sigma(0)$. In Fig. 2(b), we plotted $\sigma(0) \propto N_s$ vs. P_{pl} .^{19,30,31,32} While there is a slight scattering in the magnitude among the reported $\sigma(0)$, each reported $\sigma(0)$ data set have similar P_{pl} -dependence. The N_s linearly increases with doping for $\sim 1/16$ (P_c) $< P_{pl} < \sim 1/8$ ($2P_c$) followed by a clear plateau for $\sim 1/8$ ($2P_c$) $< P_{pl} < \sim 3/16$ ($3P_c$). It then linearly increases for $\sim 3/16$ ($3P_c$)

$< P_{pl} < 1/4 (4P_c)$ again, and ends with a sharp peak at $\sim 1/4 (4P_c)$. Finally, the N_S rapidly decreases for $P_{pl} > 1/4 (4P_c)$. Therefore, in superfluid density *vs.* P_{pl} plot, there is also a flat two-phase region bounded by $P_{pl} = 1/8$ and $3/16$, consistent with the co-existence of two PEP's of $2P_c$ and $3P_c$. It is interesting to point out that the famous linear T_c *vs.* N_S plot, the Uemura plot, failed to reveal the two phase region.³⁰ Therefore in order to have a physically meaningful comparison of various physical properties of HTS, it is of critical importance that the physical properties should always be plotted in terms of P_{pl} determined by the universal hole-scale.¹⁶

In summary, we have examined both the electronic-phase and chemical-phase diagrams of double-layer high temperature superconductors $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ as a function of the hole content per CuO_2 plane P_{pl} and oxygen doping concentration δ , respectively. The $T_c(P_{pl})$, regardless of the sample quality, is a universal curve originating at $P_c = 1/16$. The 60K-plateau, T_c -jump and

90K-plateau occur at a series hierarchical doping concentration based on P_c such as $P_{pl} = 2P_c$, $3P_c$ and $4P_c$. Our analysis suggests that the electronic phase diagram of T_c *vs.* P_{pl} can be understood, although modified by the chemical phases, in term of the existence and the EPS of PEP's. We conclude that there are at least two PEP's with $T_c = 60$ K at $P_{pl} = 2P_c = 1/8$ and $T_c = 90$ K at $P_{pl} = 3P_c = 3/16$. Beyond $P_{pl} = 4P_c = 1/4$, the superconductivity, such as T_c and N_S , is always suppressed. The observation of superconducting transitions at magic doping levels in the double-layer OD-Y123 and single-layer La-214 strongly suggest that the PEP's are generic intrinsic properties of all high temperature superconductors.

One of us (T.H.) would like to thank Dr. M. Tanimoto of Asahikawa Medical College for offering convincement for study. This work was supported by the state of Texas through the Texas Center for Superconductivity at the University of Houston.

-
- ¹ B. Lorenz, Z.G. Li, T. Honma, P.H. Hor, Phys. Rev. B **65**, 144522 (2002).
 - ² Y.H. Kim and P.H. Hor, Mod. Phys. Lett. B **15**, 497 (2001).
 - ³ P.H. Hor and Y.H. Kim, J. Phys.: Condens. Matter. **14**, 10377 (2002).
 - ⁴ X.L. Dong, P.H. Hor, F. Zhou and Z.-X. Zhao, cond-mat/0610864.
 - ⁵ J.D. Jorgensen *et al.*, Phys. Rev. B **41**, 1863 (1990).
 - ⁶ B.W. Veal *et al.*, Phys. Rev. B **42**, 6305 (1990).
 - ⁷ N.H. Andersen *et al.*, Physica (Amsterdam) **317-318C**, 259 (1999).
 - ⁸ H.F. Poulsen *et al.*, Nature **349**, 594 (1991); T. Zeiske *et al.*, Nature **353**, 542 (1991).
 - ⁹ G. Calestani *et al.*, IL Nuovo Cimento **19**, 1075 (1997).
 - ¹⁰ R. Beyers *et al.*, Nature **340**, 619 (1989).
 - ¹¹ K. Segawa and Y. Ando, Phys. Rev. Lett. **86**, 4907 (2001); J. Low Temp. Phys. **131**, 821 (2003).
 - ¹² T.A. Zaleski and T. K. Kopec, Phys. Rev. B **74**, 014504 (2006).
 - ¹³ M. Akoshima and Y. Koike, J. Phys. Soc. Jpn. **67**, 3653 (1998).
 - ¹⁴ S.D. Obertelli, J.R. Cooper and J.L. Tallon, Phys. Rev. B **46**, 14928 (1992).
 - ¹⁵ A. Knizhnik *et al.*, Physica (Amsterdam) **321C**, 199 (1999).
 - ¹⁶ T. Honma, P.H. Hor, H.H. Hsieh and M. Tanimoto, Phys. Rev. B **70**, 214517 (2004).
 - ¹⁷ T. Honma and P.H. Hor, Supercond. Sci. Technol. **19**, 907 (2006).
 - ¹⁸ S. Sanna, G. Allodi, G. Concas and R.De Renzi, J. Supercond. **18**, 769 (2005).
 - ¹⁹ S. Sanna *et al.*, Phys. Rev. Lett. **93**, 207001 (2004).
 - ²⁰ S. Sanna, G. Allodi, G. Concas and R.De Renzi, Solid State Commun. **126**, 85(2003).
 - ²¹ R. Liang, D.A. Bonn and W.N. Hardy, Physica (Amsterdam) **304C**, 105 (1998).
 - ²² R. Liang *et al.*, Physica (Amsterdam) **383C**, 1 (2002); R. Liang, D.A. Bonn and W.N. Hardy, Phys. Rev. B **73**, 180505(R) (2006).
 - ²³ B. Fisher *et al.*, Phys. Rev. B **47**, 6054 (1993).
 - ²⁴ I.R. Fisher *et al.*, Physica (Amsterdam) **235-240C**, 1497 (1994).
 - ²⁵ S.H. Naqib and A. Semwal, Physica (Amsterdam) **425C**, 14 (2005).
 - ²⁶ Y. Wang and N.P. Ong, Proc. Nat. Acad. Sci. U.S.A., **98**, 11091 (2001); cond-mat/0110215v1.
 - ²⁷ Y.S. Lee, K. Segawa, Y. Ando and D.N. Basov, Phys. Rev. Lett. **94**, 137004 (2005).
 - ²⁸ C.P. Popoviciu and J.L. Cohn, Phys. Rev. B **55**, 3155 (1997).
 - ²⁹ P.J. Ouseph and M.R. OBryan, Phys. Rev. B **41**, 4123 (1990).
 - ³⁰ Y.J. Uemura *et al.*, Phys. Rev. Lett. **62**, 2317 (1989); Phys. Rev. B **38**, 909 (1988).
 - ³¹ B. Pümpin *et al.*, Hyperfine Interactions **63**, 25 (1990).
 - ³² P. Zimmermann *et al.*, Phys. Rev. B **52**, 541 (1995).
 - ³³ B. Dabrowski *et al.*, Phys. Rev. Lett. **76**, 1348 (1996).
 - ³⁴ J.L. Tallon *et al.*, Phys. Rev. B **51**, 12911 (1995).
 - ³⁵ B.W. Veal and A.P. Paulikas, Physica (Amsterdam) **184C**, 321 (1991).
 - ³⁶ C.K. Subramaniam, H.J. Trodahl, A.B. Kaiser and B.J. Ruck, Phys. Rev. B **51**, 3116 (1995).
 - ³⁷ K. Takenaka, K. Mizuhashi, H. Takagi and S. Uchida, Phys. Rev. B **50**, 6534 (1994).