

Strain amplification of the $4k_F$ chain charge instability in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$

A. Rusydi,¹ P. Abbamonte,² H. Eisaki,³ Y. Fujimaki,⁴ S. Smadici,²
N. Motoyama,⁴ S. Uchida,⁴ Y.-J. Kim,⁵ M. Rübhausen,¹ and G. A. Sawatzky⁶

¹*Institut für Angewandte Physik, Universität Hamburg, Jungiusstraße 11, D-20355 Hamburg, Germany*

²*Physics Department and Frederick Seitz Materials Research Laboratory, University of Illinois, Urbana, IL, 61801*

³*Nanoelectronics Research Institute, AIST, 1-1-1 Central 2, Umezono, Tsukuba, Ibaraki, 305-8568, Japan*

⁴*Department of Superconductivity, University of Tokyo, Bunkyo-ku, Tokyo 113, Japan*

⁵*Physics Department, University of Toronto, Toronto, Canada*

⁶*Department of Physics and Astronomy, University of British Columbia, Vancouver, B.C., V6T-1Z1, Canada*

(Dated: March 23, 2022)

We have used resonant soft x-ray scattering (RSXS) to study the misfit strain in $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ (SCO), a cuprate that contains both doped spin ladders and spin chains, as well as a “control” sample without holes, $\text{La}_6\text{Ca}_8\text{Cu}_{24}\text{O}_{41}$ (LCCO). The misfit strain wave in SCO is strongly temperature (T)-dependent and is accompanied by a substantial hole modulation. In LCCO the strain wave is weaker, shows no hole modulation, and is T-independent. The observed strain wave vector, $L_c = 0.318$, is close to the $4k_F$ instability of the chain. Our results indicate that the chain charge order observed in SCO by several groups is a $4k_F$ charge density wave (CDW) amplified by the misfit strain in this material. This demonstrates a new mechanism for CDW formation in condensed matter and resolves several controversies over the transport properties of SCO.

PACS numbers:

The two-leg “spin ladder” is a simplified version of the $t - J$ model still believed by many to contain the basic physics of high temperature superconductivity. A doped spin ladder can exhibit, depending upon the parameters chosen, either exchange-driven superconductivity[1, 2] or an insulating “hole crystal” (HC) ground state in which the carriers crystallize into a static, Wigner lattice[1, 3, 4]. The interplay between these two phases follows much of the phenomenology of the competition between ordered stripes and superconductivity in two dimensions[5]. Detailed studies of spin ladders, both theoretical and experimental, are therefore critical for our understanding of superconductivity in two dimensions.

This has led to a great deal of recent work on the system $\text{Sr}_{14-x}\text{Ca}_x\text{Cu}_{24}\text{O}_{41}$ (SCCO), which contains both doped spin ladders and spin chains. The ladder and chain substructures in this material have incommensurate periods and are mated together under internal strain. At $x > 10$ this system was shown to exhibit superconductivity at pressures above 3 GPa[6]. Further, it exhibits both the transport properties and elementary excitations characteristic of a charge density wave (CDW)[7, 8]. Recently this system was shown, with resonant soft x-ray scattering (RSXS) studies, to contain a commensurate Wigner crystal of holes or “hole crystal” (HC) in the ladder substructure [9, 10].

Prior to these studies several authors, applying neutron[11] and hard x-ray scattering methods[12, 13], reported a distinct modulation of the crystal structure at low temperature which they interpreted as a CDW in the chain substructure. It was later pointed out by van Smaalen[14] that the observed superstructures index to the large unit cell of the total structure, arise naturally from the misfit strain, and are not necessarily an indication charge order. It was later shown, however, that

some of these reflections show anomalous temperature dependence and, regardless of their relation to the structure, may be a sign of charge order after all [15, 16, 17]. The exact origin of these peaks and their relationship to the ladder hole crystal reported in Refs. [9, 10] is currently a mystery. To resolve this mystery we report here a study of the chain charge order in this system with resonant soft x-ray scattering (RSXS).

Single crystals of $\text{Sr}_{14}\text{Cu}_{24}\text{O}_{41}$ (SCO) and control samples of $\text{La}_6\text{Ca}_8\text{Cu}_{24}\text{O}_{41+\delta}$ (LCCO), which have no doped holes, were grown by traveling solvent floating zone techniques described in Ref. [18]. The surfaces were prepared in the manner described in Ref. [9] and the samples were characterized *in situ* with x-ray absorption spectroscopy (XAS) at the O_{K} and $\text{Cu}L_{3,2}$ edges. RSXS and XAS measurements were carried out on the soft x-ray undulator beamline X1B at the National Synchrotron Light Source using a 10-axis, vacuum-compatible diffractometer. The energy resolution in the range of interest was about 200 meV. We denote periodicity with Miller indices of the chain, i.e. (H, K, L_c) denotes a momentum transfer $\mathbf{Q} = (\frac{2\pi}{a}H, \frac{2\pi}{b}K, \frac{2\pi}{c_c}L_c)$ where $a = 11.47 \text{ \AA}$, $b = 13.35 \text{ \AA}$, and $c = 27.3 \text{ \AA} \approx 7c_L \approx 10c_c$ [16].

Polarization-dependent XAS at the O_{K} edge of SCO and LCCO, taken *in situ* at room temperature, are shown in Fig. 1(a). These results are consistent with previous studies [19] and indicate good surface quality. Like the high temperature superconductors, SCO is a charge transfer insulator in the Zaanen-Sawatzky-Allen (ZSA) classification scheme[20], therefore the doped holes have $\text{O}2p$ character. A recent reexamination of the polarization-dependent XAS [21] suggests that the doped holes in SCO consist of three mobile carrier peaks (MCP) - a chain MCP at 528.1 eV, a ladder rung MCP at 528.3 eV, and a ladder leg MCP at 528.6 eV. The higher energy

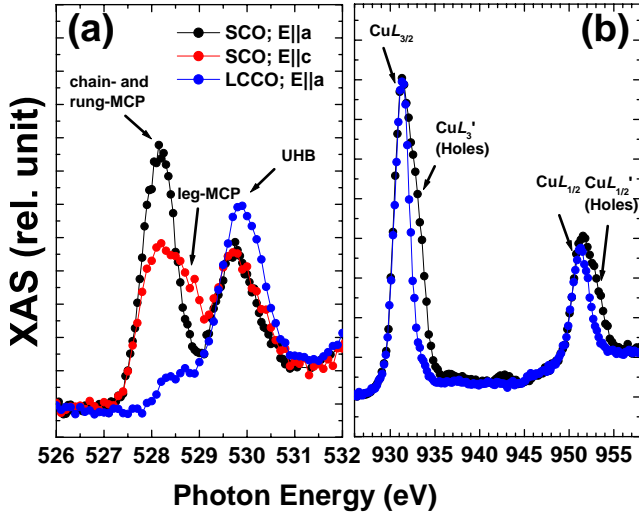


FIG. 1: Polarization dependent XAS of SCO and LCCO at 300 K (a) OK edge and (b) CuL edge.

feature at 530 eV is assigned to transitions into the upper Hubbard band (UHB) i.e. the $\text{Cu}3d$ orbitals, through $p-d$ hybridization. In contrast to SCO, in LCCO the doped hole features are absent which is consistent with the expectation that it is a zero hole system. Note that the UHB feature in LCCO is, correspondingly, stronger, indicating that spectral weight is transferred with doping in this system as in other cuprates[22].

Figure 1(b) shows the corresponding XAS at the CuL edge, also taken at room temperature. The CuL edge consists of two peaks at 931 eV and 951 eV which are transitions into the $3d$ band from a core $2p$ level with $j=3/2$ or $1/2$, respectively. The main difference between the two samples is the presence of a ligand hole side band at 933 eV and 953 in SCO which is absent in the undoped LCCO. The spectral weight in this side band can be considered a measure of the doped hole density. The XAS at both the $\text{Cu}L_{3/2}$ and the $\text{Cu}L_{1/2}$ edges was found to be polarization-independent in the ac -plane for both samples.

The first RSXS measurements were carried out on SCO at the OK edge. In this measurement the x-ray energy was tuned to 528.4 eV at which scattering from the holes is enhanced by a factor of 10^3 [9, 10, 23, 24, 25]. We first looked for a Bragg reflection at $L_c = 0.20$ as was reported previously[13]. Figure 2 shows a reciprocal space scan from $(H, K, L_c) = (0, 0, 0.1)$ to $(0, 0, 0.23)$. A reflection at $L_c = 0.142$ is visible ($L_L = 0.2$), which is the previously reported hole crystal in the ladder[9]. No reflection was observed near $(0, 0, 0.2)$. It would also be desirable to search for a Bragg reflection at $L_c = 0.25$ as had been reported in ref. [12]. However this point in reciprocal space cannot be reached at the OK edge. We therefore turned to the $\text{Cu}L'_{3/2}$ edge ($\omega = 933$ eV). At this edge the chain and ladder holes cannot be distinguished because of its larger radiative broadening. However its higher

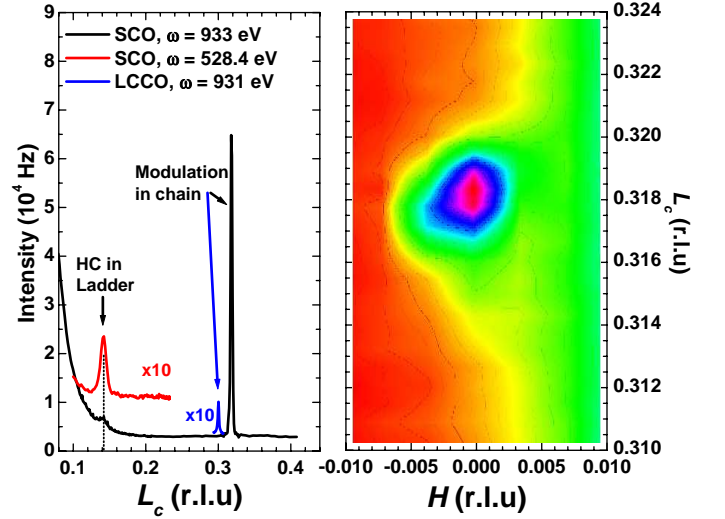


FIG. 2: (left) Widescans of L of SCO and LCCO with different photon energies. (right) HL-map of the chain modulation of SCO at $T = 28$ K.

energy allows larger Q values to be reached.

Figure 2 (left) shows an L_c scan from $(H, K, L_c) = (0, 0, 0.075)$ to $(0, 0, 0.4)$ at $\omega = 933$ eV. The ladder hole crystal is again observed. No reflection was observed at either $L_c = 0.25$ or 0.20 . Interestingly, however, we observed an incommensurate reflection at $L_c = 0.318 \pm 0.005$ (or $L_L = 0.454$ in ladder units). This reflection was mapped in the (H, L) plane, shown in Fig. 2 (right), giving its coherence lengths $\xi_c = 1100 \pm 100 \text{ \AA}$ (~ 400 chain units) along the chain direction and $\xi_a = 983 \pm 100 \text{ \AA}$, i.e. ~ 87 neighbouring chains. It was also observed in the zero-hole sample LCCO at $L_c = 0.300 \pm 0.005$. This reflection was observed previously by Hiroi *et al.* [26] and identified, on the assumption that the chain structures are more flexible than the ladders, as a misfit strain reflection from the chain layer. We will accept this assignment and assume the modulation occurs in the chain.

Our central result is the “resonance profile” (RP) of these chain modulation peaks, i.e. their energy dependence through the $\text{Cu}L'_{3/2}$ edge, shown in Fig. 3. These data were taken at $T = 20$ K. In SCO the RP consists of a strong resonance peak at 933 eV preceded by a weak resonance at 930 eV. The former coincides with the doping-dependent sideband and indicates the presence of a significant hole modulation [9, 10]. The latter, occurring at lower energy, is likely due to the misfit strain modulation (see below). Evidently this chain Bragg reflection is not a simple misfit strain wave; it has a large charge modulation so has the character of a CDW. By contrast, the same reflection in LCCO, also shown in Fig. 3, is much weaker and exhibits no hole resonance. In this sample the chain modulation appears to be a simple strain wave.

To characterize the chain modulation we wish to quantify the relative sizes of the charge and strain modulations. Because the two coexist they coherently interfere, which strongly influences the line shapes in Fig. 2. Re-

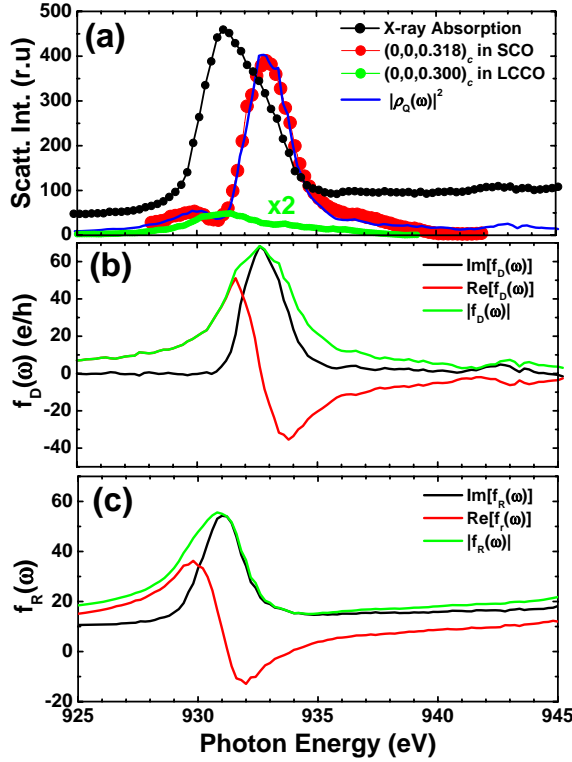


FIG. 3: (a) A comparison of integrated Bragg intensity with XAS of SCO and LCCO. Black circles, red circles and, green circles and blue line are XAS, resonance profile (RP) of $(0,0,0.318)_c$ of SCO, RP of $(0,0,0.300)_c$ of LCCO, and scattering simulation. The XAS are taken at room temperature (298 K) with $E||a$ while the RP at 20 K. (b) $f_D(\omega)$ for hole and (c) $f_R(\omega)$ for structural (see text for detail). Spectra were placed on an absolute scale by fitting to tabulated values [29] far from the edge.

cently Abbamonte [27] demonstrated a method for using this interference to determine the relative size, W , and phase ϕ of the two modulations. In this method one divides the atomic scattering factor into two parts, $f(\omega, v) = f_R(\omega) + v f_D(\omega)$, where f_R is the “raw” atomic scattering factor and f_D is the scattering factor of the doped holes. These two quantities can be determined from doping-dependent XAS measurements, such as that in Fig. 1 (a,b), by applying the relation

$$\text{Im}[n(\omega, v)] = -\frac{r_e \lambda^2}{2\pi V_{\text{cell}}} \text{Im}[\sum_i f_i(\omega, v)], \quad (1)$$

solving a system of equations at each energy point, and applying a Kramers-Kronig transform. Here $\text{Im}[n]$ is the absorptive part of the refractive index (linearly related to XAS spectra), r_e is the classical electron radius, λ is the x-ray wavelength, and f_i is the atomic scattering factor. The integrated intensity of the charge reflection is proportional to the quantity $|v_0 f_D(\omega) \exp i\phi/2 + iQ u_0 f(\omega, <v>)|^2$, where $<v>$ is the average atomic valence, v_0 is the charge modulation amplitude, u_0 is the (longitudinal)

strain amplitude, Q is the wave vector of the CDW, and ϕ is their relative phase. A fit to the resonance profile yields values for ϕ and the ratio $W = v_0/u_0$. The latter is a measure of the degree to which the CDW is driven by interactions rather than structural effects[27].

To apply this method we used the data in Fig. 1 (b) to determine $f_R(\omega)$ and $f_D(\omega)$ for Cu[30] in this system. Because the Cu atoms in the chains and ladders cannot be distinguished in XAS we simply take $<v> = 0.25$ for SCO and $<v> = 0$ for LCCO and assume the resulting form factors are valid for all Cu atoms in the sample. The results are summarized in Figure 3. We find that the doped-hole form factor $|f_D| = 67$ electrons per hole on the resonance maximum. That is, at this resonance a doped hole scatters as strongly as a Ho atom.

The best fit to the RP in SCO is shown in Fig 3(a). Carrying out this fit, we find that the apparent two-peak structure of the RP is actually due to destructive interference between the charge and strain waves due to the phase offset between them. The fit yields the values $W = 1.13 \text{\AA}^{-1}$ and $\phi = -22.5^\circ$. By contrast, the RP for LCCO simply tracks its XAS spectrum. In this case a hole amplitude is not definable and the fit yields $W \sim 0$ and ϕ undefined. In ref. [27] it was suggested that for a conventional Peierls CDW $W \sim 1 \text{\AA}^{-1}$ whereas for a more “exotic” CDW, such as the static stripe in $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$, $W > 10 \text{\AA}^{-1}$. We conclude that in LCCO the chain modulation is a pure misfit strain wave. In SCO, however, the modulation is a cooperative amplification of the misfit strain and an incipient CDW with the same wave vector.

This picture is further justified by the temperature dependence. L_c scans in both SCO and LCCO were carried out at different temperatures (see Fig. 4(a-i) to (a-iii)). In SCO a pronounced decrease is observed upon warming, indicating that the modulation has some character of a CDW transition. Unlike a conventional CDW, however, the intensity never goes completely to zero; as the temperature rises it levels off to a constant value. In LCCO, by contrast, the peak intensity is virtually temperature-independent. This phenomenology is additional evidence that the chain modulation in LCCO is a simple misfit strain wave, but in SCO it is a cooperative effect between strain and a CDW.

In the case of SCO it was possible to determine ϕ , therefore we can sketch the relationship between the charge and strain modulations (Fig. 4(b)). We find that the charges tend to accumulate on the “crest” of the strain wave. In a simple sinusoidal picture one might expect, by symmetry, that the charges would cluster in regions where the strain is either maximum or minimum, i.e. $\phi = \pm 90^\circ$. Evidently in the current case the symmetry is broken, most likely by strong anharmonicity of the modulation as evidenced by the large number of harmonics visible in electron diffraction [26].

The presence of a strain-stabilized chain CDW at higher temperature may explain the discrepancy between results of low-frequency dielectric spectroscopy [7] and

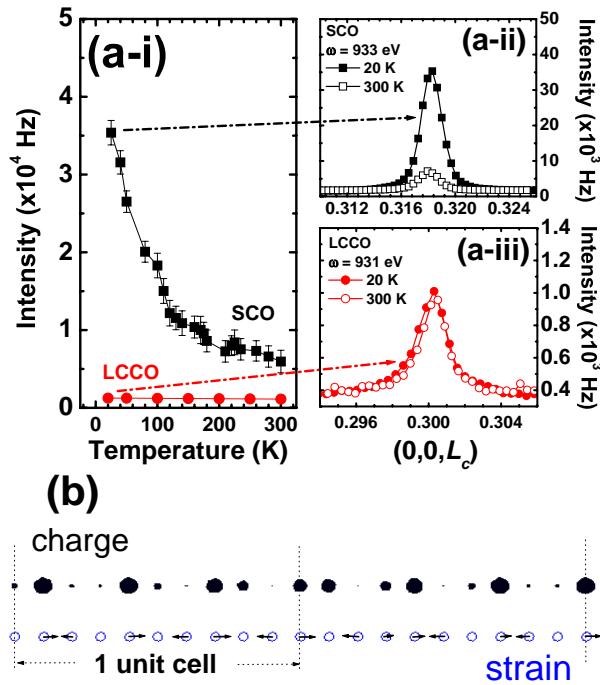


FIG. 4: (a-i) Temperature dependence of SCo and LCCO. (a-ii) L -scans for selected temperature, 20 K and 300 K, of (a-ii) SCo and (a-iii) LCCO. (b) Interplay between strain and charge modulation in SCo. Black and blue circles are the charge and strain modulation, respectively. The size of the circles represents the amplitude and the arrows represent the direction of the lattice distortion.

Raman scattering [8] studies of this compound. Vuletić *et al.* [7] found that the onset temperature of the CDW is about 210 K which is similar to the onset temperature of the HC in ladders found with RSXS [9]. Blumberg

et al. [8], however, found evidence for the presence of a CDW even up to the highest measured temperature, 630 K. We propose here that the Raman results of Blumberg arise from fluctuations in this chain modulation, in which the CDW can persist to very high temperature because of the stabilizing effect of the misfit structure.

Finally, we point out an important connection between the wave vector of this reflection, the wave vector of the ladder hole crystal reported previously [9, 10], and the hole count in the chains and ladders of SCo [21]. We recently reported a reexamination of the hole density in this system with polarization-dependent XAS. We concluded that, in SCo, 2.8 out of 6 holes reside in the ladders [21], giving $\delta_L = 0.2$. This number is much higher than previous estimates [19, 28] and is more sensible given the ladder hole crystal wave vector of $L_L = 0.2$. Here we point out that this study also implies the chain hole density is $\delta_c = 3.2/10 = 0.32$, which is very close to the current observed wave vector of $L_c = 0.318$. In other words the wave vector of the chain modulation we report here is very close to its $4k_F$ instability. We therefore conclude that the chain modulation in SCo is an interplay between the misfit strain and the $4k_F$ instability of the chain holes.

We acknowledge helpful discussions with S. van Smaalen, M. von Zimmermann and A. Gozar. This work was supported by the Helmholtz Association contract VH-FZ- 007, the Netherlands Organization for Fundamental Research on Matter (FOM), and the Office of Basic Energy Sciences, U.S. Department of Energy under Grant No. DE-FG02-06ER46285, with use of the NSLS was supported by contract No. DE-AC02-98CH10886. G.A.S. was supported by the Canadian Natural Science and Engineering Council, Foundation for Innovation, and Institute for Advanced Research.

-
- [1] E. Dagotto *et al.*, Phys. Rev. B, 45, 5744 (1992)
 - [2] T. Siegrist *et al.*, Mater. Res. Bull. 23, 1429 (1988)
 - [3] S.R. White *et al.*, Phys. Rev. B 65, 165122 (2002)
 - [4] S. T. Carr A. M. Tsvelik, Phys. Rev. B 65, 195121 (2002)
 - [5] J. M. Tranquada *et al.*, Phys. Rev. Lett. **78**, 338 (1997)
 - [6] M. Uehara *et al.*, J. Phys. Soc. Jpn 65, 27642767 (1996)
 - [7] T. Vuletić *et al.*, Phys. Rev. Lett. 90, 257002 (2003)
 - [8] G. Blumberg *et al.*, Science 297, 584 (2002)
 - [9] P. Abbamonte, G. Blumberg, A. Rusydi, A. Gozar, P. G. Evans, T. Siegrist, L. Venema, H. Eisaki, E. D. Isaacs, & G. A. Sawatzky, Nature 431, 1078 (2004)
 - [10] A. Rusydi *et al.*, Phys. Rev. Lett. 97, 016403 (2006)
 - [11] M. Matsuda *et al.*, Phys. Rev. B 54, 12 199 (1996)
 - [12] D. E. Cox *et al.*, Phys. Rev. B 57, 10 750 (1998)
 - [13] T. Fukuda *et al.*, Phys. Rev. B, 66, 12104 (2002)
 - [14] S. van Smaalen, Phys. Rev. B 67, 026101 (2003)
 - [15] M. Braden *et al.*, Phys. Rev. B 69, 214426 (2004)
 - [16] J. Etrillard *et al.*, Physica C 403, 290296 (2004)
 - [17] M. v. Zimmermann *et al.*, Phys. Rev. B 73, 115121 (2006)
 - [18] N. Motoyama *et al.*, Phys. Rev. B **55**, R3386 (1997)
 - [19] N. Nücker *et al.*, Phys. Rev. B, 62, 14384-14392 (2000)
 - [20] J. Zaanen *et al.*, Phys. Rev. Lett. 55, 418 (1985)
 - [21] A. Rusydi *et al.*, accepted for Phys. Rev. B (cond-mat/0604101) (2006)
 - [22] C.T. Chen *et al.*, Phys. Rev. Lett 66, 102 (1991)
 - [23] P. Abbamonte, L. Venema, A. Rusydi, G. A. Sawatzky, G. Logvenov, and I. Bozovic, Science, 297, 581 (2002)
 - [24] P. Abbamonte, A. Rusydi, S. Smadici, G. Gu, G. A. Sawatzky, and D. L. Feng, Nature Phys., 1, 155 (2005)
 - [25] A. Rusydi, Resonant soft x-ray scattering and charge density waves in correlated systems, Ph.D dissertation, University of Groningen, 2006
 - [26] Z. Hiroi *et al.*, Phys. Rev. B 54, 15849 (1996)
 - [27] P. Abbamonte, Phys. Rev. B 74, 195113 (2006)
 - [28] T. Osafune *et al.*, Phys. Rev. Lett. **78**, 1980 (1997).
 - [29] B. L. Henke, E. M. Gullikso, and J.C. Davis, X-ray interactions: photoabsorption, scattering, transmission, and reflection at $E=5030000$ eV, $Z=192$. At. Data Nucl. Data Tables 54, 181342 (1993).
 - [30] The scattering factors in general are tensors, however at the $\text{Cu}L_{3/2}$ edge they are isotropic in the (a,c) plane. So we will treat them as scalars here.