

Evidence for a single hydrogen molecule connected by an atomic chain

M. Kiguchi,¹ R. Stadler,² I. S. Kristensen,² D. Djukic,¹ and J. M. van Ruitenbeek^{1,*}¹Kamerlingh Onnes Laboratorium, Universiteit Leiden,
PO Box 9504, NL-2300 RA Leiden, The Netherlands²Center for Atomic-scale Materials Physics, Department of Physics,NanoDTU, Technical University of Denmark, DK-2800 Kgs. Lyngby, Denmark
(Dated: April 15, 2024)

Stable, single-molecule conducting-bridge configurations are typically identified from peak structures in a conductance histogram. In previous work on Pt with H_2 at cryogenic temperatures it has been shown that a peak near $1 G_0$ identifies a single molecule Pt- H_2 -Pt bridge. The histogram shows an additional structure with lower conductance that has not been identified. Here, we show that it is likely due to a hydrogen decorated Pt chain in contact with the H_2 molecular bridge.

PACS numbers: 73.63.Rt, 63.22.+m, 73.23.-b, 85.65.+h

The interest in chains of single metal atoms bridging between two electrodes is largely due to their unique properties as ideal one-dimensional systems [1]. For clean metals, only Au, Pt and Ir form atomic chains [2, 3]. However, atomic or molecular adsorption on metal surfaces can widen this scope. Recently, 2 nm long Ag atomic chains have been created in the presence of oxygen at ultra low temperature, while clean Ag only forms short chains [4]. Atomic chains have been imaged by transmission electron microscope (TEM) for the noble metals Cu, Ag, and Au [5, 6, 7, 8].

These atomic wires could form ideal leads to organic molecules for the investigation of their potential use in molecular electronics [9]. The first experiments contacting molecules by Pt atomic leads appear to indicate that atomic chain formation is suppressed by the molecular adsorption [10, 11]. In the latter works it was shown that a single hydrogen molecule, H_2 , can be contacted between Pt leads. The hydrogen molecule is a valuable model system for single-molecule junctions. By use of point contact spectroscopy, isotope substitution and shot noise measurements the system was characterized in great detail and close agreement with atomistic model calculations was obtained [10, 11]. The Pt- H_2 -Pt junction was first identified by its conductance. It shows up as a recurring plateau in the conductance when controllably breaking a contact, and in a histogram of conductance values collected for many such breakings it gives rise to a sharp peak near $1 G_0$, where $1 G_0 = 2e^2/h$ is the conductance quantum. This main peak at $1 G_0$ for the Pt/ H_2 system is therefore well understood. However, there is more structure in the conductance histogram for the Pt/ H_2 junctions, which has not been explained. In particular, a strong peak is found at about 0.1 - $0.2 G_0$, suggesting that other configurations of hydrogen between Pt leads may be formed. In the present study we focus on those structures, having a conductance below $1 G_0$, and we present evidence that they can be attributed to the formation of a hydrogen decorated Pt atomic chain, that forms one of the leads contacting a hydrogen molecule.

The measurements have been performed using the mechanically controllable break junction technique (see Ref. 12 for a detailed description). Once under vacuum and cooled to 4.2 K a fine Pt wire was broken. Atom-sized contacts between the wire ends can be formed using a piezo element for fine adjustment. H_2 was admitted via a capillary. DC two-point voltage-biased conductance measurements were performed by applying a voltage in the range from 10 to 150 mV. Every statistical data set (such as a conductance histogram) was built from a large number (over 3000) of individual digitized conductance traces. AC voltage bias conductance measurements were performed using a standard lock-in technique. The conductance was recorded for fixed contact configuration using an ac modulation of 1 mV amplitude and a frequency of 7.777 kHz, while slowly ramping the DC bias between -100 and + 100 mV.

Figures 1 (a) and (b) show typical conductance traces for clean Pt and for Pt after admitting H_2 . After admitting H_2 , plateaux near $1 G_0$ are frequently observed and the corresponding histogram (Fig. 1 (c)) shows a sharp feature near $1 G_0$. The plateaux near $1 G_0$ and the corresponding peak in the histogram originate from single-molecule Pt- H_2 -Pt contacts, as shown by previous studies [10, 11]. In addition to the $1 G_0$ feature, the histogram shows a peak near $0.2 G_0$ on top of a low-conductance tail. Looking at the individual traces, we find that the conductance does not suddenly drop, as expected for a contact break after the appearance of the plateau near $1 G_0$, but rather decreases by small steps while the contact is being stretched. This suggests that a structure having a conductance below $1 G_0$ is formed by further stretching the single-molecule Pt- H_2 -Pt contact. The conductance trace in Fig. 1 (b) shows that the structure can be stretched to quite long lengths (> 0.5 nm in Fig. 1 (b)), which suggests the formation of an atomic chain.

In order to investigate the chain formation, we measure the length histogram of the last plateau and the return length distribution. Figure 2 (a) shows the length histogram for the final conductance plateaux for the Pt/ H_2

contacts (filled grey distribution), and this is compared to a length histogram for clean Pt. The length for Pt/H₂ is taken here as the distance between the points at which the conductance drops below 1.3 G₀ and 0.1 G₀, respectively, while for clean Pt the boundaries are 2.5 G₀ and 1.0 G₀. The former boundaries are set such as to capture the length of the 1G₀-plateau plus the subsequent structures that give rise to the peak around 0.2 G₀ in the conductance histogram. It is striking that the Pt/H₂ contact can be stretched as long as 0.8 nm. A sequence of peaks is observed in the Pt/H₂ length histogram of Fig. 2(a), indicating the repeated occurrence of certain stable chain configurations that we identify as (A), (B), and (C). The distance between the peaks is 0.27 ± 0.01 nm, which is slightly larger than the Pt-Pt distance of a clean Pt atomic chain (0.23 nm) [3].

The inset of Fig. 2(a) shows the average return lengths as a function of chain length. This is the distance over which the two electrodes need to be moved back after the junction breaks in order to re-establish contact, averaged over many break cycles. Apart from an offset of 0.3 nm due to the elastic response of the banks [3], the relation is approximately proportional, suggesting that a fragile structure is formed with a length corresponding to that of the last plateau, which is unable to support itself when it breaks and collapses onto the banks on either side.

We further test this interpretation by analyzing the stretch length dependence of the conductance and by point contact spectroscopy. Figure 2(b) shows the average conductance for Pt/H₂ junctions as a function of the chain length. The curve is obtained by adding all measured conductance traces from the start value (1.3 G₀) onward, and dividing at each length by the number of traces included at that point. The mean conductance decreases rapidly as the chain becomes longer. Although the conductance for a pure Pt chain also decreases with length [13] its conductance stays well above 1 G₀. This fact, combined with the larger peak distance in the length histogram indicate that the structure with lower conductance is probably not a clean Pt atomic chain, and may

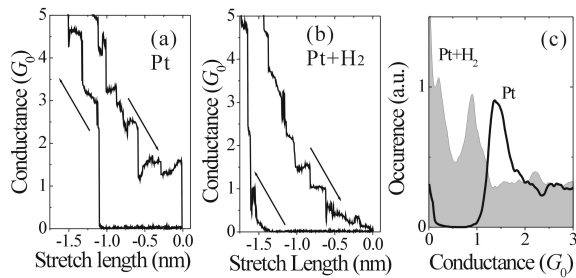


FIG. 1: Breaking and return traces for clean Pt (a), and for Pt in a H₂ atmosphere (b). Many of such curves are collected into conductance histograms as shown in (c) for clean Pt (black curve) and Pt in H₂ (filled graph).

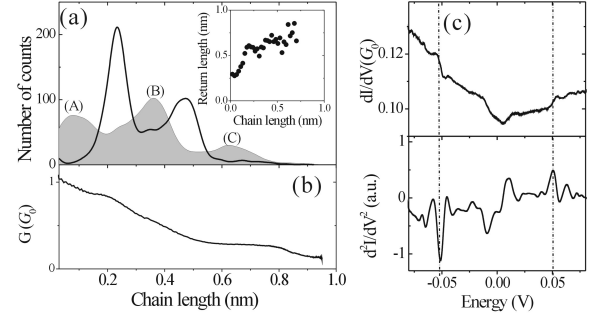


FIG. 2: (a) Length histogram for clean Pt (black curve) and Pt in H₂ (filled graph). The start and stop values between which the lengths were measured were taken as (2.5, 1.0) for Pt and (1.3, 0.1) for Pt/H₂, in units of G₀. Inset: Average return lengths as a function of chain length. (b) Average conductance as a function of chain length for Pt/H₂. (c) Differential conductance (top) and its derivative (bottom) for a Pt/H₂ contact taken at a conductance of 0.1 G₀.

be due to a hydrogen decorated atomic chain. The average conductances of structures (A), (B), and (C) are 0.96, 0.56 and 0.28 G₀, respectively. Since the conductance of structure (A) is close to 1 G₀, we identify it with the single molecule Pt-H₂-Pt contacts that have been studied previously [10, 11]. We discuss the new structures (B) and (C) that arise by further stretching of the Pt-H₂-Pt junction in the following. Note that a stable level near 0.2-0.3 G₀ is observed at 0.6-0.8 nm in length in Fig. 2(b). The slow length dependence gives rise to a high number of counts in a conductance histogram, which explains the peak at 0.2 G₀ in Fig. 1(c). Apart from this stable structure that we have labelled (C) the length histogram points at an intermediate structure (B), for which the conductance varies more strongly with stretching.

Figure 2(c) shows an example of the differential conductance and its derivative for a Pt/H₂ contact taken at a conductance of 0.1 G₀. The spectrum shows an increase in the differential conductance symmetrically at 51 meV, and clear symmetric peaks are observed in the second derivative, d²I=dV². The symmetric peaks are commonly observed near 57 ± 4 meV in the second derivatives for contacts having conductances in the range 0.6-0.1 G₀. Note that the sign of the signal in Fig. 2(c) agrees with that for inelastic electron tunnelling spectroscopy, as expected for low conductance [14]. However, most signals that we find are of the type discussed in Ref. 15. The energy of 57 meV agrees with the energy of the transverse translation mode of the molecule in the Pt-H-H-Pt configuration [11]. The close agreement suggests that a hydrogen molecule is still bridging the junction after stretching it beyond the 1 G₀ plateau.

Based on the experiments presented above we arrive at the following chain formation model for Pt atomic contacts with H₂. First, a single hydrogen molecule is

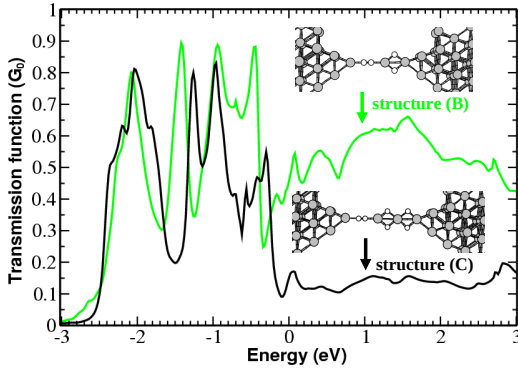


FIG. 3: (Color online) Transmission functions for the proposed structures (B) (green/gray curve) and (C) (black curve), respectively, as calculated from DFT for a setup with bulk electrodes and a (111) surface with a pyramid of Pt atoms on top. The zero point of the x-axis is the Fermi energy. The explicit geometries of the structures are shown as insets.

adsorbed between Pt electrodes (structure A). Further stretching induces the incorporation of the first Pt atom from the stem part of the electrode into the chain (structure B). Then, the second Pt atom is incorporated into the chain (structure C), and the atomic chain is formed with a single hydrogen molecule bridging. The larger distances in the length histogram and the low conductance should then be attributed to additional hydrogen decorating the Pt atomic chain. Further support for this chain formation process is obtained from density functional theory (DFT) calculations.

Electronic structure calculations were performed using a plane wave implementation of DFT [16] with an energy cutoff of 340 eV, where we used ultra-soft pseudopotentials [17], and a PW91 parametrization for the exchange and correlation functional [18]. The transmission functions of the molecular junctions were calculated using a general non-equilibrium Green's function formalism for phase-coherent electron transport [19], where both, the Green's function of the scattering region and the self-energies describing the coupling to the semi-infinite electrodes, were evaluated in terms of a basis consisting of maximally localized Wannier functions [20]. In our calculations the supercells for the scattering region are defined by 3 × 3 atoms in the surface plane and contain three to four surface layers on each side of the molecule. We used a 4 × 4 grid for the k-point integration in order to obtain well converged results for the conductance [21].

Based upon the distances and conductances found in the experiment presented above we came to consider the model structures for (B) and (C) illustrated by the insets in Fig. 3. The figure shows calculated transmission functions for structures (B) and (C) as a function of energy. The transmission function for structure (A), a hydrogen bridge with no additional hydrogen having a conductance

of $1 G_0$ [22] is lowered when going from (A) to (C). The conductances are found as 0.46 and $0.15 G_0$ for structures (B) and (C), respectively, which is in reasonable agreement with the experimental values of 0.6 and $0.3 G_0$. The theoretical values have been obtained after optimizing the distance between the contacts by total energy minimization and the optimal length of a Pt wire segment decorated with additional hydrogen was found to be 0.272 nm which agrees with the experimental results.

Our analysis shows that this reduction is due to the additional hydrogen atoms saturating the s-orbital and part of the d-orbitals between the Pt atoms they are attached to, thereby making them unavailable for electron transport. This is illustrated in Fig. 4(a) that shows the results of calculations for the H_2 bridge structure without additional hydrogen. We have simulated the effect hydrogen addition might have by cutting out Pt Wannier functions from the scattering Hamiltonian. The removal of the Pt s-orbital for one and two subsequent wire atoms (shown only for the first case in Fig. 4(a)) accounts for the successive reduction of the transmission at around 1 eV and higher above the Fermi level. For the reduction of the transmission directly at E_F and therefore the conductance, also a blocking of some of the d-orbitals is needed, which is also shown in Fig. 4(a). Although a cutting of the d-Wannier functions of the first Pt-atom alone does not have a large effect on the conductance and seems to even enhance it, the conductance is drastically reduced if both the s- and d-orbitals of the same Pt atom are blocked. For structure (B) we also compared the transmission functions of the atomic wire system with that of the more realistic surface calculation in Fig. 3. Qualitatively, the results are similar in terms of the main peak structure illustrating that the analysis is robust with respect to details of the atomic arrangement. In a quantitative comparison, however, the conductance from the surface calculation is higher than for the wire system by approximately a factor 2.0.

In Fig. 4(b) we show the dependence of the conductance with increasing the distance between the wire electrodes. In these calculations the positions of all hydrogen atoms and four Pt atoms on each side have been fully relaxed. The corresponding binding energy of the H_2 bridge molecule to the wires is also shown for comparison. Although there is a short plateau in the conductance for structure (B) when stretched beyond the optimal bonding distance (green/grey curves in Fig. 4(b)), for structure C (black curves) the overall decrease with the length seems to be slower up to a stretching length of 0.1 nm. This trend was also found in the experimental histogram. The shift in optimal distance between (B) and (C) just reflects the increase of the total cell length due to the expansion of a second wire segment.

Let us comment on the path that may lead to the structures discussed above. Since the bridging H_2 molecule is very weakly bound to the Pt electrodes, 'wire pulling'

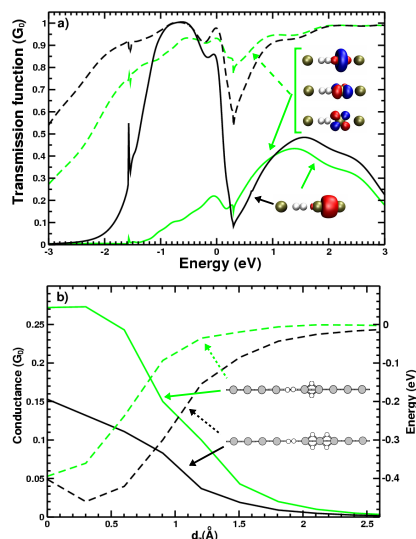


FIG. 4: (Color online) (a) Transmission functions obtained from calculations of a single H_2 bridge between wires of Pt atoms with the s-orbital (solid black curve), the d-orbitals (dashed green/grey curve), both the s- and d-orbitals (solid green/grey curve) and no atomic orbitals (dashed black line) removed from the Hamiltonian. The removed orbitals are also shown superimposed with the atomic positions in the insets. (b) Conductance (solid curves) and binding energy (dashed curves) for the molecule inside the junction for structures similar to (B) (green/grey) and (C) (black) assumed to have linear atomic wire arrangements as shown in the insets.

seems to be unlikely. Structures (B) and (C) can only be formed by a concerted process. Such a process may involve the displacement of Pt atoms at the surface due to phonons and the formation of intermediate structures with the additional hydrogen adsorbed on the electrodes. The conformational space for covering all possibilities for atomic movements in such a process is too large to be explored by our calculations in detail.

In conclusion, the experimental evidence shows that a Pt- H_2 -Pt single-molecule junction can be stretched further into forming an atomic wire. We propose a likely structure for this wire in terms of a Pt atomic chain decorated with hydrogen. This interpretation is supported by DFT calculations. While the pathway that brings new atoms into the atomic chain structure remains problematic, we obtain fair agreement in the numbers for the bond distances and the conductances.

We are very grateful to K. W. Jacobsen for his support and for many stimulating discussions. This work is part of the research program of the Stichting FOM, which is financially supported by NWO. The Center for Atomic-scale Materials Physics at NanoDTU is sponsored by the Danish National Research Foundation. We acknowledge support from the Nano-Science Center at the University of Copenhagen and from the Danish Center for Scientific Computing through Grant No. HDW-1101-05.

^y Electronic mail address: ruitenbeek@physics.leidenuniv.nl

- [1] R. E. Peierls, *Quantum Theory of Solids* (Clarendon, Oxford, 1964).
- [2] S. R. Bahn and K. W. Jacobsen, *Phys. Rev. Lett.* **87**, 266101 (2001).
- [3] R. H. M. Smit, C. Untiedt, A. I. Yanson, and J. M. van Ruitenbeek, *Phys. Rev. Lett.* **87**, 266102 (2001). A. I. Yanson, G. R. Bollinger, H. E. van den Brom, N. Agraït, and J. M. van Ruitenbeek, *Nature* **395**, 783 (1998).
- [4] W. H. A. Thijssen, D. M. Arjenburgh, R. H. Bremmer, J. M. van Ruitenbeek, *Phys. Rev. Lett.* **96**, 026806 (2006).
- [5] H. Ohnishi, Y. Kondo, and K. Takayanagi, *Nature* **395**, 780 (1998).
- [6] V. Rodrigues and D. Ugarte, *Phys. Rev. B* **63**, 073405 (2001).
- [7] V. Rodrigues, J. Bettini, A. R. Rocha, L. G. C. Rego, and D. Ugarte, *Phys. Rev. B* **65**, 153402 (2002).
- [8] J. C. Gonzalez, V. Rodrigues, J. Bettini, L. G. C. Rego, A. R. Rocha, P. Z. Coura, S. O. Dantas, F. Sato, D. S. Galvao, and D. Ugarte, *Phys. Rev. Lett.* **93**, 126103 (2004).
- [9] J. M. van Ruitenbeek, E. Scheer, and H. Weber, *Introducing Molecular Electronics*, ed. G. Cuniberti, G. Fagas and K. Richter (Heidelberg: Springer, 2005) p253
- [10] R. H. M. Smit, Y. Noat, C. Untiedt, N. D. Lang, M. C. van Hemert and J. M. van Ruitenbeek, *Nature* **419**, 906 (2002).
- [11] D. Djukic, K. S. Thygesen, C. Untiedt, R. H. M. Smit, K. W. Jacobsen and J. M. van Ruitenbeek *Phys. Rev. B* **71**, 161402(R) (2005), D. Djukic and J. M. van Ruitenbeek, *Nano Lett.* **6**, 789 (2006).
- [12] N. Agraït, A. Levy Yeyati, and J. M. van Ruitenbeek, *Phys. Rep.* **377**, 81 (2003).
- [13] R. H. M. Smit, C. Untiedt, G. Rubio-Bollinger, R. C. Segers, and J. M. van Ruitenbeek, *Phys. Rev. Lett.* **91**, 076805 (2003).
- [14] E. L. Wolf, *Principles of electron tunneling spectroscopy* (Oxford university press, Oxford, 1989)
- [15] W. H. A. Thijssen, D. Djukic, A. F. Otte, R. H. Bremmer, and J. M. van Ruitenbeek, *Phys. Rev. Lett.* **97**, 226806 (2006).
- [16] B. Hamner, L. B. Hansen, and J. K. Nørskov, *Phys. Rev. B* **59**, 7413 (1999); S. R. Bahn and K. W. Jacobsen, *Comp. Sci. Eng.* **4**, 56 (2002); The Dacapo code can be downloaded at <http://www.fysik.dtu.dk/campos>.
- [17] D. Vanderbilt, *Phys. Rev. B* **41**, R7892 (1990).
- [18] J. P. Perdew et al., *Phys. Rev. B* **46**, 6671 (1992).
- [19] Y. Meir and N. S. Wingreen, *Phys. Rev. Lett.* **68**, 2512 (1992).
- [20] K. S. Thygesen and K. W. Jacobsen, *Chem. Phys.* **319**, 111 (2005).
- [21] K. S. Thygesen and K. W. Jacobsen, *Phys. Rev. B* **72**, 033401 (2005).
- [22] K. S. Thygesen and K. W. Jacobsen, *Phys. Rev. Lett.* **94**, 36807 (2005).
- [23] R. N. Barnett, H. Haekkinen, A. G. Scherbakov and U. Landman, *Nano Lett.* **4**, 1845 (2004).
- [24] S. Csonka, A. Halbritter and G. M. Ihaly, *Phys. Rev. B* **73**, 075405 (2006).