

Structural Properties of Two-Dimensional Polymers

Christian Munkel and Dieter W. Heermann

Institut für Theoretische Physik

Universität Heidelberg

Philosophenweg 19

6900 Heidelberg

and

Interdisziplinäres Zentrum

für wissenschaftliches Rechnen

der Universität Heidelberg

Germany

(May 12, 1993)

We present structural properties of two-dimensional polymers as far as they can be described by percolation theory. The percolation threshold, critical exponents and fractal dimensions of clusters are determined by computer simulation and compared to the results of percolation theory. We also describe the dependence of the typical cluster structures on the reaction rate.

I. INTRODUCTION

Polymers are known to develop various forms, for example linear chains, stars, rings, combs, ladders, three-dimensional networks and branched polymers. All these kinds of polymers have linear chains between the branching point. The kind of two-dimensional polymers we are studying are compact sheets of monomers, which are linked together periodically with respect to two dimensions. Between the branching points there is no chain and the polymers are highly organized sheets.

The successful "in bulk" synthesis of such two-dimensional polymers was reported recently [1,2]. Stupp et al. polymerized self-organized bilayers by two different so-called stitching reactions, which act within three distinct levels of the bilayer. Each oligomer can not have more than two bonds within a layer. In addition, not all possible bonds are present, because the stitching reactivity is about 30 to 50% at the upper and lower layer (90% within the middle layer). Is it possible to form a two-dimensional polymer instead of an ensemble of ladder polymers? What is the minimal reaction rate, needed for large two-dimensional polymers? What kind of structures will be developed at different reaction rates?

These are questions, which can be answered by percolation theory [3].

II. RESULTS FOR THE STITCHING REACTION

One of the most important results of percolation theory [4,6] is related to "universality", if the system has short ranged interactions. All presently available evidence strongly suggests, that the critical exponents depend on the dimensionality of the lattice only [5] but not on the lattice structure, boundary conditions and so on. The exponents for bond or site percolation, for square, triangular or honeycomb lattices etc. are the same. We therefore would expect, that the clusters produced with the above cited stitching reaction also may be described by these exponents.

Does there exist a large ("infinite") cluster of bonded sites? To answer this question, we define the fraction of sites in the largest cluster P_1 and the probability P_s , that there is a "spanning cluster" of bonds, which connects two opposite boundaries of the underlying lattice. Then for an infinite lattice, P_1 is expected to vanish for $(p - p_c) \rightarrow 0_+$ as

$$P_1(p) / (p - p_c)^\beta ; \quad (1)$$

where p is the probability, that a bond is present, and p_c is the percolation threshold, above which an infinite cluster exists. With n_s clusters of size s (number of polymers) the mean size of the infinite clusters is related to the percolation susceptibility (omitting the largest ("infinite") cluster)

$$\chi^s = \sum_{s=1}^{\infty} s^2 n_s(p) ; \quad (2)$$

which diverges at p_c as

$$(p - p_c)^{-\gamma} ; \quad (3)$$

Finally, at $p = p_c$ the number n_s of clusters with size s is expected to decay with a power of s :

$$n_s(p_c) / s^{-\tau} \quad (4)$$

Here β , γ and τ are the mentioned exponents.

Stupp et al. [1] suggest, that they synthesized large two-dimensional polymers. Obviously, the effective reaction rate of the stitching reaction has to be larger than the percolation threshold p_c , if one wants to synthesize large sheets instead of ladder polymers. Since p_c is not universal, we use a simple but sufficient model of the two-dimensional polymer, to compute p_c . In addition we will measure the exponents.

As a model of the two-dimensional polymer we used a stack of three layers, each triangular, hexagonally shaped with free boundaries, as shown in figure 1. At the middle layer, the reaction rate was 100%, i.e. all allowed bonds (two can react) were occupied. For that purpose, the bonds of the triangular lattice were chosen successively at random. If the number of bonds of each polymer was less than 2, the randomly chosen bond was occupied. Then we stitched the upper and lower layer using the same algorithm, until n_{+1} (n_{-1}) bonds were occupied. n_{+1} (n_{-1}) is the number of occupied bonds of the middle layer n_0 times the stitching probability (reaction rate) p of the upper and lower layer. Note, that n_0 is not determined by the linear lattice size L , but may vary slightly for each configuration.

Because of the restriction, that each polymer may be stitched to at most two neighbours, we do not expect an infinite cluster or percolation at $p = 0$, i.e. without bonds at the upper and lower layer, but an ensemble of linear polymer chains. On the contrary, at $p = 1$ all allowed bonds at all three layers are occupied, resulting in an effective coordination number larger than two. It is worth noting, that even at $p = 1$ the probability, that there is only one cluster containing all polymers, vanishes with increasing system size L . Within this model, it is very unlikely to prepare very large perfect two-dimensional polymers.

If we want to answer the question, if a reaction rate of about 40% is high enough to prepare infinite clusters, we have to determine the percolation threshold. As noted, the value of p_c is not universal, but depends strongly on the used lattice and bond restrictions. An unbiased way to estimate p_c is to plot the probability P_s of the occurrence of a spanning cluster as a function of p for different lattice sizes [5]. The infinite size scaling relation for P_s simply reads

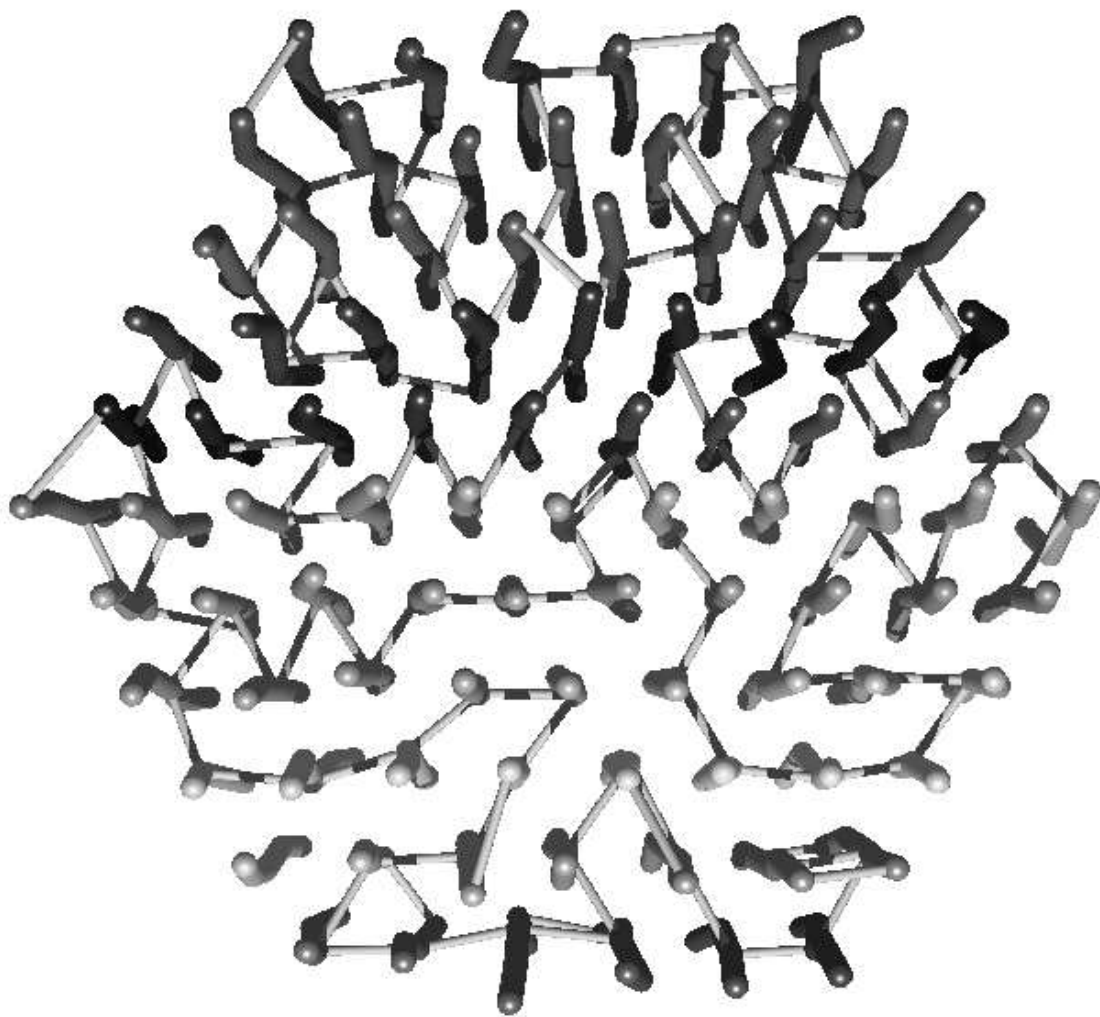


FIG. 1. Schematic representation of the two-dimensional polymer model of linear size $L = 11$ and $p = 0.4$.

$$P_s^{(L)}(p) = \tilde{P}_s \frac{L}{p} ; \quad (5)$$

where $\tilde{P}_s$ is the scaling function and p the correlation length. As a consequence, different curves $P_s^{(L)}(p)$ for different choices of L should intersect at $p = p_c$ in a common intersection point $\tilde{P}_s(0)$, apart from corrections to scaling and a bias by the choice of the critical exponents. Figure 2 shows this plot for the stitching reaction described above.

From this figure we get one of our main result, the percolation threshold $p_c = 0.110(3)$. Hence it follows, that the reaction rate of 30% to 50% reported by Stupp et al. [1] was high enough (within the limits of our percolation model) to prepare an "infinite" two-dimensional polymer.

Does the percolation of the stitching reaction lie in the same universality class as the standard bond percolation? Figure 3 shows a finite size scaling plot of P_1 using the assumed exact values for $\nu = 5/36$ and $\beta = 4/3$ and p_c obtained from the spanning probability. Within the accuracy of the data, the finite size scaling assumption seems to be fulfilled.

We may also compare the cluster size distribution to bond percolation. Using $\nu = 4/3$, we plotted the scaling function of the susceptibility in figure 4. Apart from small deviations of the smallest system far from p_c , the system sizes simulated seem to be in the scaling regime. The maximal values of χ vary by orders of magnitude in this range of L !

Finally, we are interested in the geometric properties of the cluster structure, particularly at the percolation threshold p_c . At p_c the largest (spanning) cluster should form a fractal with Hausdorff dimension d_H . This quantity can be defined with the number of polymers N within a sphere of radius R and the relation

$$N = \text{const.} \cdot R^{d_H} ; \quad (6)$$

Using the data of 1000 configurations of a $L = 1001$ hexagon at p_c , which is shown in figure 5, we measured $d_H(p_c) = 1.91(5)$ in good agreement with the result of percolation theory $91/48 = 1.896$.

Apart from the largest cluster, there are many smaller ones. Because of the statistical nature of their structure, we restrict ourselves to the number n_s of clusters of size s (which is the number of polymers), which is expected to decrease as a power of s . Within the accuracy of the data, the power law seems to be fulfilled in figure 6. Although the Fisher exponent $1.95(10)$ is somewhat smaller than the expected one $187/91$. Most probably this is due to the finiteness of the system. High quality data [7] showed, that n_s is less than the expected power law for small s and higher for the largest s . Therefore, we underestimated systematically.

- [1] S. Stupp, S. Son, H. Lin, and L. Li, *Science* 259, 59 (1993).
- [2] E. L. Thomas, *Science* 259, 43 (1993).
- [3] P. J. Flory, *J. Am. Chem. Soc.* 63, 3091 (1941).
- [4] D. Stauffer and A. Aharony, *Introduction to Percolation Theory*, 2nd ed. (Taylor and Francis, 1992).
- [5] K. Binder and D. W. Heermann, *Monte Carlo Simulation in Statistical Physics*, 2nd ed. (Springer-Verlag Heidelberg, 1992).
- [6] D. W. Heermann, *Computer Simulation Methods in Theoretical Physics*, 2nd ed. (Springer Verlag, Heidelberg, 1990).
- [7] D. C. Rapaport, *J. Stat. Phys.* 66, 1/2, (1992).

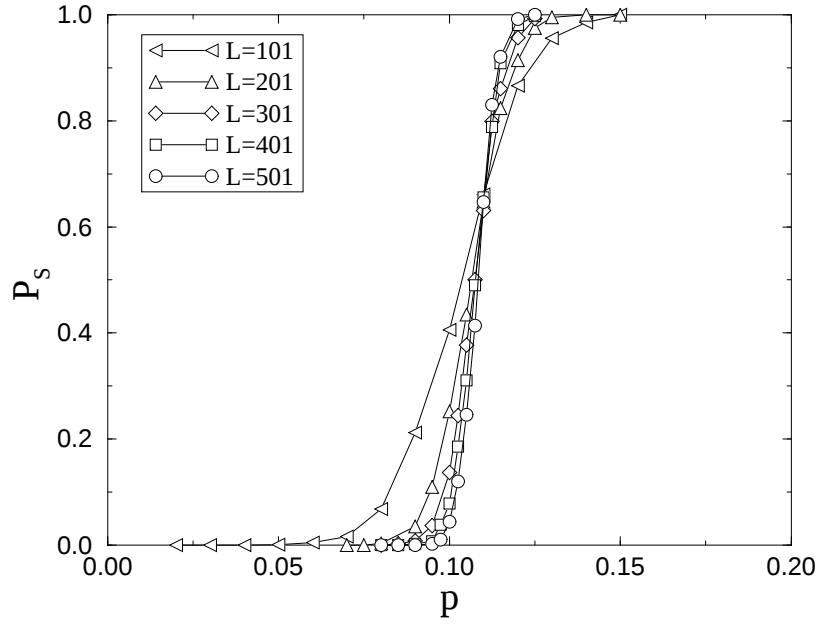


FIG . 2. Unbiased estimate of the percolation threshold $p_c = 0.110(3)$ using the spanning probability P_s .

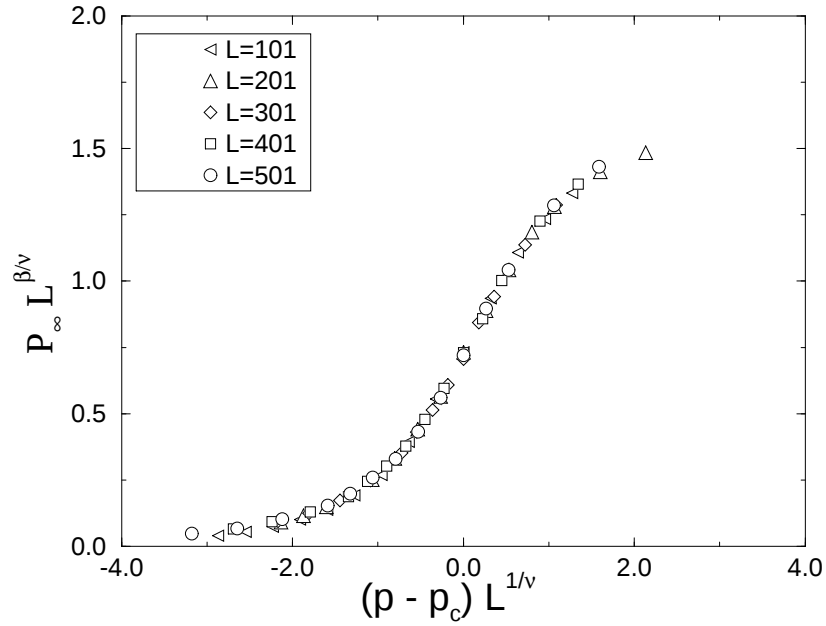


FIG . 3. Finite size scaling of the probability $P_1^{(L)}$, which was defined as the fraction of polymers in the largest cluster, with exponents $\beta = 4/3$, $\nu = 5/36$ and $p_c = 0.110(3)$.

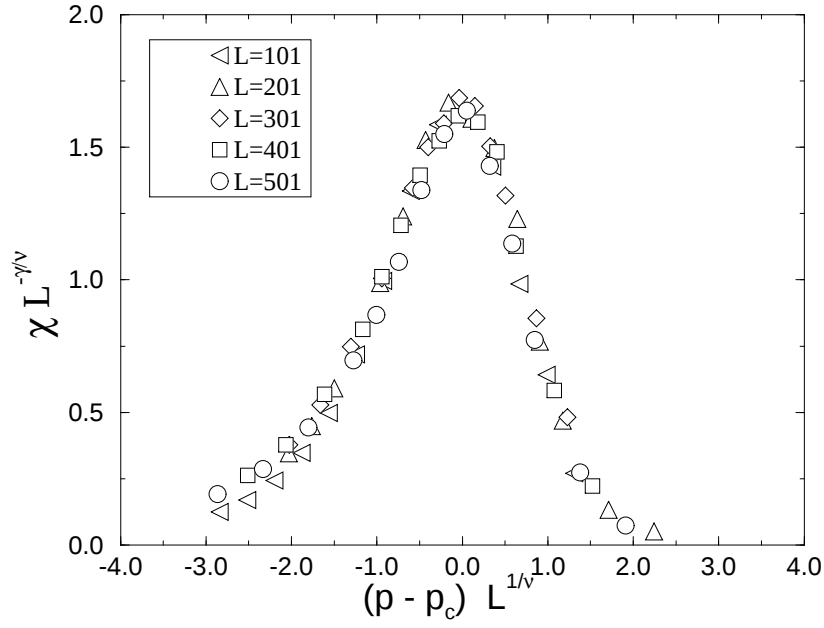


FIG. 4. Finite size scaling of the susceptibility $\chi^{(L)}$ with exponents $\gamma = 4/3$, $\nu = 43/18$ and $p_c = 0.110(3)$.

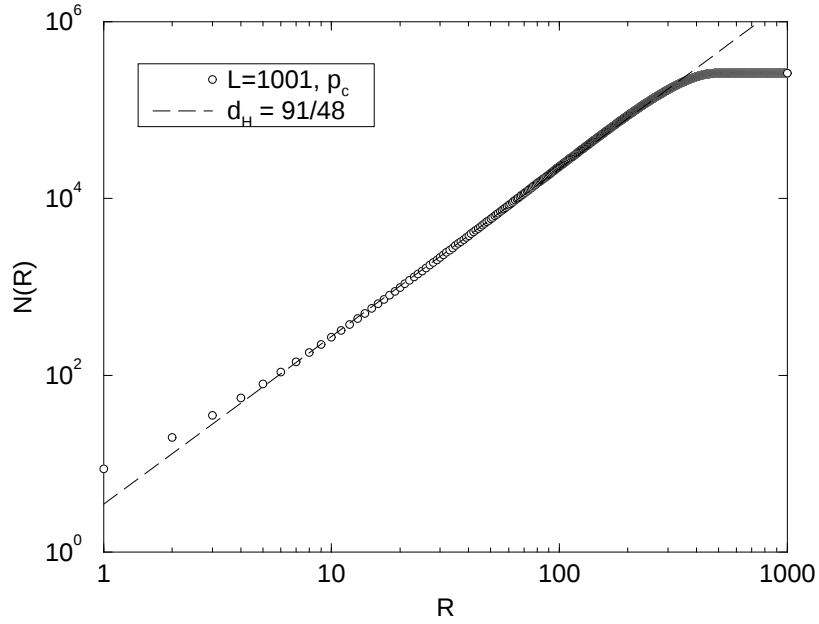


FIG. 5. Number of polymers N within a radius R of the largest cluster. The data of 1000 configurations of $L = 1001$ hexagons were accumulated. The dashed line has the exact Hausdorff dimension (slope) $d_H = 91/48$.

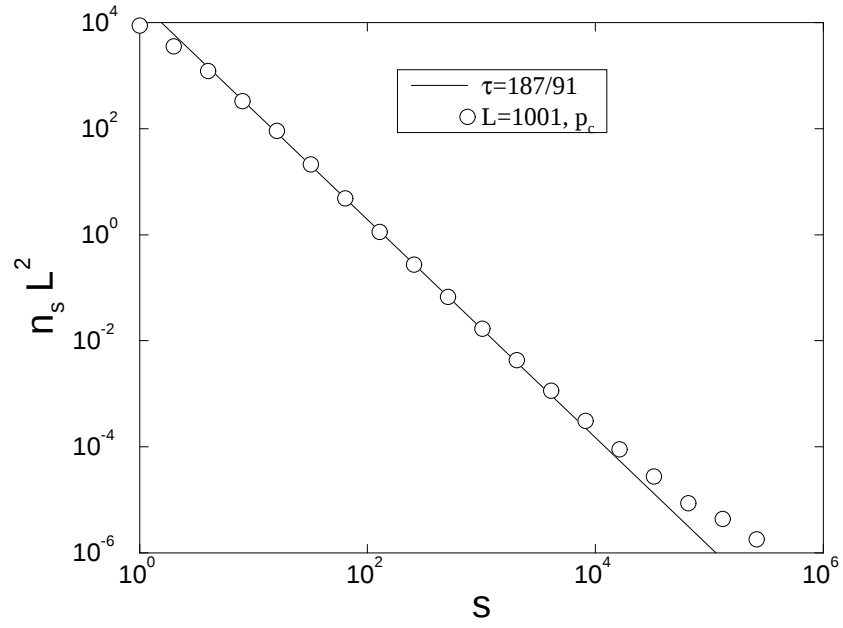


FIG. 6. Cluster distribution of 1000 configurations of $L = 1001$ hexagon (751501 polymers) at the percolation threshold $p_c = 0.110$. From the slope one computes the Fisher exponents $\tau = 1.95(10)$.