

## N E T W O R K S O F S T E P S O N A U A N D P T C R Y S T A L S

H e n k v a n B e i j e r e n

Institute for Theoretical Physics  
 Universiteit Utrecht  
 3508-TA Utrecht, The Netherlands

E n r i c o C a r l o n

Institute for Theoretical Physics  
 Katholieke Universiteit Leuven  
 B-3001 Leuven, Belgium

## A b s t r a c t

Networks of steps, seen in STM observations of vicinal surfaces on Au and Pt (110), are analyzed. A simple model is introduced for the calculation of the free energy of the networks as function of the slope parameters, valid at low step densities. It predicts that the networks are unstable, or at least metastable, against faceting and gives an equilibrium crystal shape with sharp edges either between the (110) facet and rounded regions or between two rounded regions. Experimental observations of the equilibrium shapes of Au or Pt crystals at sufficiently low temperatures, i.e. below the deconstruction temperature of the (110) facet, could check the validity of these predictions.

## I N T R O D U C T I O N

(110) surfaces of fcc metals have been intensively studied in the past years by means of several experimental techniques. It was found by scattering experiments, and subsequently confirmed by direct STM observations that some "heavy" metals such as Au, Pt, Ir form a (2 × 1) reconstructed state. Other metals, e.g. Pb and Al, are not reconstructed.

The (2 × 1) structure is also known as missing-row reconstruction because one out of two rows of atoms, aligned along the [110] direction, is missing from the surface layer. We stress also that there are two different realizations of these reconstructed states, in which either the even or the odd rows are missing.

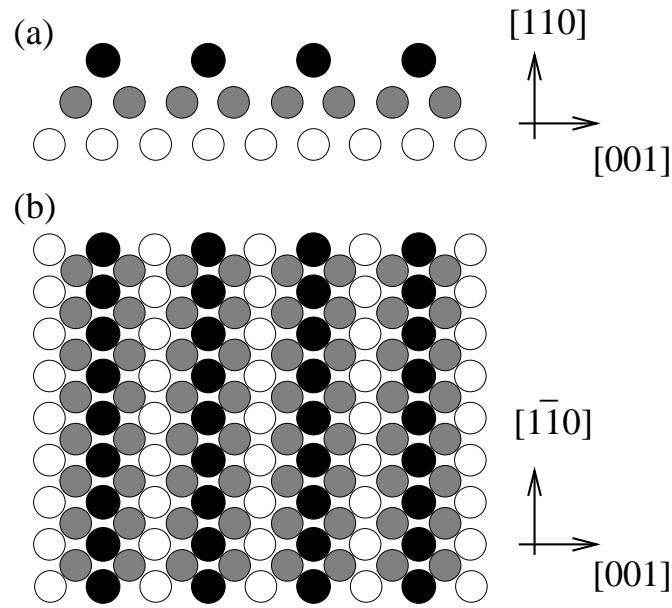


Figure 1: (a) Profile and (b) top view of a missing row reconstructed (110) surface.

Figure 1 shows a top and a side view of the missing row reconstructed structure. Along the  $[001]$  direction the surface assumes a hill-and-valley profile, where the sides of the hills are actually  $(111)$  microfacets. In the  $(111)$  orientation, surface atoms are closely packed, therefore such orientations are energetically favored.

In several STM investigations (Gritsch et al. 1991; Gmzewski et al. 1992; Kuipers, 1994) of vicinal orientations of  $(110)$  Au and Pt surfaces an unusual pattern of steps, as shown in Fig. 2, was observed. The figure represents a surface orientation slightly tilted towards the  $[110]$  direction with respect to the  $(110)$  facet. The missing rows, which are not visible in the figure, run along the vertical direction.

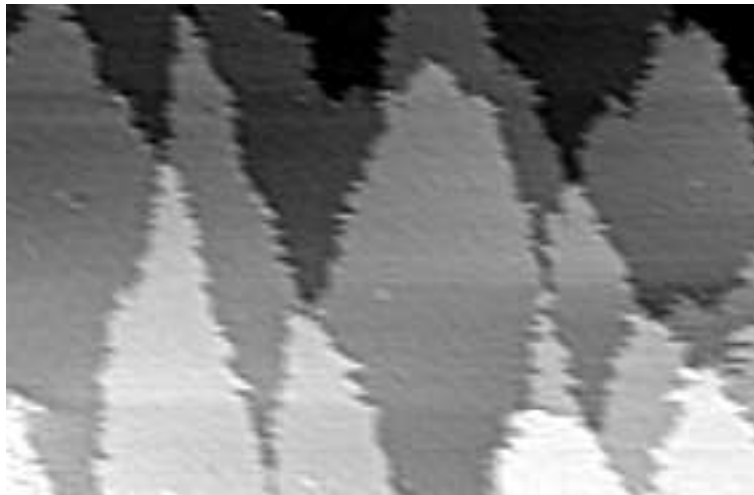


Figure 2: STM images of vicinals of Au (110) (courtesy of M. S. Hoogenan, L. Kuipers and J. W. M. Frenken, AMOLF Amsterdam). The area shown is of  $190\text{nm} \times 120\text{nm}$  at  $T = 550\text{K}$ , with a miscut angle of  $0.07$  degrees.

This pattern of steps is unusual indeed. In normal situations a miscut along the  $[110]$  direction is generated by steps that run perpendicular to the missing rows, i.e. along the horizontal direction of Fig. 2, because such an arrangement minimizes the total length and hence the total free energy of the steps required to produce the miscut. Instead, on missing-row reconstructed surfaces the steps zig-zag and repeatedly touch each other at a collection of contact points; one can also say that they form a network of

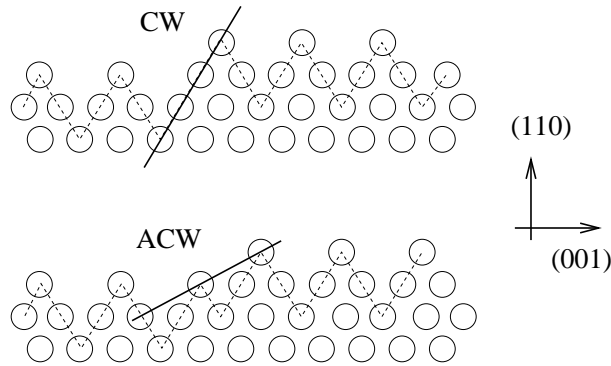


Figure 3: Examples of clockwise (CW) and anticlockwise (ACW) steps.

two arrays of roughly parallel steps crossing each other and forming on average angles  $\theta$  and  $\phi$ , with the vertical direction in Fig. 2. An explanation for the formation of this network has been given already in (Kuipers, 1994). In this article we give a more quantitative description based on a simple, yet, we think, quite realistic model, which describes surface orientations close to the (110) facet. On the basis of this model we discuss the thermodynamical properties of the networks (Carlon and Van Beijeren, 1996). We find that the network is actually unstable or at least metastable: in equilibrium it decays into a combination of stable surface orientations, with the appearance of sharp edges in between. As a consequence the edge of the (110) facet shows cusps, i.e. jumps in the direction of its tangent.

## THE MODEL

In a missing-row reconstructed (110) facet one can distinguish two different types of steps parallel to the missing rows, commonly known as clockwise and anticlockwise steps and illustrated in Fig. 3. In STM observations anticlockwise steps are rarely seen especially at low temperatures, and when present they are mostly pinned by impurities. This indicates that clockwise steps have markedly lower free energies per unit of length than the anticlockwise ones; this energy difference can in principle be derived from STM observations, by estimating the relative frequencies at which step segments of given length of either type of step do occur.

On the basis of STM observations on Au(110) surfaces it has been concluded (Kuipers, 1994) that at room temperature and for sufficiently clean samples, anticlockwise steps should be absent from the surface.

Due to the presence of reconstruction not all possible configurations of clockwise steps will actually occur on the surface. As illustrated in Fig. 4 (a) a clockwise step going up followed by another clockwise step going down induces a shift in the reconstruction of the lower terrace. For this reason, a closed clockwise step cannot be formed on a given terrace unless it is accompanied by domain boundaries separating regions of different reconstruction order (Fig. 4 (b)).

This fact may have some important consequences, for instance, on how the (110) facet roughens. In the present work however we will focus on the behavior of the system far from the deconstruction or roughening critical points.

The interplay between step orientation and surface reconstruction is essential for understanding the formation of the network of steps. Indeed, a step perpendicular to the missing rows cannot zig-zag forming clockwise segments parallel to the missing rows, if expensive domain boundaries between opposite reconstruction states are to be

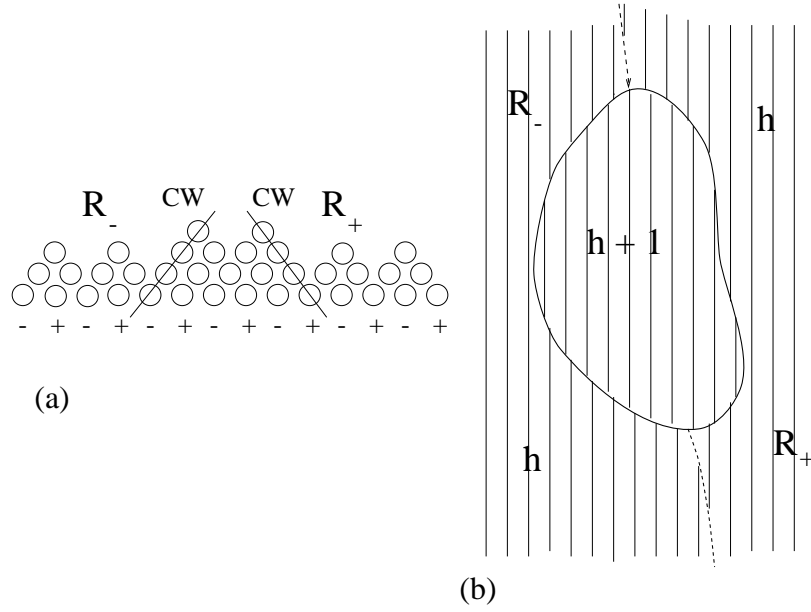


Figure 4: (a) A clockwise step up followed by a clockwise step down generate a shift in the reconstruction order;  $R_-$  and  $R_+$  indicate the two possible reconstructed phases. (b) As a consequence of this a closed clockwise step must be accompanied by domain boundaries between the two phases  $R_-$  and  $R_+$ .

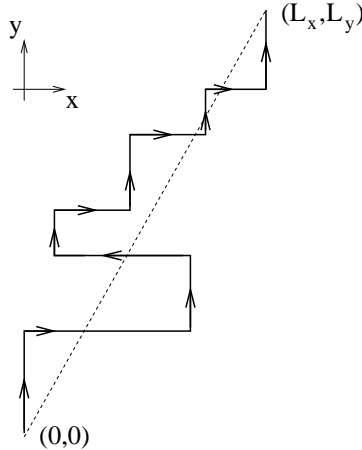


Figure 5: Example of microscopic configuration of a step; if anticlockwise steps are to be avoided only segments along the  $+y$  and  $+x$  directions are allowed.

avoided.

The single step free energy

To clarify and quantify the previous discussion we calculate the free energy of an isolated step as function of the step orientation. For convenience we consider, for the energy of an anticlockwise step segment, the limit  $E_{ACW} \rightarrow 1$ : only clockwise step segments are allowed and they have energies per unit lengths  $\gamma_y$  and  $\gamma_x$  where  $y$  and  $x$  are the directions parallel respectively perpendicular to the missing rows. One could eventually introduce more parameters, such as a corner energy, but this is not essential.

Let us consider the step as an oriented walk from a lattice point  $(0;0)$  to  $(L_x; L_y)$ , as shown in Fig. 5. As seen above, if anticlockwise steps are to be avoided, only step segments in the  $+x$ -directions and the  $+y$ -direction are allowed. A simple calculation (for more details see Appendix I) gives the following free energy of a step per unit of length, tilted over an angle  $\theta$  with respect to the missing rows:

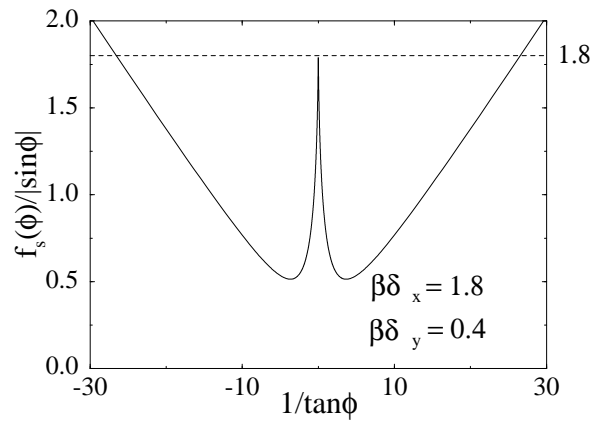


Figure 6: The step free energy per unit of projected length along the x-direction as function of  $1/\tan \phi$ . Steps with orientations close to  $\phi = \pi/2$  are unstable as can be seen from the cusp in the figure.

$$f_s(\phi) = \frac{\ln z(\phi)}{2} - j \sin \phi + j + \frac{p}{2} \ln \frac{2 \cosh(2\beta\delta_x) (z(\phi) + 1/z(\phi))}{2 \sinh(2\beta\delta_x)} \cos \phi \quad (1)$$

where  $\beta = 1/(k_B T)$  and:

$$z(\phi) = \frac{\cosh(2\beta\delta_x) t(\phi) + \frac{q}{1 + \sinh^2(2\beta\delta_x) t^2(\phi)}}{1 + t(\phi)} \quad (2)$$

with  $t(\phi) = j \tan \phi - \frac{p}{2}$ . Notice that the limiting value for the free energy of a step running perpendicular to the missing rows is simply  $f_s(\phi = \pi/2) = \beta\delta_x$ : such steps are perfectly straight and their free energy is "frozen", i.e. temperature independent. In the limit  $\beta \rightarrow 0$ , where steps are parallel to the missing rows, the step free energy is:

$$f_s(0) = -j + \frac{p}{2} \ln(\tanh(\beta\delta_x)) \quad (3)$$

where the first term on the r.h.s. is the energy of the ground state configuration, while the second term is negative and represents the contribution of thermal excursions along the x-direction.

For investigating the stability of steps of various orientations it is convenient to calculate  $f_s(\phi) - j \sin \phi$ , the step free energy per unit of projected length along the x-direction (Van Beijeren and Nolden, 1987). This quantity is shown in Fig. 6: it has a local maximum with a cusp at  $\phi = \pi/2$ . For steps slightly inclined with respect to this orientation it decreases, since such steps have a larger entropy. This can be seen expanding  $f_s(\phi) - j \sin \phi$  around  $\phi = \pi/2$ ; such an expansion yields:

$$\frac{f_s(\phi) - j \sin \phi}{j} = f_s(\pi/2) + A j + B j \log j + \dots \quad (4)$$

with A and B some non-negative constants. The second term on the r.h.s. is due to the energy of segments of steps parallel to the y-direction, while the third term is the decrease in free energy due to entropy. The entropic term dominates at sufficiently small  $j$ , except at  $T = 0$ , where  $B = 0$ .

Obviously  $f_s(\phi) - j \sin \phi$  diverges for  $\phi \rightarrow 0$ . It is minimal for an angle  $\phi_0$  satisfy-

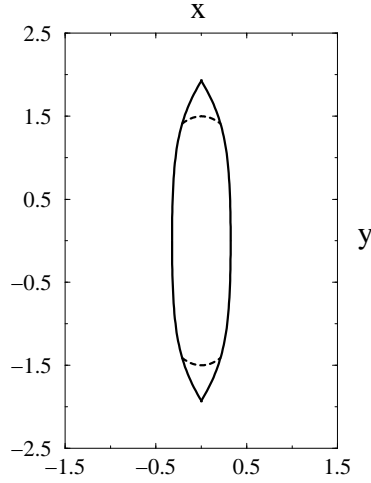


Figure 7: Equilibrium shape of the (110) facet obtained from the Wul construction, for the same values of  $x$  and  $y$  as shown in Fig. 6. Notice the cusps, due to instabilities of steps perpendicular to the missing rows.

ing<sup>1</sup>:

$$t(\theta_0) = \frac{r \frac{\cosh(2x) - e^{y^2/2} \sinh(2x)^2}{e^{y^2/2} \sinh(2x)}}{1} : \quad (5)$$

This simple calculation shows that, on a surface tilted along the [110] direction, steps making a finite angle  $\theta_0 \neq \pi/2$  with respect to the missing rows are entropically favored.  $\theta_0$  is the optimal value of the angle of the network. Its value, given by Eq. (5), could in principle be used to determine the parameters  $x$  and  $y$  from measured values of  $\theta_0$  at different temperatures. In fact the temperature dependence of  $\theta_0$  has been studied in some STM observations of networks on Au(110) surfaces by Hoogenan and Frenken (Hoogenan and Frenken, private communication). They found a characteristic angle that is rather temperature independent and pointed out this may be due to the presence of impurities which act as pinning sites for the network. We think that this point is quite interesting and deserves further experimental investigations.

The equilibrium shape of the (100) facet

The equilibrium shape of the (110) facet can be found by applying a one-dimensional Wul construction to the step free energy as function of orientation (Van Beijeren and Nolden, 1987). The result of this construction, for a representative choice of step energies and temperature, is shown in Fig. 7. Steps with orientations close to  $\theta = \pi/2$  are unstable and would phase separate in combinations of two steps of orientations  $\theta_0$  and  $\theta_0$ : the shape of the (110) facet resembles that of an almond, with cusps along the [110] direction.

This type of shape is unusual, because the cusps correspond to first order phase transitions in a one-dimensional system at finite temperatures. In normal situations this could not occur (Van Beijeren and Nolden, 1987): if steps of orientations  $\theta_0$  and  $\theta_0$  both have free energy, say  $f_0$ , steps of intermediate orientations could always be

<sup>1</sup>The quantity under the square root in (5) becomes negative at small values of  $x$  and  $y$ ; this happens at temperatures above the roughening temperature of the (110) surface when the solid-on-solid approximation for the step free energy  $f_s(\theta)$  is not positive definite and the simple theory considered here breaks down.

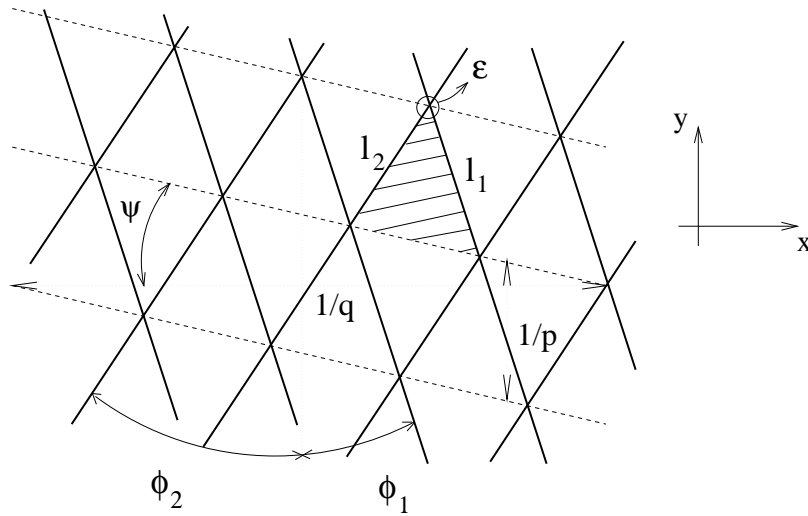


Figure 8: Schematic view of the network of crossing steps.

built out of an alternating sequence of segments of orientations  $\phi_0$  and  $\phi_1$ . Then at any non-zero temperature the lowering of free energy through entropy gain outweighs the increase through the excess energy at the corners between the successive segments, provided the density of these corners is sufficiently low. This is a variant of the usual argument against phase transitions in one-dimensional systems at finite temperatures. In the present case this argument does not work since, due to topological constraints induced by the reconstruction, a configuration of short "zigzagging" step segments of orientations  $\phi_0$  and  $\phi_1$  joined together cannot be formed, as pointed out above.

The surface free energy

Next we calculate the surface free energy as function of the slope parameters  $p$  and  $q$ , which denote the tangents of the tilting angles of the surface with the  $[110]$  and the  $[001]$  directions. Both parameters  $q$  and  $p$  will be considered small, so we restrict ourselves to vicinal surface orientations.

Interactions between steps are introduced in a simple way: a free energy  $\tilde{f}$  is associated to each pair of crossing steps.  $\tilde{f}$  keeps account of both short and long range interactions between the steps and it is defined as the excess free energy associated to the intersection point of two crossing steps forming angles  $\phi_1$  and  $\phi_2$  with the  $y$ -direction on a  $(110)$  facet:

$$\tilde{f}(\phi_1; \phi_2) = F(\phi_1; \phi_2) - A f_0 - s_1 f_s(\phi_1) - s_2 f_s(\phi_2) \quad (6)$$

Here  $F(\phi_1; \phi_2)$  is the free energy of the surface of area  $A$  with two crossing steps of lengths  $s_1$  and  $s_2$ ,  $f_0$  is the free energy of the  $(110)$  facet per unit of area (no steps are present), and  $f_s(\phi)$  the free energy of a single step, whose properties have been discussed above.

One could try to estimate  $\tilde{f}$  from a microscopic point of view taking into account long range interactions of elastic or entropic type and short range interactions near the crossing point. This estimate is non-trivial and for the general features of the equilibrium crystal shape that we want to address here, only the sign of  $\tilde{f}$  matters. In

general, it is expected (Bemasconi and Tosatti, 1993) that elastic interactions between two antiparallel steps (as are the crossing steps of the network, provided  $\theta_0$  is not too large) yield a negative contribution to  $\sim$ . Entropic interactions (Gruher and Mullins, 1967; Jayaprakash et al., 1984), which become relevant at higher temperatures, are repulsive and give a positive contribution to  $\sim$ . Finally at the crossing point one would expect a positive contribution to  $\sim$ . In the rest of the article we discuss both possibilities for the sign of  $\sim$ , which yield two different scenarios for the equilibrium shape of the crystal.

Let us consider a miscut along the [110] direction, generated by a pattern of crossing steps forming angles  $\theta_1$  and  $\theta_2$  with the y-axis, as shown in Fig. 8. The dashed inclined lines indicate hypothetical parallel isolated steps that would generate the same macroscopic orientation as the network;  $1/q$  and  $1/p$  are the average distances between these steps along the x and the y direction.

The free energy per unit of projected area can be written as:

$$f(p; q; \theta_1; \theta_2) = f_0 + \frac{1}{2A} [l_1 f_s(\theta_1) + l_2 f_s(\theta_2) + \sim(\theta_1; \theta_2)] \quad (7)$$

where  $f_0$  is the free energy per unit area of the (110) facet, while  $l_1$  and  $l_2$  are the lengths of the two sides of the dashed triangle, of area  $A$ , shown in Fig. 8.

The actual free energy can be found by minimizing the free energy (7) with respect to the angles  $\theta_1$  and  $\theta_2$ ; to lowest orders in  $p$  and  $q$  and for  $\theta_0 < \pi/2$ , this amounts to minimizing  $f_s(\theta) = \gamma \sin \theta$ . Therefore the minimum of (7) is at  $\theta_1 = \theta_2 = \theta_0 + O(p; q)$ , where  $\theta_0$  is the angle given by (5). Substituting this back into (7), expressing  $A$ ,  $l_1$ ,  $l_2$  as function of  $p$ ,  $q$ ,  $\theta_1$ ,  $\theta_2$  and expanding to lowest orders in  $p$  and  $q$  we find:

$$f(p; q) = f_0 + \frac{f_s(\theta_0)}{\sin \theta_0} p + \frac{\sim}{2} \frac{p^2}{\tan \theta_0} \tan \theta_0 q^2 \quad (8)$$

where  $\sim$  is the interaction free energy (6) calculated at angles  $\theta_1 = \theta_2 = \theta_0$ . As in usual expansions of surface free energies around facets (see e.g. Van Beijeren and Nolden, 1987) the term linear in  $p$  represents the contribution of non-interacting steps. The interaction terms are quadratic in the step densities, differently from usual step-step interactions which lead to terms cubic in the step densities (Gruher and Mullins, 1967). The origin of the quadratic term can be understood easily: the number of step crossings per unit area is simply proportional to the product of the densities,  $p q \tan \theta_0$ , of the two types of steps. In addition there are long range interactions between the parallel steps in the network, but they will only contribute to terms of cubic or higher order in the step density expansion of the free energy (Gruher and Mullins, 1967).

For  $\theta_0 > \pi/2$  the expression (7) is minimized by a single array of steps (so  $\theta_1 = \theta_0$  and  $\theta_2 = 0$ ) and the free energy takes the usual form (Gruher and Mullins, 1967):

$$f(p; q) = f_0 + f_s(\theta_0) \frac{q}{p^2 + q^2} + O((p^2 + q^2)^{\frac{3}{2}}) \quad (9)$$

Notice that the expression (8) for the free energy of the step network, irrespectively of the sign of  $\sim$ , is a non-convex function of  $p$  and  $q$ . This result implies that the network is always unstable: some surface orientations disappear from the equilibrium shape of the crystal and are replaced by sharp edges.

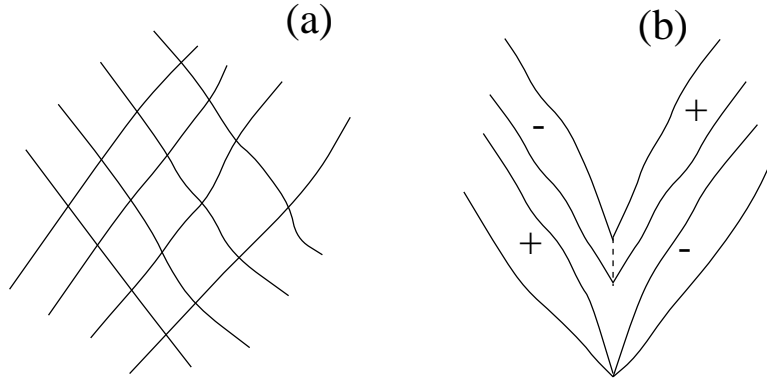


Figure 9: (a) The network of crossing steps, and (b) a combination of two step arrays of different orientation, after the phase separation, predicted by (5) for  $\tilde{\gamma} > 0$ , has occurred. The + and - indicate the opposite reconstruction phases induced by the clockwise steps.

As is well known (see, for instance, Van Beijeren and Nolden, 1987), the equilibrium crystal shape is the shape that minimizes the total surface free energy at a given fixed volume. From the minimization of the free energy calculated above we can construct the equilibrium shape of the crystal around the (110) facet. This shape depends crucially on the sign of the interaction free energy  $\tilde{\gamma}$ , therefore in the rest of the paper we will distinguish two different cases.

$\tilde{\gamma} > 0$

When  $\tilde{\gamma}$  is positive the system can decrease the surface free energy reducing the density of crossings. By applying the Maxwell construction to Eqs. (8, 9) one finds that a given surface orientation  $(p; 0)$  separates into two orientations of slopes  $(p; p \tan \theta_0)$  and  $(p; -p \tan \theta_0)$  joining at a ridge, as depicted in Fig. 9 (b). In this combination of two surface orientations all the crossing points have been "eliminated" with a net gain of free energy. To generate the interface between the two surface orientations one has to pay a positive amount of boundary free energy, but this free energy will be proportional to the length of the boundary and therefore negligible in the thermodynamic limit, when compared to terms proportional to the surface area.

The structure of the domain boundary is quite interesting as well. Two clockwise steps running under angles  $\theta = 2 + \theta_0$  and  $\theta = 2 - \theta_0$  cannot be simply joined together, because this will cause a mismatch in the reconstruction order. Such joints must be accompanied by a domain boundary.

As we saw already in the previous Section the model predicts that the network is unstable, suggesting that the pattern of steps observed in STM experiments should decay, after a sufficiently long time, into the combination of surface orientations depicted in Fig. 9 (b). In the present case this time may be extremely long. In fact once the network has been formed, the process of disentangling it into stable orientations as the ones shown in Fig. 9 (b), may require the investment of a large amount of free energy to go through very unfavorable states and it may be difficult to observe it experimentally without a careful long annealing of the surface.

Thermodynamically the metastability encountered here is highly unusual. In e.g. a homogeneous gas-liquid system a free energy that is a concave function of density always leads to instability due to spinodal decomposition. In our system this is impeded by topological constraints on the steps, requiring concerted mass transportation over relatively large distances for the decomposition of a network into stable surfaces. Therefore even a non-convex free energy can be metastable. For describing the surface

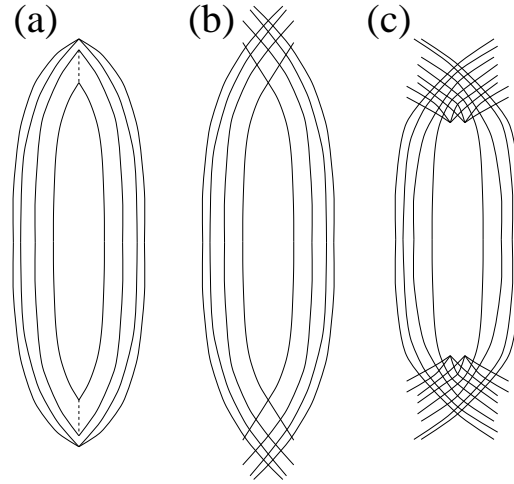


Figure 10: Arrangement of the steps surrounding the (110) facet for  $\tilde{\gamma} > 0$  in the stable phase (a), in the metastable phase (b) and for  $\tilde{\gamma} < 0$  (c).

free energy one can use Eq. (8) again. A typical arrangement of steps around the (110) facet in this situation is shown in Fig. 10 (b). In this case the shape profile along the  $y$ -axis of the crystal for vicinal orientations is expected to be of the type  $z(y) \sim (y - y_0)^2$ , due to the term proportional to  $p^2$  in the surface free energy. A free energy expansion with a term cubic in the step density would produce a shape profile with an exponent  $3/2$ , the so-called Pokrovsky-Talapov exponent (see, for instance, Van Beijeren and Nolden, 1987).

$$\tilde{\gamma} < 0$$

When a negative free energy is associated to a crossing point the network of steps tends to condense to maximize the density of crossings. On the other side, entropic repulsions (Gruher and Mullins, 1967) favor configurations where steps are far apart and tend to stabilize the network.

The competitions between repulsions and attractions may give rise to the two following scenarios: 1) if attractions dominate for the whole range of surface orientations the network fully condenses and the stable orientations along the  $p$  direction are the (110) and (100) facets, which would be directly connected under a sharp edge; 2) if repulsions, possibly of entropic type become dominant, then the surface free energy turns concave at higher step densities and the (110) facet is connected under an angle with the rounded regions.

As pointed out above, the surface free energy  $f(p; q)$  contains terms which are of cubic or higher order in the step density. A term cubic in  $p$  with a positive coefficient could well stabilize the free energy at not too small values of  $p$ . In both scenarios the (110) facet has sharp edges running roughly perpendicular to the missing-row direction.

A simple model with a negative crossing energy (Carlon et al., 1996; Carlon, 1996) the staggered body-centered-solid-on-solid model (BCSOS model), is discussed in some details in Appendix II. The model reproduces both scenarios 1) and 2), depending upon temperature.

Finally in Fig. 7 the dashed lines show the truncation of the equilibrium shape of the (110) facet by ridges connecting the facet to rounded areas and Fig. 10 (c) shows the expected arrangement of steps around the truncated facet. Notice that in this case there are sharp ridges between rounded regions covered by networks of steps and regions covered by non-crossing step arrays.

## CONCLUSION

In the present article we introduced a simple model which describes networks of crossing steps, that have been observed in STM experiments on Au(110) and Pt(110) surfaces. The model shows that these networks are unstable (or at least metastable) with respect to faceting.

From the calculation of the surface free energy for orientations close to the (110) facet the equilibrium shape for this facet has been derived. For repulsive interactions between two crossing steps ( $\gamma > 0$ ) the facet shape is rather unusual: it is cusped and elongated along the [110] direction. The cusps are connected to ridges separating rounded regions. If the interaction is attractive ( $\gamma < 0$ ) the (110) facet is still elongated with sharp edges roughly perpendicular to the missing-row direction. In this case there are much weaker cusps, between these edges and the smooth facet boundaries roughly parallel to the missing-row direction.

The predicted shapes could be observed in experiments on equilibrium shapes of crystals with (110) missing-row reconstructed facets.

Heyraud and Metois (1980) studied shapes of small gold crystals in thermalequilibrium with their vapor; in their samples only the (111) and (100) facets were observed, since the range of temperatures investigated ( $T \approx 1000^\circ\text{C}$ ) is above the roughening temperature of the (110) facet. To observe some of the shapes described in this article, temperatures below the roughening and the deconstruction temperatures of the (110) facet should be considered.

We believe that the problems connected to the metastability/instability of the networks of steps deserve further experimental investigation, as well. If  $\gamma$  is positive, as we think should be the case for gold and platinum crystals, one should be able, starting from the metastable network of steps, to observe a nucleation of arrays of parallel steps connected under a ridge. Probably this could be observed in practice, e.g. in STM experiments, only for sufficiently high temperatures and in very pure samples.

Acknowledgements:

We had several stimulating discussions with Joost Frenken, Laurens Kuipers and Misha Hoogenan, who drew our attention to the networks of steps discussed here in the first place. E.C. acknowledges financial support from grant No. CHBGCT 940734 from the European Capital and Mobility Programme.

## APPENDIX I: CALCULATION OF THE STEP FREE ENERGY

For the calculation of the step free energy we consider first the partition functions  $G_x$  and  $G_y$  of straight segments of steps along the x and y direction. The segments have energies per unit length equal to  $\epsilon_x$  and  $\epsilon_y$ . In Fourier space one has:

$$G_x(k_x) = \sum_{n=1}^{\infty} e^{2n\pi x} e^{ink_x} + e^{ink_x} = \frac{1}{e^{2\pi x + ik_x} - 1} + \frac{1}{e^{ik_x} - 1} \quad (10)$$

$$G_y(k_y) = \sum_{n=1}^{\infty} e^{n\pi y} e^{ink_y} = \frac{1}{e^{\pi y + ik_y} - 1} \quad (11)$$

Notice that segments of steps along the negative y direction are not allowed. We recall that the factors  $\pi/2$  and  $2\pi$  are the minimal length of step segments along the x and y directions. The step is generated by all possible combinations of horizontal and vertical

segments:

$$G(\mathbf{k}) = G_x + G_y + G_x G_y + G_y G_x + \dots = \frac{G_x + G_y + 2G_x G_y}{1 - G_x G_y} \quad (12)$$

The partition function of a step of lengths  $L_x$  and  $L_y$  is obtained by Fourier transform :

$$Z(L; \beta) = \int \frac{d\mathbf{k}}{4\pi^2} e^{i(k_y \frac{p}{2} L_y + k_x L_x = 2)} G(\mathbf{k}) \quad (13)$$

with  $L = \sqrt{L_x^2 + L_y^2}$  and  $\theta = \arctan(L_x/L_y)$ . The integral over  $k_y$  can be rewritten as a contour integral in the variable  $z = e^{ik_y}$ ; the integrand has a simple pole in:

$$z = e^{i \frac{p}{2} L_y} (1 + G_x(k_x)) \quad (14)$$

The partition function now becomes:

$$Z(L; \beta) = \int \frac{dk_x}{2} e^{L f(k_x; \beta)} \dots \quad (15)$$

with:

$$f(k_x; \beta) = \frac{ik_x}{2} \sin \theta + \frac{p}{2} L_y \log(1 + G_x(k_x)) \cos \theta \quad (16)$$

The dots in (15) denote terms which are not relevant in the thermodynamic limit  $L \rightarrow \infty$ . Using the saddle point approximation, one can evaluate (15) as:

$$Z(L; \beta) = e^{L f_s(\beta)} \quad (17)$$

where the step free energy is  $f_s(\beta) = f(ik; \beta)$  and  $ik$  the stationary point of  $f(k_x; \beta)$ . Working this out one obtains Eq. 1.

## APPENDIX II: THE STAGGERED BCSOS MODEL

Without going into details we present here some relevant results concerning the staggered BCSOS model, which, for certain values of the energy parameters describes networks of crossing steps with a negative crossing energy (for more details the reader may consult (Carlon et al., 1996; Carlon and Van Beijeren, 1996 II)).

The model is applicable to surfaces of ionic crystals of bcc type, as for instance CsCl, and describes all surface orientations (ts1) with  $j_1 + j_2 = 1$ . It does not have the characteristic feature, responsible for the formation of networks in the present paper, that an up step followed by a down step changes a reconstruction order; instead the networks are induced by a large corner free energy, leading to steps with long segments in the principal lattice directions, combined with a negative value of  $\sim$ , which favors crossings of steps. However, the model does illustrate the two different scenarios for step condensation discussed above for  $\sim < 0$ .

At  $T = 0$  the crystal has the shape of a truncated pyramid, with a top (100) facet and four side facets of (110) type, as shown in Fig. 11 (a). A step on the (100) facet has an energy per unit of length  $e > 0$  and a kink energy  $e_k = e$ : steps consist, especially at low temperatures, of elongated straight segments with few kinks. These segments are oriented parallel to the two axes  $\mathbf{e}_1$  and  $\mathbf{e}_2$  shown in Fig. 11 (b): differently from (110) surfaces of fcc metals these two directions are equivalent. Steps can cross each

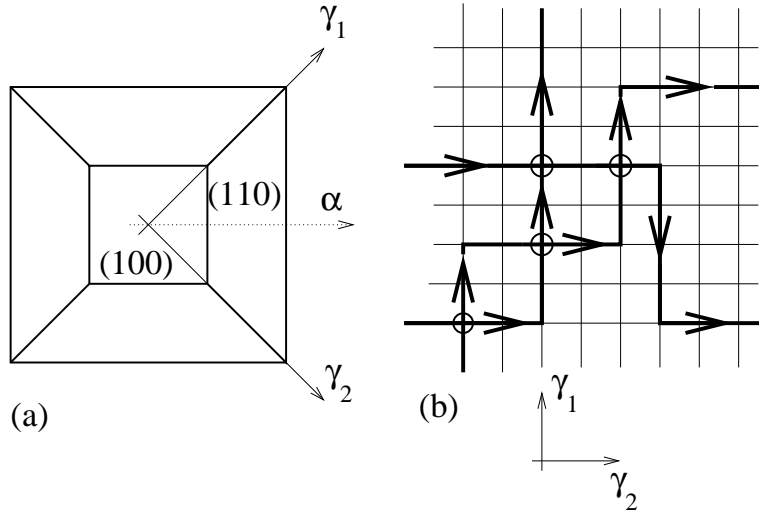


Figure 11: (a) At  $T = 0$  the equilibrium shape of the BCSO S model is a truncated pyramid. (b) Steps are composed of elongated segments with few corners since the energy of a corner is much larger than the energy of a straight segment of step  $e_K$ . Crossings of steps, indicated by circles in the figure, are energetically favored, i.e. at each crossing there is a gain of energy of  $2e$ .

other, with a gain of energy of  $2e$  at each crossing point. In this model, thus, the crossing energy is  $\sim -2e < 0$ .

The surface free energy has been calculated as function of the slope parameters  $p, q$  in mean field approximation, for all possible values of  $p$  and  $q$ , also beyond the vicinal orientations. To give an example, we restrict ourselves to considering only  $f(p)$ , i.e. the surface free energy for surface orientations of the type  $(1p0)$ , with  $0 \leq p \leq 1$ ; these are all the surface orientations along the axis of Fig. 11 (a). The mean field calculation gives a surface free energy that at low temperatures is not stable (Fig. 12 (a)): step attractions, due to the energy gained at crossings, dominate in the whole range of surface orientations and the network condenses until the optimal density of steps is reached, which in the present case corresponds to the (110) facet. In the equilibrium shape the two facets (100) and (110) touch each other at a sharp edge. The free energy instability is of the same form as that predicted in Eq.(8), with a negative value of  $\sim -$ .

We stress that the free energy  $f(p)$  of Fig. 12 (a) becomes convex for sufficiently large values of  $p$ . This change of sign of the second derivative of  $f(p)$  corresponds to a transition from a reconstructed to a non-reconstructed state. In the present case this critical point is of limited relevance since it occurs in an unstable region, and there seem to be no topological restrictions impeding the decay of an unstable orientation into two facets.

The same mean field analysis at somewhat higher temperatures gives a surface free energy of the type shown in Fig. 12 (b), which is also concave at low  $p$ , but convex at higher values of  $p$ . At low step densities, attractions still dominate, yielding a concave (i.e. unstable) free energy. Entropic repulsions (Gruher and Mullins, 1967) which become important at high temperatures and high step densities, stabilize the network. The Maxwell construction gives as coexisting surface orientations the (100) facet and a non-faceted orientation of slope  $p_0$ . These touch again at a sharp edge.

## REFERENCES

- Bemasconi, M. and Tosatti, E., 1993, Surf. Sci. Repts. 17:363.  
 Carlon, E., 1996, Ph.D. Thesis, Utrecht.

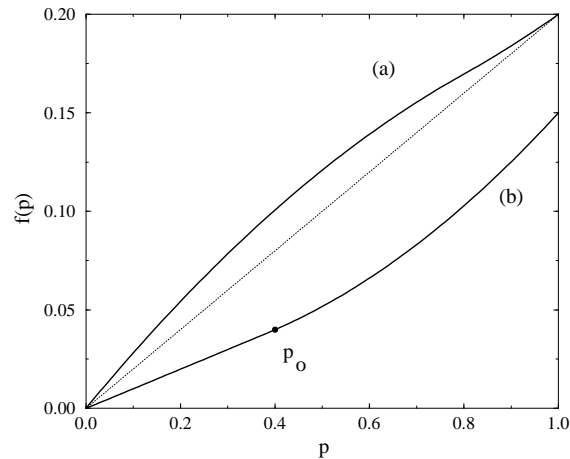


Figure 12: Surface free energy along the axis of Fig. 11. (a) At low temperatures the free energy is not stable for the whole range of orientations  $0 \leq p \leq 1$ ; the dotted line denotes the Maxwell construction. (b) At higher temperatures the range of orientations  $p_0 \approx 0.4 \leq p \leq 1$  is now stable.

- Carlton, E., Van Beijeren, H. and Mazzeo, G., 1996 Phys. Rev. E 53:5549;  
 Carlton, E. and Van Beijeren, H., 1996, Phys. Rev. Lett. 76:4191.  
 Carlton, E. and Van Beijeren, H., 1996, preprint.  
 Gimzewski, J.K., Berndt, R. and Schittler, R.R., 1992, Phys. Rev. B 45:6844.  
 Gritsch, T., Coulman, D., Behm, R.J. and Ertl, G., 1991, Surf. Sci. 257:297.  
 Guber, E.E. and Mullins, W.W., 1967, J. Phys. Chem. Solids 28:875.  
 Heyraud, J.C. and Mutois, J.J., 1980, Acta Metall. 28:1789.  
 Kuipers, L., 1994, Ph.D. Thesis Amsterdam.  
 Jayaprakash, C., Rottman, C. and Saam, W.F., 1984, Phys. Rev. B 30:6549.  
 Van Beijeren, H. and Nolden, I., 1987, in: Structure and Dynamics of Surfaces, Vol. 2, W. Schommers and P. von Blanckenhagen eds., Springer-Verlag, Berlin, 1987.