

Phase Separation in Electronic Models for Manganites

S. Yunoki¹, J. Hu¹, A. L. Malvezzi¹, A. Moreo¹, N. Furukawa², and E. Dagotto¹

¹ National High Magnetic Field Lab and Department of Physics, Florida State University, Tallahassee, FL 32306

² Institute for Solid State Physics, University of Tokyo, Roppongi 7-22-1, Minato-ku, Tokyo 106, Japan

(October 6, 2018)

The Kondo lattice Hamiltonian with ferromagnetic Hund's coupling as a model for manganites is investigated. The classical limit for the spin of the (localized) t_{2g} electrons is analyzed on lattices of dimension 1,2,3 and ∞ using several numerical methods. The phase diagram at low temperature is presented. A regime is identified where phase separation occurs between hole undoped antiferromagnetic and hole-rich ferromagnetic regions. Experimental consequences of this novel regime are discussed. Regions of incommensurate spin correlations have also been found. Estimations of the critical temperature in 3D are compatible with experiments.

PACS numbers: 71.10.-w, 75.10.-b, 75.30.Kz

The phenomenon of colossal magnetoresistance in metallic oxides such as $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$ has recently attracted considerable attention [1] due to its potential technological applications. A variety of experiments have revealed that oxide manganites have a rich phase diagram [2] with regions of antiferromagnetic (AF) and ferromagnetic (FM) order, as well as charge ordering, and a peculiar insulating state above the FM critical temperature, T_c^{FM} . Recently, *layered* manganite compounds $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ have also been synthesized [3] with properties similar to those of their 3D counterparts.

The appearance of ferromagnetism at low temperatures can be explained using the Double Exchange (DE) mechanism [4,5]. However, the DE model is incomplete to describe the entire phase diagram observed experimentally. For instance, the coupling of the electrons with the lattice may be crucial to account for the insulating properties above T_c^{FM} [6]. The presence of a Berry phase in the large Hund coupling limit also challenges predictions from the DE model [7]. In this paper we remark that another phenomena occurring in manganites which is not included in the DE description, namely the charge ordering effect, may be contained in a more fundamental Kondo model where the t_{2g} (localized) electrons are ferromagnetically (Hund) coupled with the e_g (mobile) electrons. More precisely, here we report the presence of *phase separation* (PS) between hole undoped antiferromagnetic and hole-rich ferromagnetic regions in the low temperature phase diagram of the FM Kondo model. Upon the inclusion of long-range Coulombic repulsion, charge ordering in the form of non-trivial extended structures may be stabilized. A similar phenomenon has been extensively discussed before in the context of the high-Tc superconductors, although without the presence of ferromagnetic domains [8,9]. In the cuprates neutron scattering experiments have shown indications of stripe formation [10], as predicted by theoretical calculations after the inclusion of Coulomb interactions [11]. The analysis reported in this paper suggests that phenomena as rich as observed in the cuprates may exist in the mangan-

ites, and hopefully the present results will induce further theoretical and experimental work in this context.

The FM Kondo Hamiltonian [4,12] is defined as

$$H = -t \sum_{\langle ij \rangle \sigma} (c_{i\sigma}^\dagger c_{j\sigma} + h.c.) - J_H \sum_{i\alpha\beta} c_{i\alpha}^\dagger \sigma_{\alpha\beta} c_{i\beta} \cdot \mathbf{S}_i, \quad (1)$$

where $c_{i\sigma}$ are destruction operators for one species of e_g -fermions at site \mathbf{i} with spin σ , and \mathbf{S}_i is the total spin of the t_{2g} electrons, assumed localized. The first term is the e_g electron transfer between nearest-neighbor Mn-ions, $J_H > 0$ is the Hund coupling, the number of sites is L , and the rest of the notation is standard. The density is adjusted using a chemical potential μ . In this paper the spin \mathbf{S}_i will be considered classical (with $|\mathbf{S}_i| = 1$) rather than quantum mechanical, unless otherwise stated. Phenomenologically $J_H \gg t$, but here J_H/t was considered an arbitrary parameter, i.e. both large and small values for J_H/t were studied. Although models beyond Eq.(1) may be needed to fully understand the manganites, it is important to study the properties of simple Hamiltonians to clarify if part of the experimental rich phase diagram can be accounted for using purely electronic models.

To study Eq.(1) in the t_{2g} spin classical limit a Monte Carlo technique was used: first, the trace over the fermionic degrees of freedom in the partition function was carried out exactly diagonalizing the $2L \times 2L$ Hamiltonian of electrons in the background of the spins $\{\mathbf{S}_i\}$, using library subroutines. Here the fermionic trace is a positive function of the classical spins and, thus, the resulting integration over the two angles per site parametrizing the \mathbf{S}_i variables can be performed with a standard Monte Carlo algorithm without "sign problems". In addition, part of the calculations were also performed with the Dynamical Mean-Field approximation ($D=\infty$) [12], the Density-Matrix Renormalization Group (DMRG), and the Lanczos method. Special care must be taken with the boundary conditions (BC). Closed shell BC or open BC are needed to stabilize a ferromagnetic spin arrangement. If other BC are used the spin correlations at short

distances are still strongly FM (if working at couplings where ferromagnetism is stable), but not at large distances where they become negative. This well-known effect was observed before in this context [13,14] and it does not present a problem in the analysis shown below.

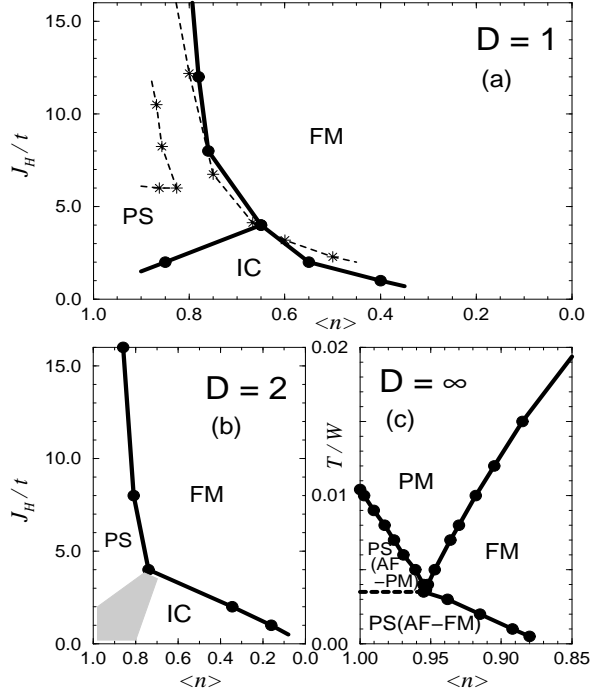


FIG. 1. Phase diagram of the FM Kondo model reported here. FM, IC, PM and PS denote regimes with strong FM correlations, incommensurate correlations, paramagnetic correlations, and with phase separation between undoped AF and hole-rich FM regions, respectively. (a) was obtained with MC simulations at $T = t/75$ using chains with $L=20, 30$ and 40 sites. The full circles correspond to classical spins. The stars and dashed lines are DMRG results obtained with t_{2g} spins $S=3/2$ on chains with up to $L=16$ sites keeping 48 states, and using $(2/3)J_H$ as coupling in the Hund term; (b) are MC results for classical spins at $T = t/50$ using $4 \times 4, 6 \times 6$ and 8×8 clusters. In the shaded region a crossover from PS to IC was observed but the actual boundary position is difficult to find accurately; (c) corresponds to results in the $D=\infty$ limit at a fixed coupling $J_H/W = 4.0$ and as a function of T and $\langle n \rangle$ (W is defined in the text). The “PS (AF-PM)” region denotes PS between undoped AF and hole-rich PM regions.

The results reported here can be summarized in the phase diagrams obtained for several dimensions D shown in Fig.1. In both 1D and 2D and at low temperatures clear indications of (i) strong ferromagnetism, (ii) incommensurate (IC) correlations, and (iii) a novel regime of phase separation were identified. For $D=1$ and 2 , finite size effects were found to be small for the lattice sizes used in this study, although the PS-IC boundary in 2D was

difficult to identify accurately and, thus, only a crossover is indicated. Results are also available in small 3D clusters and qualitatively they agree with those in Figs.1a-b. In 1D we also obtained results with quantum t_{2g} spins $S=3/2$. In this case the PS regime was studied calculating the compressibility with the DMRG technique, and the FM regime monitoring the ground state spin quantum number with the Lanczos method. The agreement with results in the classical limit is good, specially regarding the ferromagnetic line. PS for $S=3/2$ is between hole undoped AF and hole-rich non-fully-saturated FM regions. Similar results were obtained in the case $S=1/2$. In Fig.1c results in $D=\infty$ are shown at $J_H/W = 4$, where W is the half-width of the semicircular density of states $D(\epsilon) = (2/\pi W)\sqrt{1 - (\epsilon/W)^2}$ for the e_g electrons. In excellent agreement with the predictions for $D=1$ and 2 , at low temperatures phase separation between undoped AF and hole-rich FM regions was observed. For $\langle n \rangle < 0.88$ and $T/W \ll 1$ the ground state becomes ferromagnetic. The quantitative similarities between the results obtained for $D=1, 2$ and ∞ led us to believe that the conclusions of this paper are also valid for 3D manganese systems. Below the details justifying the proposed phase diagrams shown in Fig.1 are provided.

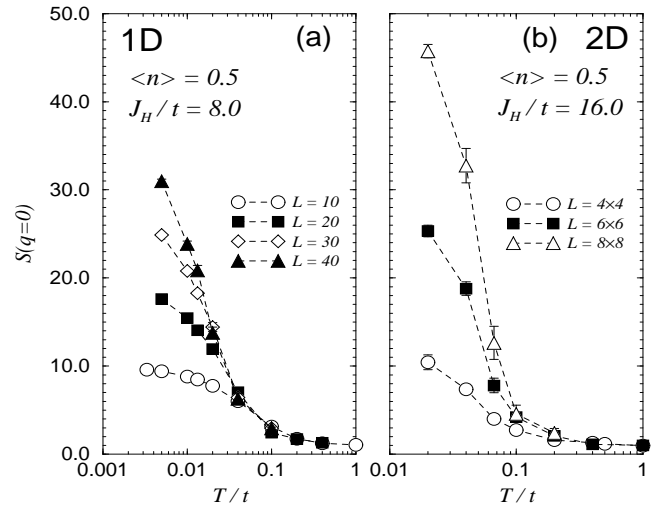


FIG. 2. Spin-spin correlations of the classical spins at zero momentum $S(\mathbf{q} = 0)$ vs temperature T (in units of t). Results for several lattice sizes are shown on (a) chains and (b) 2D clusters. The technique used is the Monte Carlo algorithm described in the text. The density and coupling are shown. In (a) closed shell BC are used i.e. periodic BC for $L = 10$ and 30 and antiperiodic BC for $L = 20$ and 40 . In (b) open BC are used.

The boundaries of the FM region of the phase diagram were found evaluating the spin-spin correlation between the classical spins defined as $S(\mathbf{q}) = (1/L) \sum_{\mathbf{j}, \mathbf{m}} e^{i(\mathbf{j}-\mathbf{m}) \cdot \mathbf{q}} (\mathbf{S}_{\mathbf{j}} \cdot \mathbf{S}_{\mathbf{m}})$. Fig.2 shows $S(\mathbf{q})$ at zero momentum vs. T/t for typical examples in 1D and 2D.

The rapid increase of the spin correlations as T is reduced and as the lattice size grows clearly points towards the existence of ferromagnetism in the system [15]. Repeating this procedure for a variety of couplings and densities, the robust region of FM shown in Fig.1 was determined, in qualitative agreement with previous studies at $D = \infty$ [12] and in the large J_H/t limit on 1D chains [13].

In the small J_H/t region incommensurate correlations were observed. IC effects were predicted using a Hartree-Fock approximation [16] as an alternative to canted FM [5]. The IC region was observed in our studies monitoring $S(\mathbf{q})$. Both in 1D and 2D there is one dominant peak which moves away from the AF location at $\langle n \rangle = 1$ towards zero momentum as $\langle n \rangle$ decreases. In the 2D clusters the peak moves from (π, π) towards $(\pi, 0)$ and $(0, \pi)$, rather than along the main diagonal. Our results confirm a tendency towards the development of IC correlations in the FM Kondo model [16,17]. However, our computational study predicts IC correlations only in the small and intermediate J_H/t regime i.e. in a region of parameter space not realized in the manganites. Details will be provided elsewhere.

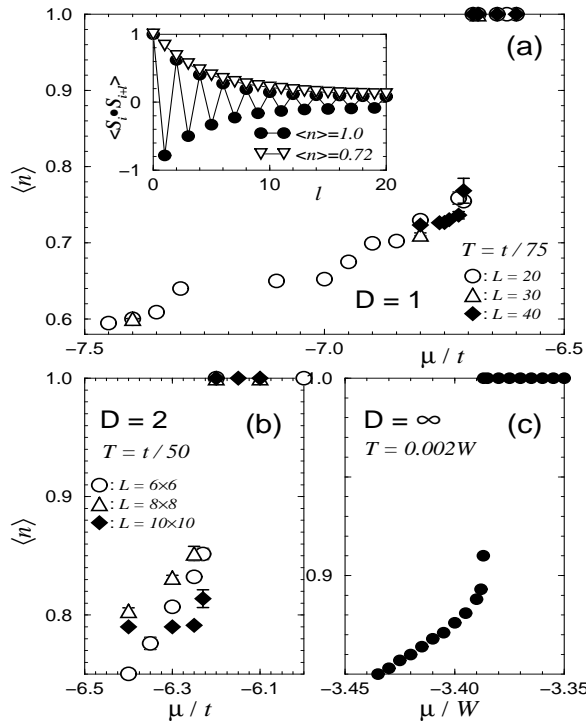


FIG. 3. Electronic density $\langle n \rangle$ vs chemical potential μ in (a) $D=1$, (b) $D=2$, and (c) $D = \infty$ clusters. The temperatures are indicated. The coupling is $J_H/t = 8.0$ in (a) and (b) and $J_H/W = 4.0$ in (c). The meaning of W is explained in the text. PBC were used both in $D=1$ and 2. The discontinuities shown in the figures are indicative of PS. In (a) the inset contains the spin-spin correlation in real space at densities 1.0 and 0.72 showing that indeed PS occurs between AF and FM regions.

The main result of the paper is contained in Fig.3 where the computational evidence for the existence of phase separation in dimensions 1, 2, and ∞ is given [18]. The presence of a discontinuity in $\langle n \rangle$ vs μ shows that some electronic densities can not be stabilized. If the system is nominally prepared with such density it will spontaneously separate into two regions with the densities corresponding to the extremes of the discontinuities of Fig.3 [19]. By analyzing these extremes the properties of the two domains can be studied. At least in the classical limit for the t_{2g} spins, one region is undoped ($\langle n \rangle = 1$) with strong AF correlations, while the other contains all the holes and the spin-spin correlations between the classical spins indicate the presence of strong FM correlations [20] (for a justification of this statement see the inset of Fig.3a. The results are similar in $D=2$ and infinite). This is natural since holes optimize their kinetic energy in a fully aligned background. On the other hand, at $\langle n \rangle = 1$ the DE mechanism is not operative: if the electrons fully align their spins they simply cannot move in the conduction band due to the Pauli principle. Then, energetically it is better to form an antiferromagnetic pattern (similar intuitive and numerical conclusions were reached for the case of $S=3/2$ and $1/2$ localized spins). As J_H grows, the jump in Fig.3 is reduced and it tends to disappear in the $J_H = \infty$ limit [21].

Experimentally, PS may be detectable using neutron diffraction techniques if the two coexisting phases have different lattice parameters as in $\text{La}_2\text{CuO}_{4+\delta}$, a Cu-oxide with hole-rich and hole-poor regions [22]. NMR and NQR spectra, as well as magnetic susceptibility measurements, can also be used to detect PS [23,24]. Note also that in the PS regime $S(\mathbf{q})$ presents a two peak structure, one located at the AF position and the other at zero momentum. Since this also occurs in a canted ferromagnetic state care must be taken in the analysis of the experimental data. In particular recent experimental results by Kawano et al. [25] are in qualitative agreement with Fig.1c since these authors observed a reentrant structural phase transition accompanied by “canted ferromagnetism” below T_c^{FM} , at $0.10 < x < 0.17$ in $\text{La}_{1-x}\text{Sr}_x\text{MnO}_3$. Also the polaron-ordered phase reported by Yamada et al. [26] can be reanalyzed in terms of the present results since it is known that the AF phase in 3D manganites is orthorhombic while the FM is pseudo-cubic. The formation of a lattice superstructure may stabilize the magnetic tendency to phase separate and minimize lattice distortions.

Another alternative is that Coulombic forces and low Sr mobility prevent the macroscopic accumulation of charge intrinsic of a PS regime. Thus, extended hole-rich domains in the form of stripes (as in cuprates) [11], or some other arrangement, could be formed. Although these details certainly deserve further work, the results in this paper are enough to show that tendencies similar to those found in models for the 2D cuprates, notably the $t - J$ model, may also be operative in manganites.

The main difference is that instead of separation between hole-poor AF and hole-rich superconducting regions, as in $\text{La}_2\text{CuO}_{4+\delta}$, here the observed PS is between undoped AF and hole-rich *ferromagnetic* regimes. Tendencies to pairing in Cu-oxides are replaced by tendencies to form ferromagnetic ground states in Mn-oxides [13].

Although the phase diagrams of Fig.1 have PS close to half-filling, actually this phenomenon should also occur at high hole doping $\langle n \rangle \sim 0$ if an extra direct AF exchange interaction between the localized t_{2g} spins is included. This coupling may be originated in a small hopping amplitude for the t_{2g} electrons. At $\langle n \rangle = 0$ model Eq.(1) supplemented by a Heisenberg coupling J'/t among the localized spins will certainly produce an AF phase, as in experiments, which upon electron doping will induce a competition between AF (with no e_g electrons) and FM electron-rich regions, similarly as in the half-filled limit but replacing holes by electrons. Previous studies in 1D support these claims [13]. Thus, PS or charge ordering could exist in manganites both at large and small fermionic densities.

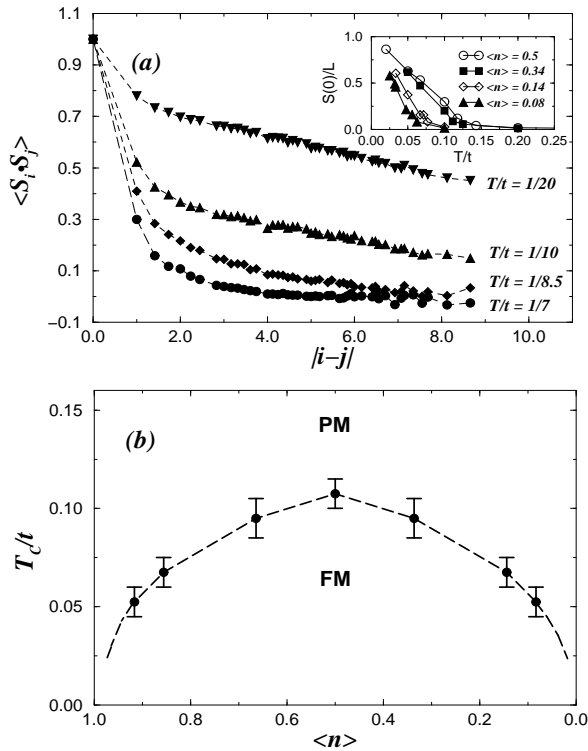


FIG. 4. (a) Real space spin-spin correlations among the classical spins at distance $|i - j|$ obtained with the MC technique at $\langle n \rangle = 0.5$, $J_H = \infty$, on a 6^3 cluster, and parametric with temperature T/t . The inset shows $S(\mathbf{q})$ at zero momentum and several densities vs T/t ; (b) Bounds on the critical temperature as estimated from data as shown in (a) as a function of $\langle n \rangle$.

For completeness, upper bounds on the critical temper-

ature T_c^{FM} in 3D systems are also provided. Using Monte Carlo simulations in principle it is possible to calculate T_c^{FM} accurately. However, the characteristics of the algorithm used here prevented us from studying clusters larger than 6^3 even at $J_H = \infty$. In spite of this limitation, monitoring the spin-spin correlations in real space allows us to judge at what temperature T^* the correlation length reaches the boundary of the 6^3 cluster. Since the bulk T_c^{FM} is smaller than T^* , this allows us to establish upper bounds for the critical temperature based on finite size cluster calculations. Fig.4a shows the spin-spin correlations at several temperatures in the $J_H = \infty$ limit and at $\langle n \rangle = 0.5$. When $T \sim 0.1t$ robust correlations reach the boundary, while for $T \geq 0.12t$ the correlation is short-ranged. Thus, at this density we estimate that $T_c^{FM} < 0.12t$. Results for several densities in this limit are shown in Fig.4b. For realistic densities, such as $\langle n \rangle \sim 0.7$, our results are about a factor 1.7 smaller than predicted by high temperature expansions [27] (this small discrepancy may be caused by the use of $S=1/2$ localized spins in Ref. [27]). Nevertheless the order of magnitude of both calculations is similar. Monitoring the rapid growth of the zero momentum spin correlations (inset of Fig.4a) provides similar bounds. T_c^{FM} is the highest at $\langle n \rangle = 0.5$, if $J_H = \infty$. Since results for the e_g electrons bandwidth range from $BW \sim 1 \text{ eV}$ [28] to $BW \sim 4 \text{ eV}$ [29], producing a hopping $t = BW/12$ between 0.08 and 0.33 eV, then our estimation for the critical temperature ranges roughly between $T_c^{FM} \sim 100 \text{ K}$ and 400 K. This is within the range observed experimentally, in agreement with other results [12,27], and in disagreement with previous estimations using classical spins that predicted a much higher critical temperature $T_c^{FM} \sim 2000 \text{ K}$ [6]. Then, purely electronic models can account for T_c^{FM} without resorting to electron-phonon couplings.

Summarizing, here the main conclusion of the paper is that the phenomenon of phase separation occurs in realistic models for manganites. Then, experimentalists should consider this potential regime in the interpretation of their results i.e. tendencies to phase separate could be as strong as those towards ferromagnetism in the real materials. Hopefully the present paper will trigger discussion on how phase separation will reveal itself in manganites from the experimental point of view. It is anticipated that the inclusion of long-range Coulombic interactions may stabilize complex charge ordered structures, that could be observed experimentally using a variety of techniques. Neutron scattering experiments should detect these charge fluctuations above the critical temperature, similarly as it occurs in the cuprates. From a more basic perspective, our results suggest that the existence of phase separation in the context of electronic models for transition metal oxides is a more general phenomenon than previously anticipated.

S. Y. is supported by the Japanese Society for the Promotion of Science. J. H. is supported by the Florida State grant E&G 502401002. He thanks E. Miranda for useful

discussions. A. L. M. acknowledges the financial support of the Conselho Nacional de Desenvolvimento Científico e Tecnológico (CNPq-Brazil) A. M. and E. D. are supported by the NSF grant DMR-9520776.

-
- [1] S. Jin, et al., Science **264**, 413 (1994).
- [2] P. E. Schiffer, A. P. Ramirez, W. Bao, and S-W. Cheong, Phys. Rev. Lett. **75**, 3336 (1995); C. H. Chen and S-W. Cheong, Phys. Rev. Lett. **76**, 4042 (1996).
- [3] Y. Moritomo, et al., Nature **380**, 141 (1996).
- [4] C. Zener, Phys. Rev. **82**, 403 (1951); P. W. Anderson and H. Hasegawa, Phys. Rev. **100**, 675 (1955).
- [5] P. G. de Gennes, Phys. Rev. **118**, 141 (1960).
- [6] A. J. Millis, P. B. Littlewood, and B. I. Shraiman, Phys. Rev. Lett. **74**, 5144 (1995); H. Röder, J. Zang and A. R. Bishop, Phys. Rev. Lett. **76**, 1356 (1996).
- [7] E. Müller-Hartmann and E. Dagotto, Phys. Rev. **B 54**, R6819 (1996).
- [8] V. J. Emery, S. A. Kivelson, and H. Q. Lin, Phys. Rev. Lett. **64**, 475 (1990). Note that here PS between AF hole-poor and FM hole-rich regions was also mentioned. However, in the $t - J$ model this may occur at unrealistic values of the couplings, while in the FM Kondo model it is present in the realistic regime. We thank S. Kivelson for this comment. See also V. J. Emery, and S. A. Kivelson, Physica **C 209**, 597 (1993).
- [9] E. Dagotto, Rev. Mod. Phys. **66**, 763 (1994).
- [10] J. M. Tranquada et al., Nature **375**, 561 (1995).
- [11] U. Löw et al., Phys. Rev. Lett. **72**, 1918 (1994); S. Haas et al., Phys. Rev. **B 51**, 5989 (1995).
- [12] N. Furukawa, J. Phys. Soc. Jpn. **63**, 3214 (1994); *ibid*, 2754 (1995).
- [13] J. Riera, K. Hallberg and E. Dagotto, Phys. Rev. Lett. **79**, 713 (1997).
- [14] K. Kubo, J. Phys. Soc. Jpn. **51**, 782 (1982); J. Zang, H. Röder, A. R. Bishop, and S. A. Trugman, J. Phys.: Condens. Matter **9**, L157 (1997); T. A. Kaplan and S. D. Mahanti, J. Phys.: Condens. Matter **9**, L291 (1997).
- [15] In both 1D and 2D the Mermin-Wagner theorem forbids a nonzero T_c^{FM} in the model. However, the correlation lengths can be very large even at finite T/t .
- [16] J. Inoue and S. Maekawa, Phys.Rev.Lett.**74**, 3407 (1995).
- [17] Our results for the IC correlations in 2D are in qualitative agreement with M. Hamada and H. Shimahara, Phys. Rev. **B 51**, 3027 (1995).
- [18] Up to 10^6 sweeps were needed to obtain accurate results in Fig.3.a-b, maintaining the acceptance rate close to 0.5.
- [19] Actually, by fine tuning μ to be very close to its “critical” value, a two peak structure was observed in $\langle n \rangle$ as in a first order phase transition.
- [20] It was observed that the FM correlations at the boundary with PS in Fig.1 are weaker than at the center of the FM phase, probably caused by a small $T = 0$ order parameter.
- [21] PS in manganites was also conjectured in Ref. [13] based on 1D studies of the “ $t - J$ ” version of Eq.(1).
- [22] P. G. Radaelli, et al., Phys. Rev. **B 49**, 6239 (1994) and references therein.
- [23] P. C. Hammel, et al., Phys. Rev. Lett. **71**, 440 (1993).
- [24] It is interesting to observe that experimental studies of $\text{Sr}_{2-y}\text{La}_y\text{MnO}_4$ have reported evidence for electronic phase separation and charge ordering at small y . See W. Bao, et al., preprint.
- [25] H. Kawano et al., Phys. Rev. **B 53**, R14709 (1996); Phys. Rev. **B 53**, 2202 (1996).
- [26] Y. Yamada et al., Phys. Rev. Lett. **77**, 904 (1996).
- [27] H. Röder, R. R. P. Singh, and J. Zang, Phys. Rev. **B 56**, 5084 (1997).
- [28] Y. Moritomo, A. Asamitsu and Y. Tokura, Phys. Rev. **B 51**, 16491 (1995).
- [29] D. D. Sarma et al., Phys. Rev. **B 53**, 6873 (1996).