

Double exchange magnets: Spin-dynamics in the paramagnetic phase

Peter Horsch^a, Janez Jaklič^{a,b}, and Frank Mack^a

(a) Max-Planck-Institut für Festkörperforschung, Heisenbergstr. 1, D-70569 Stuttgart (Germany)

(b) Max-Planck-Institut für Physik komplexer Systeme, Bayreuther Str. 40, D-01187 Dresden (Germany)

(December 31, 2021)

The electronic structure of perovskite manganese oxides is investigated in terms of a Kondo lattice model with ferromagnetic Hund coupling and antiferromagnetic exchange between t_{2g} -spins using a finite temperature diagonalization technique. Results for the dynamic structure factor are consistent with recent neutron scattering experiments for the bilayer manganite $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$. The susceptibility shows Curie-Weiss behaviour and is used to derive a phase diagram. In the paramagnetic phase carriers are characterized as ferromagnetic polarons in an antiferromagnetic spin liquid.

PACS numbers: 75.10.-b 75.40.Cx 75.40.Gb 25.40.Fq

Double exchange (DE) as an explanation of ferromagnetic order in doped manganites [1] was proposed shortly after the first experimental work on these compounds [2]. Open questions are connected with the proper understanding of the paramagnetic (PM) phase above the Curie temperature T_C and the giant magnetoresistance at the phase transition. Millis *et al* [3] argued that DE is neither sufficient to explain the size of the resistivity above T_C nor the activated form of $\rho(T)$ observed in many compounds, and suggested that Jahn-Teller polaron formation is essential. A different point of view [4], is that these systems are governed by strong correlations while spin disorder scattering is crucial for the understanding of the resistivity. Further complications not considered here may arise from orbital degeneracy [5,6] and charge disorder [7].

A detailed investigation of the spin-dynamics is therefore important for a deeper understanding of the manganites. Inelastic neutron scattering experiments in the PM-phase were performed recently by Perring *et al*. [8] for the highly doped bilayer manganite system $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ [9]. Particularly surprising was the observation of growing antiferromagnetic (AF) scattering at low energy parallel to increasing ferromagnetic (FM) critical scattering as the FM T_C was approached from above. Our aim here is to shed light on these experiments by an investigation of the spin-dynamics within a standard model for these compounds.

The appearance of ferromagnetism was explained by Zener [1] in terms of a strong Hund coupling J_H of the e_g conduction electrons to $S=3/2$ core spins \mathbf{S}_i^c formed by the energetically well separated t_{2g} -electrons. The e_g electron in Mn^{3+} couples to a $S=2$ high-spin configuration. A relevant model is the *ferromagnetic* Kondo lattice model [10–12]

$$H_{KLM} = - \sum_{ij\sigma} t_{ij} d_{i\sigma}^\dagger d_{j\sigma} - J_H \sum_{i\sigma\sigma'} \mathbf{S}_i^c \cdot d_{i\sigma}^\dagger \vec{\sigma}_{\sigma\sigma'} d_{i\sigma'} + J_{AF} \sum_{\langle ij \rangle} \mathbf{S}_i^c \cdot \mathbf{S}_j^c + U \sum_i n_{i\uparrow} n_{i\downarrow}. \quad (1)$$

The operators $d_{j\sigma}$ and \mathbf{S}_i^c refer to e_g -electrons and t_{2g} -

spins, respectively, while $n_{i\sigma} = d_{i\sigma}^\dagger d_{i\sigma}$ denotes the e_g -density operator. A typical value for the Hund coupling is $J_H \sim 1\text{eV}$, while the nearest neighbor hopping $t_{ij} = t \sim 0.15\text{eV}$ [6,13]. In view of the large local repulsion $U \sim 8\text{eV}$, we shall furtheron exclude double occupancy of e_g -orbitals, and define $J_H/t = 6$. The model explains ferromagnetism via the optimization of the kinetic energy of the $N_e = \sum_i n_{i\sigma}$ conduction electrons in the partially filled e_g band when the spins are aligned at low temperature. At low doping manganite materials are usually AF insulators. Antiferromagnetic superexchange interaction J_{AF} between the t_{2g} -electrons or spins is an obvious source of such correlations.

The interplay of the global AF exchange interaction with the local FM alignment induced by the motion of e_g -electrons via the DE mechanism is a subtle problem. A simple physical picture, which is consistent with our numerical study, is that of *ferromagnetic* spin polarons, where a local FM surrounding of t_{2g} -spins moves with the holes through an otherwise AF background.

Our calculations are based on a finite temperature diagonalization approach developed by Jaklič and Prelovšek [14], which was successfully used for the study of the t - J model. Here due to the much larger Hilbert space only relatively small systems can be solved. Nevertheless due to the high density of low energy excitations we believe that our results reflect already the physics of large systems. We have found large similarity between 1D and 2D systems, in striking contrast to the physics of the t - J model. We shall present here mainly 1D results, since the resolution in momentum space is larger. Our energy and temperature units are $t = 1$, while $S = 1$ is used instead of $S = 3/2$ t_{2g} -spins to save computer time.

A global measure for the evolution of magnetic correlations is given by the square of the total spin $\mathbf{S} = \sum_i \mathbf{S}_i$, which includes both core- and e_g -spins. Results for different e_g -concentration and J_{AF} are shown in Fig. 1(a). The high- T limit is determined by independent spins (i.e. for $T < J_H$; for even higher T also the e_g -spins decouple). In the absence of J_{AF} FM correlations develop as the temperature is lowered. For quite small J_{AF} this be-

haviour is already changed. For $J_{AF} = 0.1$ $\langle \mathbf{S}^2 \rangle$ decreases with decreasing temperature for a single hole. This suggests the evolution of AF correlations, while at higher doping FM correlations are established via the DE mechanism. Further insight is gained from the uniform susceptibility $\chi = \langle S_z^2 \rangle / Nk_B T$. The corresponding $1/\chi(T)$ -data, Fig. 1(b), show Curie-Weiss behavior, similar to experiments [15,16]. It is quite remarkable that for these small systems with $N = 6$ and 8 sites $1/\chi(T)$ follows a linear Curie-Weiss law to quite low temperatures, which allows us to determine a mean-field transition temperature T_C^{MF} . Deviations at lower temperatures are expected from non mean-field behavior of low-dimensional systems and finite size effects.

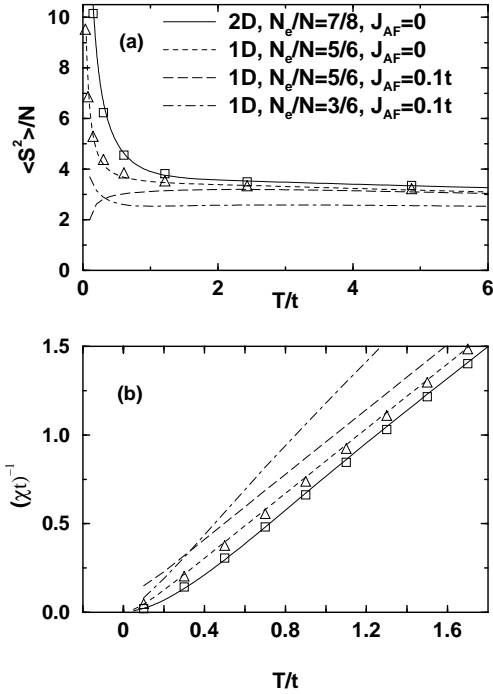


FIG. 1. Square of total spin (a) and inverse susceptibility (b) vs. temperature for hole concentrations $x = (1 - N_e/N) = 1/6, 3/6$ (1D) and $1/8$ (2D). A comparison with the FM polaron approach is shown for a single hole in 1D (triangles) and 2D (squares) for $J_{AF} = 0$.

The mean-field phase diagram (Fig. 2) reflects the interplay between antiferromagnetism and carrier induced ferromagnetism at higher doping. T_C^{MF} scales with coordination number and is consistent with the experimental T_C -scale. The value chosen for J_{AF} (~ 0.1) is typical for real systems [8,6]. For $J_{AF} = 0$ our data is well described by $T_C^{MF} \sim x(1-x)$ [4], while it differs in that respect from high-temperature series expansion results [17].

A simple estimate of $\langle \mathbf{S}^2 \rangle$ in terms of a *ferromagnetic* spin-polaron picture has been given by Varma [4] for the model without AF-interactions. The spin polaron is assumed to be determined by a number P of ferromag-

netically aligned spins around the hole which allows the particle to improve its kinetic energy. The gain in kinetic energy is counterbalanced by the loss of spin entropy due to the coupling of P spins, which can no longer rotate independently. An estimate for the change of free energy is $\delta E_P = at/P^\eta + Pk_B T \ln(2S_2 + 1)$. The kinetic energy exponent $\eta = 2/3, 1, 2$ in 3, 2, and 1-dimensions, respectively. Minimization leads to $P(T) = (\frac{\eta at}{Bk_B T})^{1/(1+\eta)}$ with $B = \ln(2S_2 + 1)$. Under the same assumptions the square of the total spin is given in terms of $S_P = (S_1 + PS_2)$

$$\langle \mathbf{S}^2 \rangle = N \left[x S_P (S_P + 1) + (1 - x - Px) S_2 (S_2 + 1) \right], \quad (2)$$

where in the case of few e_g -holes x is the hole concentration. Here $S_1 = 1$ and $S_2 = 3/2$ (instead of $3/2$ and 2). A comparison of this approach with exact diagonalization is shown in Figs. 1(a) and (b) for a 1D (2D) system with 6(8)-sites and one e_g hole. Good fits over the whole T -range were obtained by choosing smaller values for the exponent $\eta = 1.5(0.6)$ for 1D (2D), respectively.

The effective spin S_{eff} for a single polaron may be defined as $S_{eff}(S_{eff} + 1) = \langle \mathbf{S}^2 \rangle_T - \langle \mathbf{S}^2 \rangle_\infty$. Near T_C^{MF} we obtain $S_{eff} \sim 7$ for the two-dimensional case. This corresponds to an enhancement factor ~ 14 with respect to the spin $S = 1/2$ of the e_g conduction electron (hole). This result is qualitatively consistent with EPR experiments [16] where large effective spins at temperatures slightly above T_C were observed.

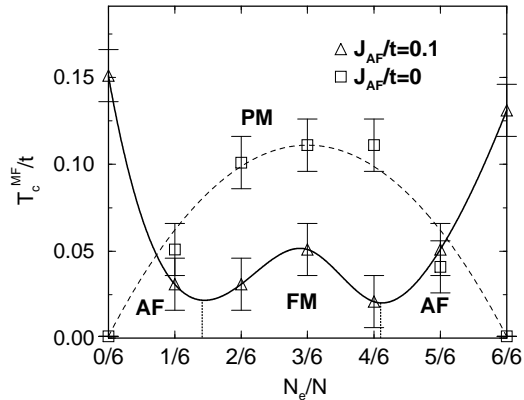


FIG. 2. Mean-field phase diagram of a 1D chain for $J_{AF} = 0.1$ (triangles) vs. $(1-x) = N_e/N$. The boundaries between AF, FM and PM phases (solid lines) are guides to the eye. (Anti)periodic boundary conditions were used for odd (even) electron number [18]. The $J_{AF} = 0$ data (squares) is compared with the predicted behavior $T_C^{MF} \sim x(1-x)$.

The study of correlation functions (CF) gives further support to the FM polaron picture even at high doping concentration and with frustrating AF interactions, although the simple formulation above is certainly not sufficient for these cases. The temperature dependence of the $\langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle$ correlation functions for $J_{AF} = 0.1$ is shown in Fig. 3. We distinguish (a) a low- and (b) a

high-doping case where the system approaches the AF (FM) phase (Fig. 2) at low temperature, respectively. In the single hole case (a) the nearest-neighbor (n.n.) CF becomes AF as T is lowered, while further neighbor correlations remain small. The CF's for $x = 0.5$ (b) become all FM at low T . Yet it is interesting to notice that for intermediate T the n.n. CF is antiferromagnetic. For $T \gg t$ all CF's vanish.

To investigate the structure of the spin-polaron we calculate the *relative correlation function* (RCF)

$$C_n^{n+1} = \sum_i \langle n_i^h \mathbf{S}_{i+n} \cdot \mathbf{S}_{i+n+1} \rangle, \quad (3)$$

which measures the spin-CF $\langle \mathbf{S}_0 \cdot \mathbf{S}_1 \rangle$ in a distance \mathbf{n} from the position of the moving hole. Here $n_i^h = (1 - n_i)$ and \mathbf{l} is a lattice vector. The results in Fig. 3 show the FM alignment of the spins at the position of the hole and on the neighboring site, i.e. C_0^1 , at low T even in the single hole case where $\langle \mathbf{S}_0 \cdot \mathbf{S}_1 \rangle$ becomes antiferromagnetic. The large drop at very small T suggests that FM-polarons are unstable in the low temperature AF-phase consistent with Fig. 1(a). The CF's C_0^1 are weakly antiferromagnetic at higher temperatures similar to $\langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle$.

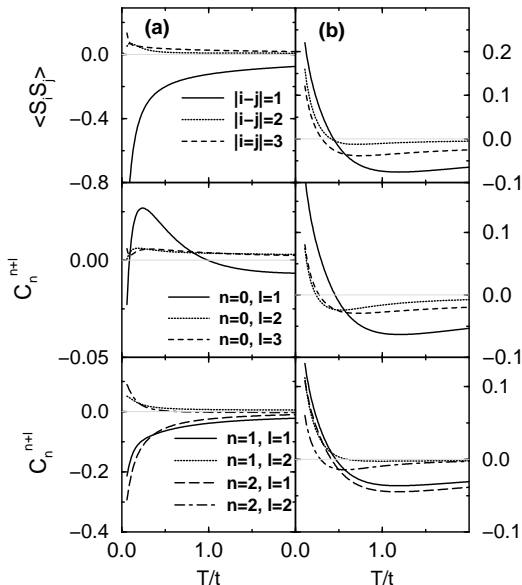


FIG. 3. Temperature dependence of spin correlation functions $\langle \mathbf{S}_i \mathbf{S}_j \rangle$ and C_n^{n+1} (Eq. 3) for one (a) and 3 e_g -holes (b) for a 6-site chain with $J_{AF} = 0.1$.

In the single hole case (a) all other ($n \neq 0$) RCF's become gradually AF with decreasing temperature, i.e. indicating that the AF-phase dominates. The CF's for $x = 0.5$ (b) are indicative for frustrated antiferromagnetism at temperatures above $T \sim 0.5$, while at lower temperature all CF's become ferromagnetic. Hence on the basis of these *equal-time* CF's there is no evidence for significant AF correlations at low T near T_C^{MF} for high

doping. Nevertheless there are clear AF-correlations in the low-frequency response.

The complete information about the spin-dynamics is contained in the dynamic structure factor

$$S_q(\omega) = \frac{1}{2\pi} \int_{-\infty}^{\infty} dt \exp(-i\omega t) \langle \mathbf{S}_q \mathbf{S}_{-q}(t) \rangle, \quad (4)$$

which can be directly measured by inelastic neutron scattering. A central result of this work is the evolution of $S_q(\omega)$ with temperature (Fig. 4). As an example results for a 6-site chain with 3 e_g -holes are shown for $J_{AF} = 0$ (a) and 0.1 (b) at different momenta. At high T critical scattering extends over the whole Brillouin zone, while at low temperature it is confined to $q \sim 0$ in the absence of AF-interactions. In case (a) FM magnons emerge when lowering the temperature already well above $T_C^{MF} \sim 0.1$. Their energy scale is consistent with theoretical work on the magnon dispersion [19] and neutron scattering in the FM-phase [20] of $\text{La}_{0.7}\text{Pb}_{0.3}\text{MnO}_3$. Antiferromagnetic frustration appears to be small in this system, since already LaMnO_3 consists of FM planes with a well developed magnon spectrum even at T_C [21]. The interlayer coupling is AF and weak in this system.

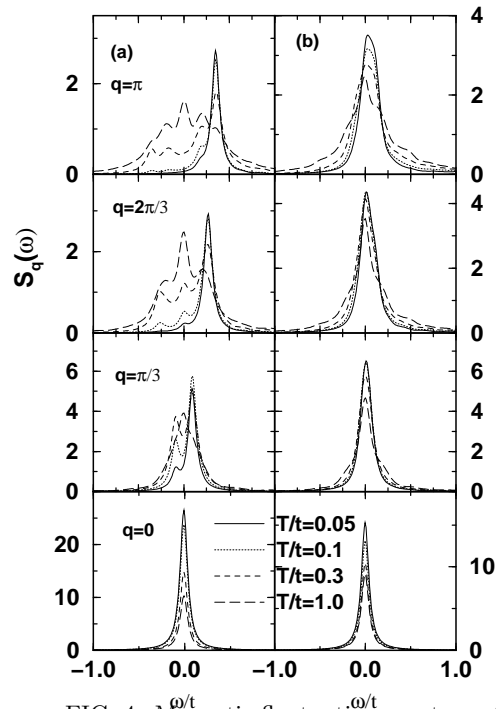


FIG. 4. Magnetic fluctuation spectrum $S(q, \omega)$ as function of ω for different momenta and temperatures. Data for a 6-site chain with e_g -electron concentration $x = 0.5$ for (a) $J_{AF} = 0$ and (b) $J_{AF} = 0.1$.

In the frustrated case (b) the magnon structures are hardly visible, consistent with a substantial softening. The dominant feature is *critical scattering for all q* . As temperature is lowered FM-critical scattering is dominant, yet surprisingly low energy AF-correlations at

$q = \pi$ are growing as well. We note that our data is broadened by $\delta = 0.05$. The natural linewidth of the $\omega \sim 0$ structures appears to be smaller than T .

The low frequency response $\delta S(\mathbf{q}) = \int_{-\omega_c}^{\omega_c} d\omega S_{\mathbf{q}}(\omega)$ integrated over a small energy window ($\omega_c = 0.05$), is frequently measured in neutron scattering experiments [8]. It is interesting to contrast the momentum dependence of $\delta S(\mathbf{q})$ from the behavior of the static structure factor $S(\mathbf{q}) = \int_{-\infty}^{\infty} d\omega S_{\mathbf{q}}(\omega)$, which measures equal-time correlations (Fig. 5). In the high-temperature limit $S(\mathbf{q})$ is constant, reflecting the absence of spin-correlations. At low temperature $S(\mathbf{q})$ develops a peak centered at $q = 0$ in the model without antiferromagnetic interactions due to carrier induced ferromagnetic correlations. With increasing J_{AF} the data shows the evolution of short-range (nearest-neighbor) AF correlations.

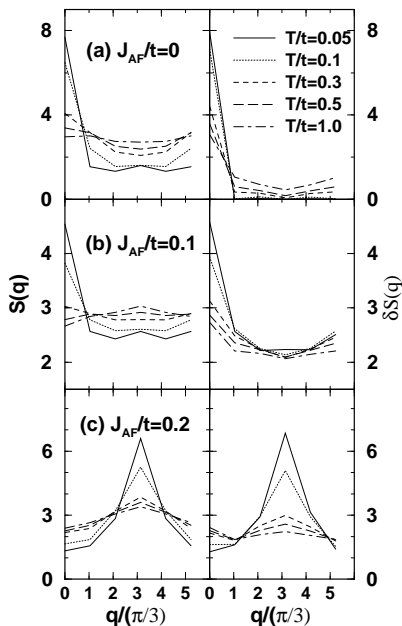


FIG. 5. Comparison of $S(\mathbf{q})$ and integrated low-frequency response $\delta S(\mathbf{q})$; parameters as in Fig. 4.

The observation of pronounced AF-correlations in $\delta S(\mathbf{q})$, e.g. for $J_{AF} = 0.1$, in the presence of FM critical scattering is consistent with the experimental finding of local AF correlations by Perring *et al* [8]. These experiments show strong AF correlations in the PM-phase (at low frequency) and their sudden disappearance at T_C when the low- T FM-order is established. We stress that the observation of a well defined AF peak in the low-frequency spin-fluctuation spectrum $S_{\mathbf{q}}(\omega \rightarrow 0)$ is actually very surprising since these experiments were performed for a highly doped ($x = 0.4$) double-layer system and at temperatures slightly above the transition into the FM-phase. We find considerable qualitative agreement between the present model and neutron scattering,

although we do not find a significant peak structure in the momentum dependence at $q = \pi$, except for larger values for J_{AF} where the FM scattering is reduced. The disappearance of the AF signal in the low-temperature FM phase [8] is consistent with our studies [22].

In summary we have shown, that the competition between AF and FM correlations detected by neutron scattering in the highly doped double layer compound $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ is consistent with the physics of the frustrated Kondo lattice model. From our study of various correlation functions, we conclude that the temperature and doping dependence of the magnetic correlations in the *paramagnetic phase* can be qualitatively understood in terms of FM polarons moving in a short-range AF-spin liquid. Slow spin-dynamics as a consequence of frustration may lead to localization of magnetic polarons.

We would like to thank G. Khaliullin, K. Kubo and A. M. Oles for stimulating discussions. Partial support by E.U. Grant No. ERBCHRC CT94.0438 is acknowledged.

-
- [1] C. Zener, Phys. Rev. **82**, 403 (1951).
 - [2] G. H. Jonker and J.H. van Santen, Physica (Utrecht) **16**, 337 (1950).
 - [3] A. J. Millis, P. B. Littlewood, and B. I. Shraiman, Phys. Rev. Lett. **74**, 5144 (1995).
 - [4] C. M. Varma, Phys. Rev. B **54**, 7328 (1996).
 - [5] K. I. Kugel and D. I. Khomskii, Sov. Phys.-JETP **37**, 725 (1973).
 - [6] S. Ishihara, J. Inoue, and S. Maekawa, Phys. Rev. B **55**, 8280 (1997).
 - [7] R. Allub and B. Alascio, Phys. Rev. B **55**, 14113 (1997).
 - [8] T. G. Perring *et al.*, Phys. Rev. Lett. **78**, 3197 (1997).
 - [9] Y. Moritomo *et al.*, Nature **380**, 141 (1996).
 - [10] K. Kubo and N. Ohata, J. Phys. Soc. Jpn. **33**, 21 (1972).
 - [11] J. Riera, K. Hallberg, and E. Dagotto, cond-mat/9609111.
 - [12] T. A. Kaplan and S. D. Mahanti, J. Phys.: Cond. Mat. **9**, L291 (1997).
 - [13] S. Satpathy, Z. S. Popović, and F. R. Vukajlović, Phys. Rev. Lett. **76**, 960 (1996);
 - [14] J. Jaklič and P. Prelovšek, Phys. Rev. B **49**, 5065 (1994).
 - [15] J. O'Donnell *et al.*, Phys. Rev. B **54**, R6841 (1996).
 - [16] S. B. Oseroff *et al.*, Phys. Rev. B **53**, 6521 (1996).
 - [17] H. Röder, R.R.P. Singh, and J. Zang, cond-mat/9703146
 - [18] Alternating boundary conditions were chosen to favor high-spin states and to guarantee a systematic dependence on doping. See also [11,12].
 - [19] N. Furukawa, J. Phys. Soc. Jpn. **65**, 1174 (1996).
 - [20] T. G. Perring *et al.*, Phys. Rev. Lett. **77**, 711 (1996).
 - [21] K. Hirota *et al.*, J. Phys. Soc. Jpn. **65**, 3736 (1996).
 - [22] F. Mack, J. Jaklič, and P. Horsch, (unpublished).