

Cu-Au, Ag-Au, Cu-Ag and Ni-Au intermetallics: First-principles study of phase diagrams and structures

V. Ozolins, C. Wolverton, and Alex Zunger
National Renewable Energy Laboratory, Golden, CO 80401
(September 14, 1997)

The classic metallurgical systems { noble metal alloys } that have formed the benchmark for various alloy theories, are revisited. First-principles fully relaxed general potential LAPW total energies of a few ordered structures are used as input to a mixed-space cluster expansion calculation to study the phase stability, thermodynamic properties and bond lengths in Cu-Au, Ag-Au, Cu-Ag and Ni-Au alloys. (i) Our theoretical calculations correctly reproduce the tendencies of Ag-Au and Cu-Au to form compounds and Ni-Au and Cu-Ag to phase separate at $T = 0$ K. (ii) Of all possible structures, Cu_3Au (L_{12}) and CuAu (L_{10}) are found to be the most stable low-temperature phases of $\text{Cu}_{1-x}\text{Au}_x$ with transition temperatures of 530 K and 660 K, respectively, compared to the experimental values 663 K and 670 K. The significant improvement over previous first-principles studies is attributed to the more accurate treatment of atomic relaxations in the present work. (iii) LAPW formation enthalpies demonstrate that L_{12} , the commonly assumed stable phase of CuAu_3 , is not the ground state for Au-rich alloys, but rather that ordered h100i superlattices are stabilized. (iv) We extract the non-configurational (e.g., vibrational) entropies of formation and obtain large values for the size mismatched systems: $0.48 k_B/\text{atom}$ in $\text{Ni}_{0.5}\text{Au}_{0.5}$ ($T = 1100$ K), $0.37 k_B/\text{atom}$ in $\text{Cu}_{0.441}\text{Ag}_{0.559}$ ($T = 1052$ K), and $0.16 k_B/\text{atom}$ in $\text{Cu}_{0.5}\text{Au}_{0.5}$ ($T = 800$ K). (v) Using 8 atom/cell special quasirandom structures we study the bond lengths in disordered Cu-Au and Ni-Au alloys and obtain good qualitative agreement with recent EXAFS measurements.

PACS numbers: 61.66.Dk, 71.20.Gj, 81.30.Bx

I. INTRODUCTION: CHEMICAL TRENDS IN NOBLE METAL ALLOYS

Noble metal alloys are, experimentally, among the most studied intermetallic systems.^{1,24} In addition, the Cu-Au system has been considered the classic paradigm system for applying different theoretical techniques of phase diagram and phase stability calculations.^{25,63} Most notably, this system has been considered as the basic test case for the classic Ising-Hamiltonian statistical-mechanics treatment of alloys.^{25,32} More recently, noble metal binary alloys have been treated theoretically via empirical fitting of the constants in Ising-Hamiltonians,^{25,34} semiempirical interatomic potentials,^{35,47} and via first-principles cluster expansions.^{48,55} The essential difference in philosophy between the classical application of Ising models to CuAu ^{25,30,33} and more modern approaches based on the density functional formalism⁶⁴ is that in the former approach the range and magnitudes of the interactions are postulated at the outset (e.g., first or second neighbor pair interactions), while the latter approaches make an effort to determine the interactions from an electronic structure theory. However, despite recent attempts,^{48,54} it is still not clear whether the noble metal alloys can be essentially characterized as systems with short-range pair interactions, or not.

Now that first-principles cluster expansion approaches^{65,66} have advanced to the stage where both

$T = 0$ ground state structures and finite-temperature thermodynamic quantities can be predicted without any empirical information, it is interesting to take a global look at the noble metal alloy family. Table I summarizes some of the salient features^{1,4,14,15,18,67,69} of the four binary systems Cu-Au, Ag-Au, Cu-Ag and Ni-Au. We included the relative lattice constant mismatch $a = \bar{a} = 2 \bar{p}_A - \bar{p}_B$ between the constituents,⁶⁷ the electronegativity difference $\chi = \chi_A - \chi_B$ on the Pauling scale,⁶⁸ the mixing enthalpy of the equiatomic alloy,^{2,18} the sign of the calculated nearest neighbor pair interaction J_2 (present study), the structural identity of the low-temperature phases^{1,4,67} and the order-disorder transition (or miscibility gap) temperatures^{2,69} T_c . Some interesting observations and trends which we will attempt to reproduce theoretically, are apparent from this general survey:

(i) Despite a large (12%) size mismatch in Cu-Au, and a small (0%) size mismatch in Ag-Au, both systems form ordered compounds at low temperatures and have negative mixing enthalpies, suggesting attractive ("anti-ferromagnetic") A-B interactions. Thus, when the difference in the electronegativity of the constituent atoms is sufficiently large, as it is in CuAu and AgAu, size mismatch apparently does not determine ordering vs. phase separation tendencies.

(ii) Despite a similar size mismatch (12%) in Cu-Au and Cu-Ag, the former orders while the latter phase-separates. Thus, the existence of large electronegativity

TABLE I. Major physical properties of Ag-Au, Cu-Ag, Cu-Au and Ni-Au alloys. We give constituent size mismatches, $a = \bar{a} = 2(a_A - a_B)/(a_A + a_B)$, electronegativity differences on the Pauling scale,⁶⁸, mixing enthalpies of the disordered alloys at the equiatomic composition, $H_{mix}(x = \frac{1}{2})$, signs of the nearest-neighbor Ising interaction, J_2 , order-disorder transition temperatures (or miscibility gap temperatures for Cu-Ag and Ni-Au), $T_c(x = \frac{1}{2})$, and excess entropies of solid solutions, S_{tot}^{form} and S_{ideal} . All phases are fcc-based.

System	$a = \bar{a}$ ^a	b ^b	$H_{mix}(x = \frac{1}{2})$ (meV/atom)	J_2	Low-T phases ^g	$T_c(x = \frac{1}{2})$ (K)	S_{tot}^{form} (k _B /atom)	S_{ideal} ^g (k _B /atom)
Cu-Au	12%	0.64	91 ^c	> 0	L1 ₂ , L1 ₀ , L1 ₂ (?)	683 ^g	+ 0.36	
Ag-Au	0%	0.61	48 ^d	> 0	L1 ₂ , L1 ₀ , L1 ₂	115-168 ^h	0.17	
Cu-Ag	12%	0.03	+ 80 ^e	< 0	Phase sep.	> T _m	+ 0.04	
Ni-Au	15%	0.63	+ 76 ^f	> 0	Phase sep.	1083 ^d	+ 0.35	

^aRef. 67.

^bRef. 68.

^cRefs. 15, 14, 2.

^dRef. 2.

^eTheoretically calculated value from this work.

^fRefs. 2, 18.

^gRefs. 2, 4.

^hRef. 69.

difference in Cu-Au (as opposed to the small difference in Cu-Ag), seems to induce ordering tendencies.

(iii) Cu-Ag and Ni-Au both phase-separate (and have positive H_{mix}) as they have large size mismatches. Yet, Ni-Au having a large electronegativity difference, shows an ordering-type nearest-neighbor pair interaction ($J_2 > 0$), just like the compound forming Cu-Au and Ag-Au, while Cu-Ag has a clustering-type nearest-neighbor interaction ($J_2 < 0$). Thus, the sign of J_2 does not reflect the low temperature ordering vs. phase separation.

(iv) The amount $S_{XS} = S_{tot}^{expt} - S_{ideal}$ by which the measured entropy² S_{tot}^{expt} deviates from the ideal configurational entropy $S_{ideal} = k_B [x \log x + (1-x) \log(1-x)]$, is unexpectedly large in Cu-Ag and Ni-Au, indicating a large non-configurational entropy of formation.

Other interesting facts about the noble metal binary intermetallics include:

(v) Despite numerous studies,^{1{4;7;8;10{12} the structure of the ordered phases in Au-rich Cu-Au is not well established yet. It is often assumed^{1{4} that the stable Au-rich low-temperature phase is CuAu₃ in the L1₂ structure, but direct experiments^{7;8;10} below the order-disorder transition temperature $T_c(x = \frac{3}{4}) \approx 500$ K are difficult because the diffusion rates are very low and even the best ordered samples contain significant disorder. Possible further thermodynamic transformations at lower temperatures may be kinetically inhibited.

(vi) The trends in bond lengths vs. composition are non-trivial. Traditionally, all coherent-potential-approximation based theories^{70{72} of intermetallic alloys have assumed that the nearest-neighbor bond lengths are equal, $R_{AA} = R_{AB} = R_{BB}$, and proportional to the average lattice constant. Recent theories^{73{75} suggested, however, that bond lengths relax in the alloy to new values, and this has a significant effect on the electronic structure.^{53;76;77} Recent EXAFS experiments on NiAu²³

and CuAu²⁴ show distinct $R_{AA} \neq R_{AB} \neq R_{BB}$ bond lengths, which need to be explained.

In this work we will analyze the above mentioned trends in terms of a first-principles mixed-space cluster expansion,^{65;66} based on modern local density approximation (LDA) total energy calculations. We reproduce the observed trends (i)-(vi) in ordering preferences, mixing enthalpies H_{mix} , transition temperatures T_c and interatomic bond lengths. In addition, we predict new, hitherto unsuspected ordered phases in Au-rich Cu-Au alloys.

II. BASIC IDEOLOGY AND METHODOLOGY

There are many problems in solid state physics that require knowledge of the total energy $E(\gamma)$ of a lattice with N sites as a function of the occupation pattern of these sites by atoms of types A and B. This information is needed, for example, in the ground state search problem,⁷² where one seeks the configuration with the lowest energy at $T = 0$ K. $E(\gamma)$ is also needed for calculating the temperature- and composition-dependent thermodynamic functions and phase diagrams of an $A_{1-x}B_x$ alloy.

A direct, quantum-mechanical calculation of the total energy $E_{direct}(\gamma) = \langle \gamma | \hat{H} | \gamma \rangle$ (where γ is the electronic ground state wave function and \hat{H} is the many-electron Hamiltonian) is possible only for a limited set of configurations. This is so because (i) the computational effort to solve the Schrodinger equation for a single configuration scales as the cube of the number of atoms per unit cell, so that only small unit cells can be considered, (ii) there are 2^N configurations, and (iii) for each configuration, one has to find the atomic relaxations $u_{min}(\gamma)$ which minimize the total energy. Consequently, one searches for a "cluster expansion" (CE) that

accurately reproduces the results of a direct, quantum-mechanical (e.g., LDA) calculation

$$E_{CE}(\mathbf{r}) = E_{\text{direct}}(\mathbf{r}); \quad (1)$$

without the unfavorable scaling of the computational cost with the size of the unit cell.

In designing a cluster expansion, there are few choices of independent parameters. For example, one could choose to obtain a cluster expansion for the volume- (V) dependent equation of state $E_{\text{direct}}(\mathbf{r}; V)$ [see, e.g., Refs. 52, 78, 79], or to find a cluster expansion for the energy at the volume $V_{\text{min}}(\mathbf{r})$ that minimizes $E_{\text{direct}}(\mathbf{r}; V)$. We choose the latter possibility. Furthermore, for each configuration, we wish to reproduce the total energy corresponding to the fully relaxed cell shape and atomic positions $\mathbf{r}_{\text{min}}(\mathbf{r})$. In other words, we choose to represent

$$E_{CE}(\mathbf{r}) = E_{\text{direct}}[\mathbf{r}; \mathbf{r}_{\text{min}}(\mathbf{r}); V_{\text{min}}(\mathbf{r})] - E_{\text{direct}}(\mathbf{r}); \quad (2)$$

Note that by focusing on the equilibrium energy of each configuration, we give up the possibility of studying non-equilibrium geometries (e.g., bond lengths) and equations of state. Instead, for each occupation pattern, we can find the total energy $E(\mathbf{r})$ of the atomically relaxed and volume-optimized geometry.

The best-known cluster expansion is the generalized Ising model in which the equilibrium total energy of an arbitrary configuration is expanded in a series of basis functions defined as pseudospin products on the crystal sites:

$$E(\mathbf{r}) = J_0 + \sum_i J_{1i} S_i + \frac{1}{2} \sum_{i \neq j} J_{ij} S_i S_j + \frac{1}{3!} \sum_{i \neq j \neq k} J_{ijk} S_i S_j S_k + \dots; \quad (3)$$

where in binary $A_1 \times B_x$ alloys $S_i = +1$ or -1 , depending on whether the site i is occupied by an atom of type A or B. Equation (3) is valid whether the lattice is relaxed or not, as long as a one-to-one correspondence exists between the actual positions of atoms and the ideal fcc sites. The practical usefulness of the cluster expansion Eq. (3) rests on the assumption that the effective cluster interactions (ECI's), $J_{ij}; J_{ijk}; \dots$, are rapidly decreasing functions of the number of sites and intersite separation, so that only a finite number of terms has to be kept in Eq. (3) for the desired accuracy. In this case, we can write the formation enthalpy of structure \mathbf{r} ,

$$H_{\text{direct}}(\mathbf{r}) = E(\mathbf{r}) - x E_A - (1-x) E_B; \quad (4)$$

where E_A and E_B are total energies of the pure constituents A and B, as the following cluster expansion (CE):

$$H_{CE}(\mathbf{r}) = J_0 + \sum_f D_f \overline{J_f}(\mathbf{r}); \quad (5)$$

Here N_f is the number of nonzero effective interactions and $\overline{J_f}(\mathbf{r})$ are lattice averages of the spin products in configuration \mathbf{r} .

Sanchez, Ducastelle and Gratias⁸⁰ have shown that there is a set of composition-independent interactions for Eq. (3) which can exactly reproduce the directly calculated total energies of all configurations. This statement is strictly true if all possible clusters are included in Eq. (3), and should hold for the truncated series Eq. (3) if the cluster expansion is well converged. Several methods^{81;82} yield concentration-dependent effective interactions, providing in principle equally valid schemes for representing $H_{\text{direct}}(\mathbf{r})$ in terms of a cluster expansion. In the present work, we select composition-independent interactions, since these can be directly compared to previous Ising model treatments^{25;34;48;55} of the noble metal alloy phase diagrams.

A number of issues arise in trying to construct a cluster expansion that satisfies Eq. (2):

(i) The number of interactions and their types (pair, multibody) cannot be decided arbitrarily, but must be constrained by a microscopic electronic-structure theory according to Eqs. (1) and (2).

(ii) In most configurations, atoms move away from the ideal lattice sites, which not only lowers the total energies $E_{\text{direct}}(\mathbf{r})$, but also slows down the convergence⁸⁵ of the expansion Eq. (3). The solution is to have a cluster expansion with many interaction terms N_J that can represent such situations. We accomplish this by using a reciprocal space formulation, formally equivalent to an infinite number of real-space pair interactions.

(iii) Some cluster expansions⁷⁸ require that the number of interactions N_J must equal the number of configurations N whose total energies need to be evaluated via the direct electronic-structure method. The number of such calculations may be excessive in view of (ii). We thus introduce a method in which $N < N_J$. Furthermore, interactions that are not needed to satisfy Eq. (2) are automatically discarded.

(iv) One has to deal with the macroscopic elastic strain leading to a $k \rightarrow 0$ singularity in the Fourier transform of the pair interactions,

$$J_{\text{pair}}(\mathbf{k}) = \sum_j D_j J_{\text{pair}}(\mathbf{R}_i - \mathbf{R}_j) e^{i\mathbf{k} \cdot \mathbf{R}_j}; \quad (6)$$

where D_j is the number of $\mathbf{R}_i; \mathbf{R}_j$ pairs per lattice site. As shown by Laks et al.⁶⁵ (see also the discussion below), in size mismatched systems the correct $J_{\text{pair}}(\mathbf{k})$ depends on direction $\hat{\mathbf{k}}$ in the long-wavelength limit $k \rightarrow 0$. To solve this, we express $J_{\text{pair}}(\mathbf{k})$ as a sum of two parts,

$$J_{\text{pair}}(\mathbf{k}) = J_{\text{SR}}(\mathbf{k}) + J_{\text{CS}}(\hat{\mathbf{k}}); \quad (7)$$

where $J_{\text{SR}}(\mathbf{k})$ is an analytic function of \mathbf{k} and can be obtained from short-ranged real space pair interactions, while $J_{\text{CS}}(\hat{\mathbf{k}})$ contains the nonanalytic behavior around

$k = 0$ and depends only on the direction \hat{k} . To explain this singularity, we consider the energy of a coherent A_nB_n superlattice, formed by a periodic stacking of n layers of A and n layers of B in direction $\hat{\Phi}$. By introducing the structure factor,

$$S(\mathbf{k};) = \sum_j S_j e^{i\mathbf{k} \cdot \mathbf{R}_j}; \quad (8)$$

the total pair interaction energy in Eq. (3) can be expressed as a reciprocal space sum:

$$E_{\text{pair}}(;) = \sum_k J_{\text{pair}}(\mathbf{k}) S(\mathbf{k};)^2; \quad (9)$$

A_nB_n superlattice has nonzero structure factor at $\mathbf{k} = \frac{1}{2n}\hat{\Phi}$, and therefore its energy is determined by $J_{\text{pair}}(\frac{1}{2n}\hat{\Phi})$. As $n \rightarrow 1$ its formation energy is given by a sum of the epitaxial deformation energies of pure constituents needed to bring them to a common lattice constant in the plane perpendicular to $\hat{\Phi}$. Since the epitaxial deformation energy of pure constituents is direction dependent (e.g., it is easier to stretch Cu in [100] planes than in [111] planes, see Sec. IIIB), the formation energy $H(A_1B_1)$ is also direction dependent. Therefore, $\lim_{k \rightarrow 0} J_{\text{pair}}(\mathbf{k})$ must depend on the direction of approach to the origin, proving that $J_{\text{pair}}(\mathbf{k})$ is singular. Physically, the nonanalyticity of $J_{\text{pair}}(\mathbf{k})$ is caused by long-range interactions via macroscopic elastic strain and cannot be reproduced using finite-ranged real-space pair interactions, but must be accounted for explicitly in reciprocal space. If the singularity is neglected, then as explained in Ref. 65, the cluster expansion fails not only for long-period ($n \rightarrow 1$) superlattices A_nB_n , but also for those short-period ($n > 2$) superlattices which have not been explicitly included in the constraint Eq. (2). We emphasize that although the contribution of $J_{\text{sing}}(\mathbf{k})$ to the formation energy is nonzero only in size-mismatched systems, it is not related to the atomic relaxation energy for a particular structure in any simple way (except if itself is a long-period superlattice).

The singularity in $J_{\text{pair}}(\mathbf{k})$ is similar to the singularity in the dynamical matrix $D(\mathbf{0};\mathbf{k})$ of polar crystals in the long-wavelength limit,⁸³ caused by long-range electrostatic interactions via macroscopic electric field. In lattice dynamics, $D(\mathbf{0};\mathbf{k})$ is expressed as a sum of regular and singular parts, $D(\mathbf{0};\mathbf{k}) = D^{\text{sing}}(\mathbf{0};\mathbf{k}) + D^{\text{reg}}(\mathbf{0};\mathbf{k})$, where $D^{\text{reg}}(\mathbf{0};\mathbf{k})$ (analytic as $k \rightarrow 0$) is due to short-range force constants. The singular part $D^{\text{sing}}(\mathbf{0};\mathbf{k})$ gives rise to LO/TO splitting of the zone-center optical frequencies in polar crystals, and also leads to a directional dependence of $\omega(\hat{k})$ in uniaxial crystals (e.g., CuPt-type GaInP_2). These phenomena cannot be reproduced by any set of finite-ranged microscopic force constants, but have to be calculated explicitly using the macroscopic Maxwell equations.⁸⁴

In summary, we seek to find a function $E_{\text{CE}}(;)$ which accurately reproduces the LDA total energies

$E_{\text{LDA}}[; u_{\text{min}}(;); V_{\text{min}}(;)] = E_{\text{LDA}}(;)$ at the atomically relaxed geometry and equilibrium volume of configuration $;$. The function $E_{\text{CE}}(;)$ we consider includes composition- and volume-independent interactions, so as to maintain maximum similarity with the classical Ising model. The number and type of interactions are not decided arbitrarily, but are constrained by the electronic structure theory used (here, the LDA). Relaxation is treated accurately by including long-range pair interactions in the reciprocal space representation. The $k \rightarrow 0$ singularity, affecting both short and long-period superlattices, is dealt with explicitly.

The above requirements are satisfied by the mixed space cluster expansion (MSCE):

$$H_{\text{CE}}(;) = \sum_k J_{\text{pair}}(\mathbf{k}) S(\mathbf{k};)^2 + \sum_f D_f J_f(;) + E_{\text{CS}}(;); \quad (10)$$

We have separated out the so-called equilibrium constituent strain energy term, $E_{\text{CS}}(;)$, which accounts for the $k \rightarrow 0$ singularity.⁶⁵ In Eq. (10) we do not need to calculate $E_{\text{CS}}(;)$ for each configuration $;$, but only for the directions \hat{k} of the wave vectors with nonzero $S(\mathbf{k};)$. In fact, it is constructed to coincide with the elastic strain energy of coherent superlattices in the long-period limit.⁶⁵

$$E_{\text{CS}}(;) = \sum_k J_{\text{CS}}(\mathbf{x};\hat{k}) S(\mathbf{k};)^2; \quad (11)$$

$$J_{\text{CS}}(\mathbf{x};\hat{k}) = \frac{E_{\text{CS}}^{\text{eq}}(\mathbf{x};\hat{k})}{4x(1-x)}; \quad (12)$$

where $S(\mathbf{k};)$ is the structure factor from Eq. (8). The quantity $E_{\text{CS}}^{\text{eq}}(\mathbf{x};\hat{k})$ depends only on the direction \hat{k} , and will be given in Sec. IIIB. Equation (11) is exact for long-period superlattices, but represents a choice for short-period superlattices and non-superlattice (e.g., $L1_2$) structures. It has been found⁶⁵ that the choice Eq. (11) improves the cluster expansion predictions also for short-period superlattices.

Equation (10) is a generalized Ising model description of the formation energy of any relaxed configuration $;$, even if a direct LDA calculation for this is impractical. The cluster interaction energies $fJ_{\text{pair}}(\mathbf{k})g$ and fJ_fg are obtained by fitting Eq. (10) to the LDA formation energies. An additional smoothness requirement is imposed on $J_{\text{pair}}(\mathbf{k})$, which ensures that the pair interactions are optimally short-ranged in real space. Namely, we minimize the sum

$$\begin{aligned} \chi_{\text{ms}}^2 = & \frac{1}{N} \sum_w [H_{\text{CE}}(;) - H_{\text{LDA}}(;)]^2 \\ & + \frac{t}{k} \sum_k J_{\text{pair}}(\mathbf{k}) r_k^2 =^2 J_{\text{pair}}(\mathbf{k}); \end{aligned} \quad (13)$$

TABLE II. Definition of the small-unit-cell ordered structures used in the LDA total energy calculations.

Simple superlattices					
Composition	(001)	(011)	Orientation (111)	(311)	(201)
AB	L1 ₀ (CuAu)	L1 ₀ (CuAu)	L1 ₁ (CuPt)	L1 ₁ (CuPt)	L1 ₀ (CuAu)
A ₂ B	\ 1" (MoS _{1/2})	\ 1" (MoPt _{1/2})	\ 1" (CdI ₂)	\ 1" (MoPt _{1/2})	\ 1" (MoPt _{1/2})
AB ₂	\ 2" (MoS _{1/2})	\ 2" (MoPt _{1/2})	\ 2" (CdI ₂)	\ 2" (MoPt _{1/2})	\ 2" (MoPt _{1/2})
A ₃ B	\ Z1"	\ Y1"	\ V1"	\ W1"	D ₀₂₂ (TiAl ₃)
AB ₃	\ Z3"	\ Y3"	\ V3"	\ W3"	D ₀₂₂ (TiAl ₃)
A ₂ B ₂	\ Z2"	\ Y2"	\ V2"	\ W2"	\ 40" (CuFeS ₂)
Other structures					
Composition	Name	Prototype	Superlattice direction	Period	Reference
A ₃ B ₁	L1 ₂	Cu ₃ Au	none		52
A ₁ B ₃	L1 ₂	Cu ₃ Au	none		52
A ₇ B	D7 _a		none		52
A ₄ B ₄	D4		none		52
AB ₇	D7 _b		none		52
A ₈ B		NiNb	none		95
AB ₈		NiNb	none		95
A ₆ B ₂	D ₀₂₃	Al ₃ Zr	(401)	(5,1,1,1)	95
A ₆ B ₂	LPS-3		(601)	(5,1,1,1)	87
A ₄ B ₄	SQ S8 _a		(311)	(2,3,2,1)	76
A ₄ B ₄	SQ S8 _b		(311)	(3,2,1,2)	76
A ₆ B ₂	SQ S14 _a		(201)	(6,2)	73
A ₂ B ₆	SQ S14 _b		(201)	(2,6)	73

where α and t are free parameters and β is a normalization constant.⁶⁵ Typically we choose $\beta = 4$ and $t = 1$, but the β is not sensitive to this choice.

This approach solves the four problems indicated above in the sense that (i) the fitting process itself automatically selects the pair interactions that are essential to obtain a good fit (process still does not select multibody figures), (ii) the pair interactions can be of arbitrary long range, facilitating treatment of systems with large elastic relaxations, (iii) the number of pairs can be much larger than the number of ordered structures in the fit, and (iv) the directly calculated constituent strain energy E_{CS} contains the $k \rightarrow 0$ singularity. Unlike all CPA-based methods,^{70;71} the present approach includes full account of atomic relaxation and local environment effects. Unlike the classical Ising descriptions,^{25;27;33} the interaction energies are determined by the electronic structure rather than being guessed. Finally, unlike the computational alchemy linear response approach,⁸⁵ multibody terms are included here.

Having written the expression for the total energy of arbitrary configuration, Eq. (10), we can evaluate its constants from a limited number of LDA calculations on small unit cell ($N_{\text{atoms}} < 10$) ordered structures with fully relaxed atomic positions. Equation (10) can then be employed in simulated annealing and Monte Carlo calculations^{86;87} yielding $T = 0$ ground states and $T > 0$ statistical and thermodynamic properties. Further details of the method are given in Sec. III.

III. DETAILS OF THE METHOD

A. $T = 0$ energetics

The calculations of $T = 0$ total energies employ the full-potential linearized augmented plane wave method⁸⁸ (FLAPW). The basis set consists of plane waves in the interstitial region, augmented in a continuous and differentiable way with the solutions of the radial Schrödinger equation inside the non-overlapping muffin-tin spheres. Non-spherical potential and electronic charge density terms are calculated in all space and included in the Hamiltonian matrix. Core states are treated fully relativistically and recalculated in each self-consistency iteration. The wave equation for the valence states includes all relativistic effects except the spin-orbit interaction, i.e., they are treated scalar relativistically. FLAPW is the most accurate all-electron method, superior to the methods employing overlapping atomic spheres (atomic-spheres approximation (ASA)) and/or shape approximations to the potential.

We use the Wigner exchange-correlation functional.⁸⁹ As a check, we have performed several calculations using the Perdew-Zunger⁹⁰ parametrization of the Ceperley-Alder⁹¹ functional and the generalized gradient approximation of Perdew and Wang.⁹² We find (see Sec. IV A 1) that the various exchange-correlation functionals change the enthalpies of formation of ordered Cu-Au compounds by a negligible amount (less than 2 meV/atom).

TABLE III. LDA calculated formation [Eq. (4)] enthalpies for fcc superstructures (defined in Table II) of Ag-Au, Cu-Ag, Cu-Au and Ni-Au. The numbers in parentheses represent errors of the cluster expansion fit. All energies in meV/atom.

Structure		Ag-Au	Cu-Ag		Cu-Au		Ni-Au	
Superlattice	Name	$H_{\text{unrel}}^{\text{LDA}}$	$H_{\text{unrel}}^{\text{LDA}}$	$H_{\text{rel}}^{\text{LDA}}$	$H_{\text{unrel}}^{\text{LDA}}$	$H_{\text{rel}}^{\text{LDA}}$	$H_{\text{unrel}}^{\text{LDA}}$	$H_{\text{rel}}^{\text{LDA}}$
A	fcc	0:0 (0:4)	0.0	0:0 (0:1)	0.0	0:0 (+ 0:2)	0.0	0:0 (+ 0:4)
B	fcc	0:0 (0:5)	0.0	0:0 (+ 0:3)	0.0	0:0 (0:4)	0.0	0:0 (0:2)
(001) Struct:								
A ₁ B ₁	L 1 ₀	59:7 (0:8)	+ 107:6	+ 100:5 (+ 0:4)	36:1	48:2 (+ 0:1)	+ 98:1	+ 76:1 (+ 1:4)
A ₂ B ₁	\ 1"	40:8 (0:1)	+ 130:2	+ 90:8 (0:7)	+ 51:0	3:8 (2:6)	+ 207:8	+ 105:7 (0:1)
A ₁ B ₂	\ 2"	40:0 (+ 0:1)	+ 112:0	+ 75:0 (+ 1:0)	+ 40:1	40:8 (+ 0:6)	+ 151:7	+ 38:3 (+ 0:1)
A ₃ B ₁	\ Z1"	29:2 (0:1)	+ 126:4	+ 79:8 (+ 1:8)	+ 76:5	+ 10:6 (+ 0:3)	+ 221:7	+ 89:9 (4:2)
A ₁ B ₃	\ Z3"	27:9 (+ 0:7)	+ 96:8	+ 56:9 (0:2)	+ 50:0	28:2 (+ 1:8)	+ 142:0	+ 32:4 (+ 4:0)
A ₂ B ₂	\ Z2"	28:8 (0:3)	+ 164:7	+ 77:8 (+ 0:4)	+ 136:4	6:7 (1:0)	+ 286:7	+ 70:2 (+ 0:1)
A ₂ B ₃	\ Z5"						+ 273:3	+ 57:1 (0:8)
A ₃ B ₃	\ Z6"						+ 355:5	+ 63:2 (+ 0:7)
A ₁ B ₁		0:0 (0:0)		+ 20:4 (0:0)		+ 20:3 (0:1)	+ 576:2	+ 30:8 (0:0)
(111) Struct:								
A ₁ B ₁	L 1 ₁	43:0 (0:4)	+ 134:8	+ 129:8 (1:1)	+ 60:3	+ 32:5 (0:1)	+ 192:3	+ 166:8 (+ 1:4)
A ₂ B ₁	\ 1"	30:2 (0:0)	+ 152:4	+ 120:4 (2:9)	+ 123:0	+ 61:4 (7:7)	+ 288:5	+ 202:2 (6:4)
A ₁ B ₂	\ 2"	30:8 (0:0)	+ 124:9	+ 95:0 (+ 2:9)	+ 86:4	+ 2:1 (+ 7:7)	+ 200:9	+ 100:9 (+ 6:4)
A ₃ B ₁	\ V1"	21:3 (+ 0:3)	+ 145:9	+ 108:4 (+ 0:4)	+ 136:1	+ 78:6 (+ 4:1)	+ 290:8	+ 193:7 (+ 4:1)
A ₁ B ₃	\ V3"	21:4 (+ 0:6)	+ 106:8	+ 73:6 (+ 1:5)	+ 79:5	+ 5:1 (+ 0:8)	+ 172:8	+ 83:0 (+ 4:0)
A ₂ B ₂	\ V2"	22:9 (0:4)	+ 177:1	+ 109:1 (1:0)	+ 170:6	+ 52:2 (2:5)	+ 335:8	+ 162:4 (4:1)
A ₁ B ₁		0:0 (0:0)		+ 86:3 (1:0)		+ 95:8 (+ 0:3)	+ 576:2	+ 173:8 (+ 1:3)
(011) Struct:								
A ₂ B ₁	1	49:7 (0:4)	+ 106:4	+ 100:3 (0:6)	14:2	18:4 (+ 3:3)	+ 123:3	+ 98:9 (3:8)
A ₁ B ₂	2	46:9 (+ 0:4)	+ 97:2	+ 92:5 (+ 0:8)	+ 1:7	6:7 (5:2)	+ 126:3	+ 102:6 (+ 3:8)
A ₃ B ₁	\ Y1"	37:0 (0:0)	+ 105:1	+ 85:4 (+ 3:5)	+ 21:8	1:3 (+ 3:8)	+ 148:5	+ 99:2 (+ 7:8)
A ₁ B ₃	\ Y3"	35:4 (+ 0:6)	+ 85:5	+ 75:2 (1:3)	+ 19:4	1:0 (+ 0:1)	+ 104:1	+ 78:7 (+ 1:1)
A ₂ B ₂	\ Y2"	44:1 (0:3)	+ 136:0	+ 105:7 (1:1)	+ 59:5	4:2 (2:0)	+ 192:3	+ 96:6 (4:5)
A ₁ B ₁		0:0 (0:0)		+ 75:3 (1:2)		+ 66:1 (+ 0:3)	+ 576:2	+ 117:7 (+ 1:6)
(113) Struct:								
A ₃ B ₁	\ W 1"	35:9 (+ 0:5)	+ 104:7	+ 94:2 (0:2)	+ 22:0	+ 7:0 (+ 1:5)	+ 125:7	+ 120:8 (+ 5:2)
A ₁ B ₃	\ W 3"	34:4 (0:2)	+ 98:6	+ 91:4 (+ 9:0)	+ 21:1	+ 7:8 (+ 0:6)		+ 88:4 (+ 5:3)
A ₂ B ₂	\ W 2"	50:6 (0:1)	+ 121:9	+ 104:7 (4:4)	+ 15:7	20:9 (1:0)	+ 144:2	+ 93:6 (5:3)
A ₁ B ₁		0:0 (0:0)		+ 65:9 (1:4)		+ 69:5 (+ 0:4)	+ 576:2	+ 119:8 (+ 1:9)
(201) Struct:								
A ₃ B ₁	D 0 ₂₂	42:3 (0:2)	+ 85:2	+ 85:1 (+ 1:3)	32:7	32:8 (+ 0:3)	+ 75:0	+ 75:0 (+ 5:6)
A ₁ B ₃	D 0 ₂₂	41:0 (0:3)	+ 76:8	+ 76:4 (0:5)	10:6	11:8 (1:8)	+ 68:7	+ 68:6 (+ 1:5)
A ₂ B ₂	CH, or \ 40"	55:3 (+ 0:3)	+ 109:6	+ 107:5 (0:4)	19:0	23:0 (0:6)	+ 93:5	+ 84:8 (3:6)
A ₁ B ₁		0:0 (0:0)		+ 67:3 (+ 1:6)		+ 53:4 (0:4)	+ 576:2	+ 84:8 (2:0)
(401) Struct:								
A ₅ B ₁ A ₁ B ₁	D 0 ₂₃				33:3	33:6 (0:0)		
(601) Struct:								
A ₅ B ₁ A ₁ B ₁	LPS 3				34:1			
Other Struct:								
A ₃ B ₁	L 1 ₂	43:4 (+ 0:4)	+ 84:8	+ 84:8 (1:4)	37:3	37:3 (0:1)	+ 77:5	+ 77:5 (2:7)
A ₁ B ₃	L 1 ₂	44:0 (+ 0:3)	+ 76:0	+ 76:0 (+ 1:8)	17:3	17:3 (0:8)	+ 78:9	+ 78:9 (0:2)
A ₇ B ₁	D 7	20:8 (+ 0:6)	+ 61:9	+ 61:9 (3:1)	+ 6:8	+ 6:8 (8:3)	+ 82:9	+ 82:9 (15:8)
A ₄ B ₄	D 4	42:9 (+ 1:1)						
A ₁ B ₇	D 7 _b	20:0 (0:1)	+ 47:1	+ 47:1 (3:3)	+ 12:9	+ 12:9 (+ 1:9)	+ 56:8	+ 56:8 (0:7)
A ₈ B ₁	N i ₈ Nb-type		+ 63:7	+ 47:7 (+ 0:4)	+ 9:3	9:1 (4:5)		
A ₁ B ₈	N i ₈ Nb-type		+ 42:7	+ 36:4 (1:7)	+ 30:9	+ 18:2 (+ 13:3)		
Random:								
A ₄ B ₄	SQ S8 _a	42:5 (+ 0:2)				+ 12:9 (+ 5:7)		+ 122:6 (+ 1:2)
A ₄ B ₄	SQ S8 _b	43:6 (0:2)				15:2 (5:7)		+ 97:5 (9:7)
A ₃ B ₁	SQ S14 _a		+ 116:2	+ 77:3 (+ 7:0)	+ 56:5	+ 5:5 (+ 7:7)	+ 183:2	+ 96:8 (+ 15:3)
A ₁ B ₃	SQ S14 _b		+ 92:2	+ 69:7 (7:0)	+ 37:8	5:2 (7:7)	+ 118:2	+ 59:8 (15:3)

The total energies of the ordered structures and end-point constituents are obtained keeping all computational parameters exactly equal. Specifically, we always use the same basis sets ($R_{K_{max}} = 9$), charge density cut-offs ($R_{K_{max}} = 19$), muffin-tin radii $R_{Au} = 2.4a_0$, $R_{Ag} = R_{Cu} = R_{Ni} = 2.2a_0$, maximum difference in the angular momenta in the nonspherical Hamiltonian terms ($l_{max} = 4$), maximum angular momenta in the nonspherical charge densities and potentials inside the muffin-tin spheres ($l_{max} = 8$), and equivalent k point sets⁹³ in the evaluation of Brillouin zone integrals. When the unit cell vectors of the ordered compound permit, we choose a k mesh equivalent to the 60 special points $8 \times 8 \times 8$ for mesh. Several structures (e.g., those of A_2B or AB_2 stoichiometry) have reciprocal unit cell vectors which are incommensurate with the $8 \times 8 \times 8$ mesh. In these cases we calculate the total energies of the compounds and fcc constituents with a finer k point grid. This procedure ensures that, due to systematic cancellation of errors, the formation enthalpies H_f , Eq. (4), converge much faster than the total energies. Indeed, the tests for Cu-Au described in Sec. IV A 1 show that with our choice of parameters H_f are converged to within 2 meV/atom.

The atomic positions are relaxed using quantum mechanical forces⁹⁴ obtained at the end of the self-consistency iterations. Minimization of the total energy with respect to the cell-external degrees of freedom is done by distorting the shape of the unit cell and tracing the decrease in the total energy. We estimate that the formation enthalpies are converged to at least 5 meV/atom with respect to all relaxational degrees of freedom.

Table II and its caption describes our small-unit-cell ordered structures. Many are actually superlattices along (100), (110), (111), (201) and (311) directions. Table III gives the calculated LDA formation energies [Eq. (4)] for these Au-Ag, Cu-Au, Cu-Ag and Ni-Au compounds.

B. The constituent strain energy

It is well known⁶⁶ that real-space cluster expansions with finite-ranged interactions incorrectly predict zero formation enthalpies per atom for coherent long-period A_pB_q superlattices, while the correct answers are non-zero and depend on the superlattice direction Φ . The constituent strain energy term $E_{CS}(\Phi)$ in Eq. (10) is specifically designed to reproduce these superlattice energies, which are calculated directly from the LDA as follows.

In the long-period limit $p, q \rightarrow 1$ the interfacial energy becomes negligibly small ($O(1/p)$) in comparison with the elastic strain energy needed to deform the constituents to a common in-plane lattice constant a_s .^{55;96} Therefore, the formation energy per atom of A_1B_1 superlattice along Φ with composition x is given by the constituent strain energy $E_{CS}(x; \Phi)$, defined as the equilibrium (eq) value of the composition-weighted sum of the

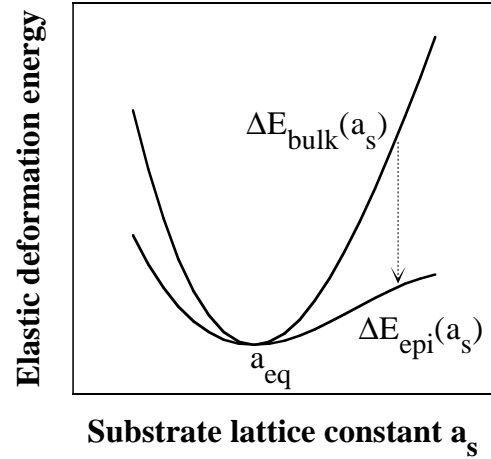


FIG. 1. A schematic illustration of the concept of the epitaxial softening function $q(\Phi)$, given by the ratio of the bulk (upper curve) and epitaxial (lower curve) deformation energies. In the harmonic approximation $q(\Phi)$ is the ratio of the curvatures of these curves at the equilibrium point.

energies required to deform bulk A and B to the epitaxial geometry with a planar lattice constant a_s :

$$E_{CS}^{eq}(x; \Phi) = \min_{a_s} \left[x E_A^{epi}(a_s; \Phi) + (1-x) E_B^{epi}(a_s; \Phi) \right] \quad (14)$$

Here $E^{epi}(a_s; \Phi)$ is the strain energy of the material epitaxially stretched to the lattice constant a_s in the direction orthogonal to Φ , and then allowed to relax along Φ . $E^{epi}(a_s; \Phi)$ is related to the bulk equation of state $E^{bulk}(a_s)$ via the epitaxial softening function $q(a_s; \Phi)$:

$$q(a_s; \Phi) = \frac{E^{epi}(a_s; \Phi)}{E^{bulk}(a_s)}; \quad (15)$$

where $E_A^{bulk}(a_s)$ is the energy required to hydrostatically deform a bulk solid to the lattice constant a_s . Figure 1 illustrates the concept of epitaxial softening:⁹⁷ when the bulk solid is deformed hydrostatically from a_{eq} to $a_s \neq a_{eq}$, its energy rises. Energy can then be lowered if we keep $a_x = a_y = a_s$ but relax the third lattice vector to its equilibrium value. $q(a_s; \Phi)$ measures the relative energy lowering.

Figure 2 shows the calculated LDA q 's for Cu, obtained by minimizing the total energy with respect to the lattice constant c parallel to Φ for each value of the substrate lattice parameter a_s . As explained in Ref. 96, this treatment neglects the so-called shear strain terms, but is exact for the high symmetry directions (100), (111) and (110). The calculated $q_{Cu}(a_s; \Phi)$ is seen to be a nontrivial function of the substrate lattice parameter a_s and direction Φ . In contrast, the harmonic elasticity theory,^{97,100}

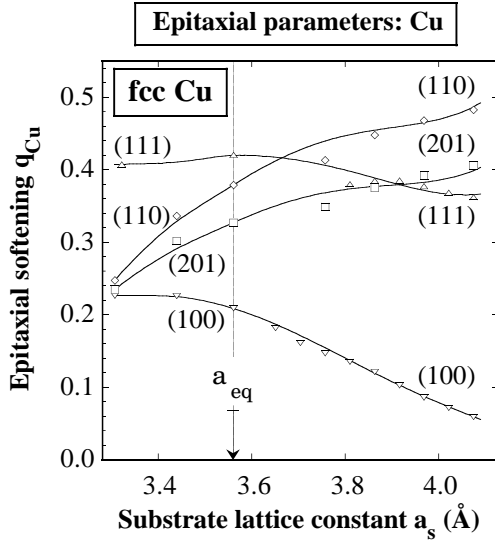


FIG. 2. $q(\phi)$ of fcc Cu for principle directions as functions of the substrate lattice parameter a_s . Directly calculated LDA values are represented by open symbols, lines show the fit using the expansion of $q(\phi)$ in Kubic harmonics.

routinely used for semiconductor system s ,^{97;100;101} gives q 's which do not depend on a_s :

$$q_{\text{ham}}(\phi) = 1 - \frac{B}{C_{11} + q_{\text{ham}}(\phi)}; \quad (16)$$

where $q_{\text{ham}}(\phi)$ is a geometric function of the spherical angles formed by ϕ :

$$q_{\text{ham}}(\phi) = \sin^2(2\phi) + \sin^4(\phi) \sin^2(\phi) = \frac{4p}{5} - \frac{4}{5} [K_0(\phi) - \frac{2}{21} K_4(\phi)]; \quad (17)$$

and K_l are the Kubic harmonics of angular momentum l . Figure 2 shows that the harmonic approximation manifestly breaks down for large epitaxial strains in metals since there are several important qualitative differences between the behavior in Fig. 2 and that predicted by the harmonic elasticity. First, $q(a_s; \phi)$ strongly depends on the substrate lattice constant, while the harmonic $q_{\text{ham}}(\phi)$ does not. Second, the harmonic expression gives a definite order of $q(\phi)$ as a function of the direction, i.e., either (100) is the softest and then (111) must be the hardest, or vice versa. This order does not hold for large deformations. For instance, (201) becomes the softest direction for $a_s > a_0$ and (110) is the hardest for $a_s < a_0$ in Cu. Finally, $q(100)$ exhibits a particularly dramatic softening for $a_s > a_0$, which has important consequences for the constituent strain energy and stability of superlattices along this direction.⁹⁶

The above mentioned properties of q_{Cu} can be described by generalizing Eq. (17) for q to higher Kubic harmonics and strain-dependent expansion coefficients:

$$q_s(\phi) = \sum_{l=0}^{l_{\text{max}}} b_l(a_s) K_l(\phi); \quad (18)$$

which has the property that in the harmonic limit ($a_s \rightarrow a_0$) all expansion coefficients with angular momentum higher than 4 tend to zero, reproducing q_{ham} from Eq. (17). Due to the cubic symmetry, only terms with $l = 0; 4; 6; 8; 10; 12; \dots$ enter in this expansion. Detailed discussion of the nonlinear epitaxial strain properties of elemental metals will be given in a separate publication.⁹⁶

The constituent strain energy $E_{\text{CS}}^{\text{eq}}(x; \phi)$ is calculated numerically from Eq. (14) using the direct LDA values of $E^{\text{epi}}(a_s; \phi)$ for six principle directions. The obtained $E_{\text{CS}}^{\text{eq}}$ for these directions are shown in Fig. 3, illustrating several properties of the constituent strain which cannot be reproduced by the harmonic theory.⁶⁵ First, the curves in Fig. 3 are skewed to different sides, while the harmonic $E_{\text{CS}}^{\text{eq}}$ must be all skewed to the same side. Second, the calculated $E_{\text{CS}}^{\text{eq}}$ cross for different directions, a property not allowed by the harmonic functional form. These crossings lead to (201) as the softest direction below $x \approx 0.2$, and (110) as the hardest for Au-rich superlattices, while the harmonic theory gives $E_{\text{CS}}^{\text{eq}}(111)$ as the highest and $E_{\text{CS}}^{\text{eq}}(100)$ as the lowest constituent strain for all compositions of the studied noble metal alloys. The behavior of $E_{\text{CS}}^{\text{eq}}$ for (100) is particularly interesting, since the curves in Fig. 3 abruptly change slope around $x \approx 0.15$ and have very low values for $x > \frac{1}{4}$. As we show in Ref. 96, this is a manifestation of the low energy cost of deforming fcc Cu into the body-centered tetragonal structure along the epitaxial Bain path. Small constituent strain of (100) superlattices has profound influence on the predicted ground states of Cu-Au (see Sec. IV A 1).

The constituent strain energy for arbitrary direction ϕ is then obtained by interpolating between the principle directions using the following expansion in Kubic harmonics:

$$E_{\text{CS}}(x; \phi) = \sum_{l=0}^{l_{\text{max}}} c_l(x) K_l(\phi); \quad (19)$$

We have taken $l_{\text{max}} = 10$, which gives very composition-dependent fitting coefficients determined from a fit to the directly calculated values [Eq. (14)] for six principle directions. The characteristic errors of this fit at the equiatomic composition are $1 - 2$ meV/atom. Equation (19) is then used in Eqs. (11)-(12).

C. Constructing the Cluster Expansion

Once we have a closed-form expression for the equilibrium constituent strain energy $E_{\text{CS}}(\phi)$ and a set of $H^{\text{LDA}}(\phi)$ of $T = 0$ formation enthalpies, we determine the unknown cluster interactions of Eq. (10) in the following two-step process:

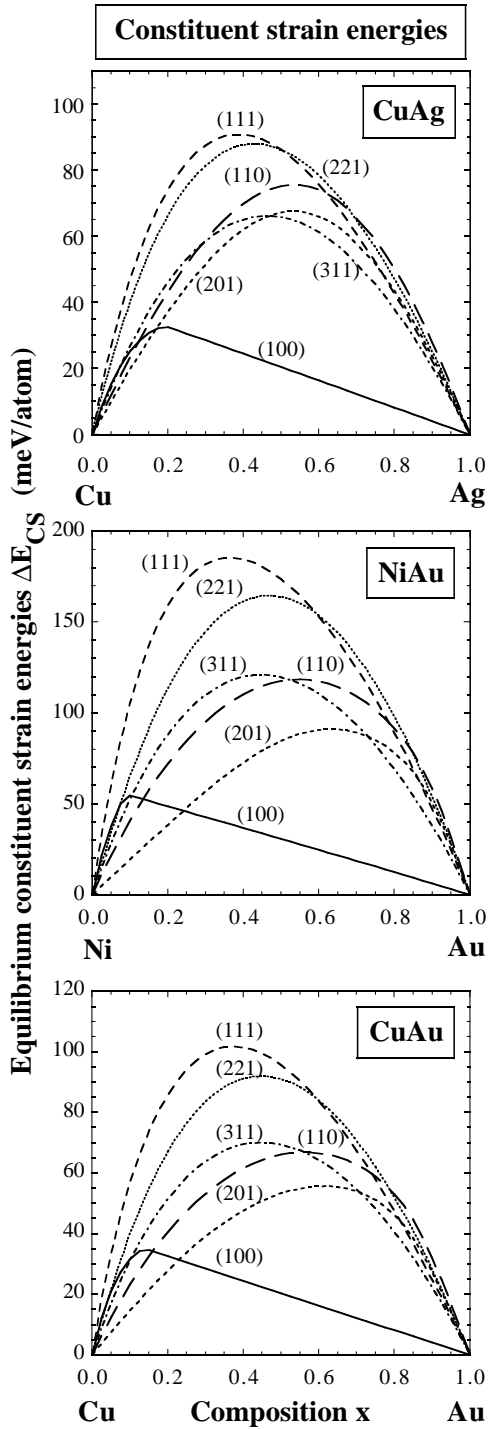


FIG. 3. Equilibrium constituent strain energies for Cu-Au, Ni-Au and Cu-Ag. The constituent strain energy of Ag-Au is negligibly small and therefore not shown.

First, the total energies of all structures from Table III are used in the fit to investigate the behavior of the root-mean-square (rms) error ϵ_{rms} of the fit, Eq. (13), as a function of the number of real-space pair and multibody interactions. Reciprocal space CE allows to add pair interactions systematically in the order of increasing intersite separation, up to any number of near-neighbor shells. The k-space smoothness criterion in Eq. (13) automatically selects optimally short-ranged interactions and chooses physically important pair interactions which are essential to produce a good fit to the directly calculated LDA energies. The dependence of the rms error on the number of pair and multibody interactions is shown in Fig. 4. Figure 4(a) is obtained by fixing the number of multibody interactions, and varying the number of pair interactions. It shows that in all systems the cluster expansion is well converged using 10 to 20 pair interactions. The convergence rate is fastest for Ag-Au and slowest for Ni-Au, which we attribute to increasing size mismatch going from Ag-Au to Ni-Au, with Cu-Ag and Cu-Au exhibiting intermediate convergence rates.

Selection of important multibody interactions is more delicate. The number of pair interactions is fixed to a converged value (20 or more), and a large set of 3- to 4-body figures is tested as to whether it improves the rms error of the overall fit. It is retained in the CE only if ϵ_{rms} decreases considerably. During the fitting process, we also monitor the overall stability of the CE, as measured by a change in other multibody interactions upon the addition of a particular figure. Unstable behavior usually signals of linear dependencies in the chosen set of clusters and an ill-conditioned inverse problem, necessitating a different choice of $\{J_{\mathbf{f}}\}$. Figure 4(b) shows the convergence of the CE with respect to the number of multibody interactions, keeping N_{pairs} equal to their converged values. An important thing to notice is that the multibody interactions produce a decrease in the rms error which is of the same magnitude as that due to the pair interactions. Furthermore, the effect of multibody interactions is largest in Ni-Au, and decreases in order of decreasing size mismatch, becoming negligible in Ag-Au.

In the second step we test the stability of the fit and its predictive power. Using the trial set of figures obtained in the previous step, we exclude several structures which are fit rather well (e.g., Z_2 , Z_2 , and L_{12} in Ni-Au), and repeat the fit, obtaining new values of the effective cluster interactions. These values are used to predict the total energies of the structures excluded from the fit. If the change in $H_{\text{CE}}(\cdot)$ is not acceptable (more than few meV/atom), we return to the first step to search for a better set of interactions. The most severe test is to exclude structures with the poorest fit to their formation enthalpies, e.g., $SQS14_a$ and $SQS14_b$ in Ni-Au. If the predicted formation energy does not change significantly, the chosen set of figures is considered to be stable and predictive. The final cluster expansion is produced by using this set of figures and all structures from Table III.

Figure 5 shows the calculated pair interactions as func-

Convergence of Cluster Expansion

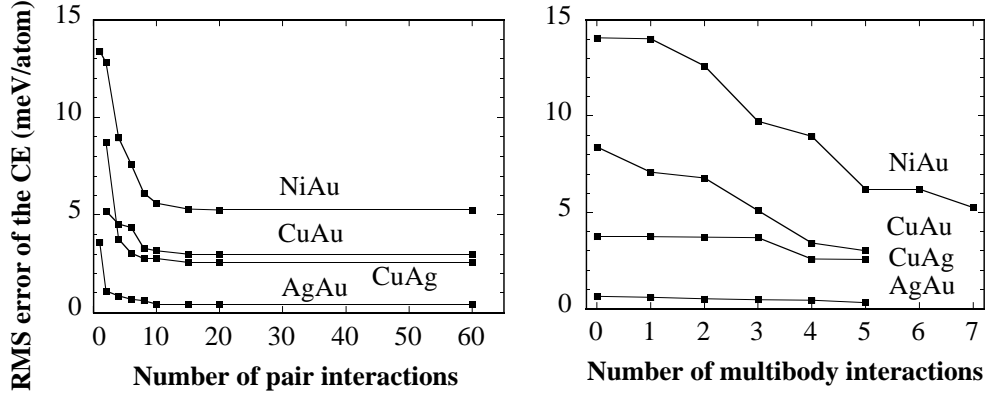


FIG. 4. Root-mean-square errors of the cluster expansions for Ag-Au, Cu-Ag, Cu-Au and Ni-Au as functions of the number of pair and multibody interactions.

tion of the near-neighbor fcc shell. There are several noteworthy trends in the four alloy systems:

(i) Only in Ag-Au and Cu-Au are the nearest-neighbor pair interactions dominant: in Cu-Ag the 1-st and 3-rd neighbor pair interactions are of similar magnitude, while the 3-rd neighbor interaction dominates in Ni-Au.

(ii) The dominant interactions have signs consistent with the observed phase diagrams: Ag-Au and Cu-Au have positive ("antiferromagnetic") nearest-neighbor pair interactions J_2 , corresponding to the tendency towards complete miscibility and ordering at low temperatures. The behavior of Ni-Au, in spite of positive 1-st and 2-nd neighbor pair interactions, is dominated by the "ferromagnetic" 3-rd neighbor interaction L_2 (which causes phase separation at low temperatures). Both dominant 1-st and 3-rd neighbor pair interactions in Cu-Ag are negative, implying a miscibility gap. The constituent strain energy E_{CS}^{eq} is always positive and therefore increases the propensity for incoherent phase separation.

(iii) Although the nearest-neighbor pair interaction is clearly dominant in Cu-Au, other pair interactions show a long-ranged oscillatory behavior extending over approximately 15 shells. As found in other systems,^{65,85} this is a direct consequence of the atomic relaxation caused by the constituent size mismatch between Cu and Au. The pair interactions are slowly decaying in Cu-Ag and Ni-Au, too.

The calculated multibody interaction energies are shown in Figure 6. J_1 is the point interaction, J_3, K_3, N_3, \dots are triplets and J_4, K_4 , and L_4 are four-point clusters in increasing order of interatomic separation (see Lu et al.⁵⁴ for a full description of the clusters). Figure 6 illustrates the importance of the multibody terms in our Hamiltonian.

D. Finding the $T = 0$ ground states and $T > 0$ properties

Having parametrized the configurational energies in terms of the mixed-space cluster expansion Eq. (10), we can use it with established statistical methods to predict various structural properties: $T = 0$ ground states, order-disorder transition temperatures, configurational entropies, free energies, phase stabilities and atomic short-range order parameters. Due to the presence of both reciprocal and real space terms in the Hamiltonian (10), traditional techniques, e.g., the Cluster Variation Method, are not readily applicable. Monte Carlo simulations must be used instead to calculate statistical properties at finite temperatures. The basic computational algorithm is as follows. We adopt the Metropolis algorithm in the canonical ensemble (fixed composition). For each attempted spin flip, the change in the multiplet interaction energy is evaluated in the real space. To obtain the reciprocal space energy (constituent strain and pair interaction energies), the Fourier transform of the spin function $S(\mathbf{R}_i; \sigma_i)$ is needed. It can be calculated either with the help of the Fast Fourier Transform (FFT) or evaluated directly taking advantage of the special method described in Ref. 87, which is much more economical: if the total number of sites in the simulation box is N , a full FFT has to be done only once after approximately every N accepted spin flips, which makes the whole computational effort for this special method scale as $N^{1.5}$.

A simulation box of $N = 4096$ atoms ($16 \times 16 \times 16$) is used to calculate all thermodynamic properties presented in this paper. The transition temperatures are computed by cooling the system from high temperatures and monitoring the discontinuities in the average energy and peaks in heat capacity. To eliminate possible hysteresis effects, the resulting low-temperature configurations are gradually heated up past the transition point. The former

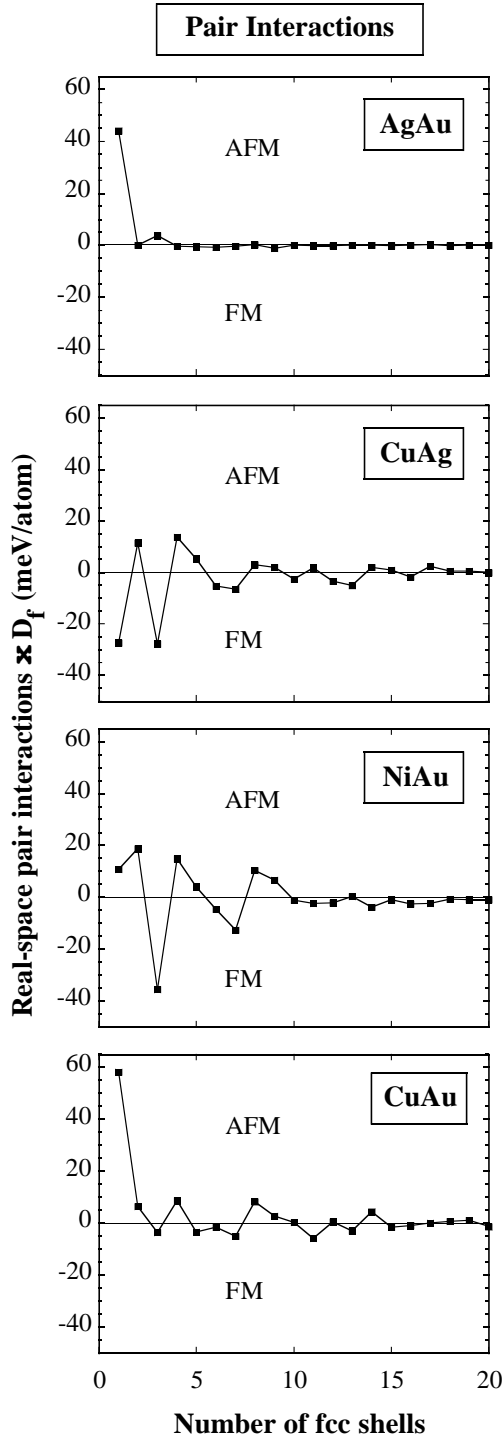


FIG. 5. Real space pair interactions for the studied noble metal alloy systems.

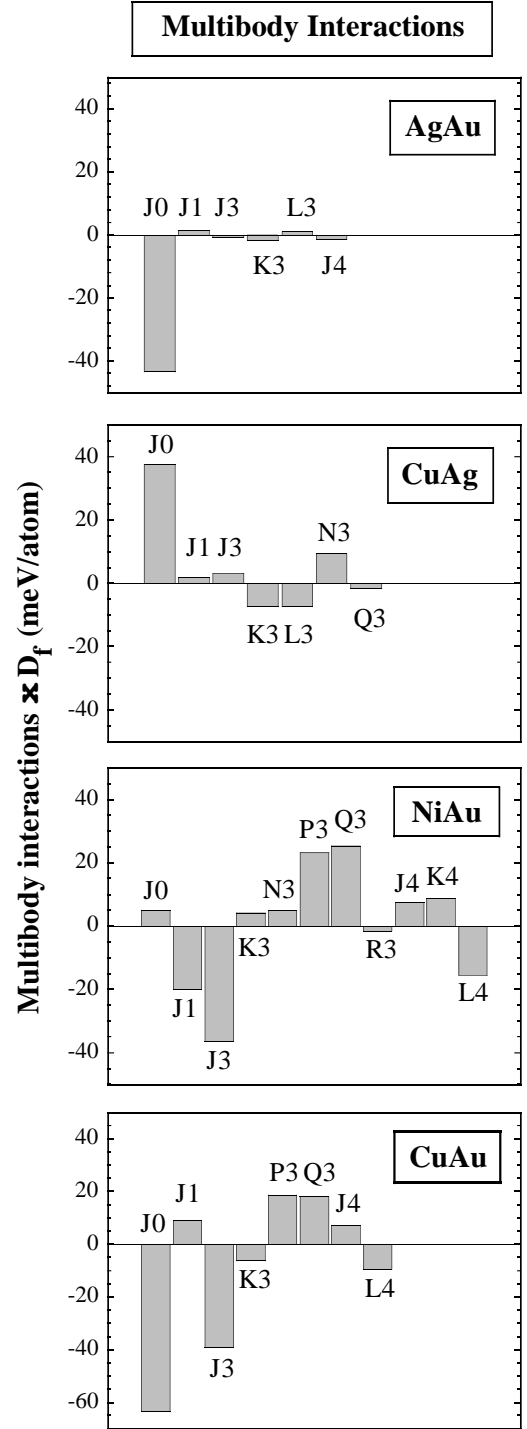


FIG. 6. Multibody interactions for the studied noble metal alloy systems.

process provides the lower bound on the transition temperature, T_1 , while the latter gives the upper bound, T_2 . The heating and cooling rates are such that T_1 and T_2 differ by no more than 20K, an insignificant uncertainty compared to the inaccuracies of the LDA calculations and the errors of the cluster expansion. 1000 ips/site and a temperature decrease of 2% for each Monte Carlo step are usually sufficient, although in a few cases the results are checked using 2000 ips/site and 0.5% temperature change.

Zero temperature ground states are found by cooling the system to $T = 0$ and checking whether the energy of the final configuration lies on the convex hull. This process is repeated for several random number seeds and starting temperatures, always yielding configurations with similar (usually identical) energies. We explore many equally spaced compositions with an interval $x = 0.05$. The number of possible configurations for each x is $N_{\text{conf}} = \frac{N!}{(xN)!(N(1-x))!}$.

Configurational entropy of the disordered alloys at finite T is computed from the energy vs. temperature curves obtained by cooling the system from very high ($T = 1000$) temperatures. The following thermodynamic formula gives the configurational entropy at temperature T :

$$S_{\text{conf}}(T) = S_{\text{ideal}} + E(T) - T \int_0^T \frac{E(T')}{T'^2} dT'; \quad (20)$$

where $k_B = 1$ and $S_{\text{ideal}} = -k_B [x \log x + (1-x) \log(1-x)]$ is the configurational entropy of an ideal solid solution.

IV. RESULTS

A. $T = 0$ G round States

1. Ground states of Cu-Au

Figure 7 shows the calculated $T = 0$ ground state lines of Cu-Au and Ag-Au which were obtained from simulated annealing quenches of a $16 \times 16 \times 16$ system. In Cu-Au, we find the $L1_2$ (Cu_3Au) and $L1_0$ (CuAu) structures as the stable ground states of Cu-rich alloys, in agreement with the existing phase diagram data.^{1,4} These data also list $L1_2$ as the stable low-temperature phase of $\text{CuAu}_{1/3}$. However, we find new, previously unsuspected ground states of Au-rich compounds, all belonging to the family of (001) superlattices. At $x = \frac{2}{3}$ we find a stable 2×2 (CuAu_2) phase (prototype MoSi_2), which is a Cu_1Au_2 superlattice along (001). At $x = \frac{3}{4}$, our cluster expansion predicts that a complex $\text{Cu}_1\text{Au}_4\text{Cu}_1\text{Au}_4\text{Cu}_1\text{Au}_2\text{Cu}_1\text{Au}_2$ (001) superlattice falls on the convex hull, although its energy is less than 2 meV below the tie line connecting 2×2 (CuAu_2) and Au. Furthermore, even the directly

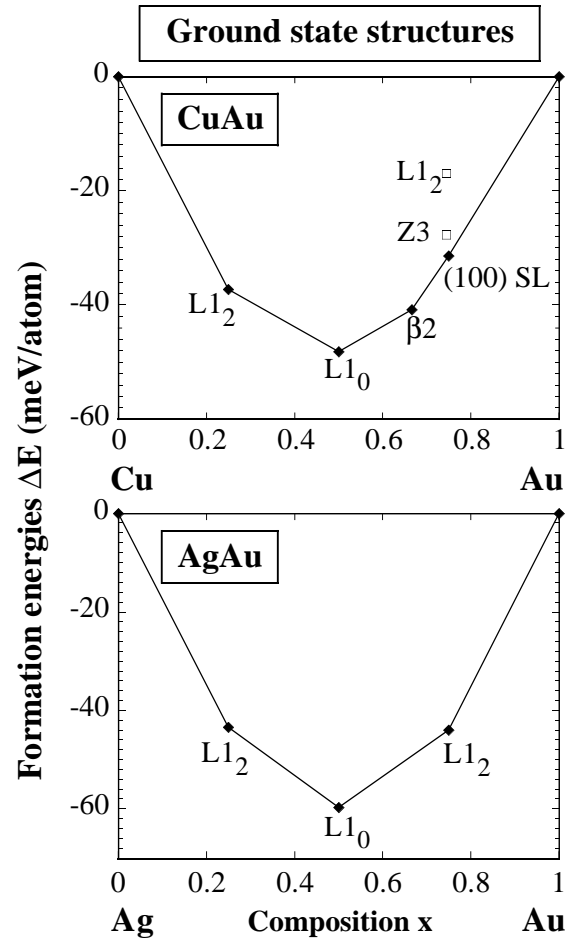


FIG. 7. $T = 0$ K ground state lines for Cu-Au and Ag-Au obtained from simulated annealing calculations. $L1_2$ $\text{CuAu}_{1/3}$ is not only above the ground state line, but also has a higher formation enthalpy than other structures at the same composition, e.g. LDA calculations place the formation enthalpy of $Z3$ below that of $L1_2$. Plots for Cu-Ag and Ni-Au are not shown since these systems phase separate at $T = 0$ K.

calculated LDA enthalpy of formation of $Z3$ (which is a Cu_1Au_3 (001) superlattice) is considerably lower than that of $L1_2$ $\text{CuAu}_{1/3}$.

We carefully checked whether the predicted new LDA ground states for Au-rich Cu-Au alloys artifacts of some approximation in our LDA calculations or the error of the cluster expansion. The latter possibility was quickly dismissed, since the directly calculated LDA enthalpies of formation for $L1_0$, 2×2 , $L1_2$ and $Z3$ agreed with the values derived from the cluster expansion to better than 2 meV/atom (see Table III), while the new (100) SL ground state is 14 meV/atom below $L1_2$. To address the former possibility, we performed careful convergence tests for $L1_0$, 2×2 , $L1_2$ and $Z3$ with respect to the plane wave cutoff and number of k points in the first Brillouin zone. The cutoff was increased from $RK_{\text{max}} = 9$ to $RK_{\text{max}} = 11$ and the density of the Brillouin zone

mesh was doubled from $8 \times 8 \times 8$ to $16 \times 16 \times 16$, an eightfold increase in the total number of k points. These tests showed that the formation enthalpies of $L1_0$, $L1_2$ and $L1_2$ were converged to within 1 meV/atom with respect to the size of the basis set and the number of k points. Further, we checked how the choice of muffin-tin radii affected H . Varying $R_{MT}(\text{Au})$ between $2.3a_0$ and $2.5a_0$ changed the formation enthalpies by at most 2 meV/atom and did not shift the relative stabilities of phases. Finally, we repeated these calculations using the Perdew-Zunger⁹⁰ parametrization of the Ceperley-Alder⁹¹ LDA functional, as well as the generalized gradient approximation (GGA) of Perdew and Wang,⁹² and found insignificant (about 2 meV/atom) changes in the formation enthalpies. Inclusion of the spin-orbit interaction in the second variation procedure¹⁰⁴ changed the formation enthalpy of $L1_0$ (CuAu) by only 3.7 meV/atom (from 48.2 to 51.9), indicating that it is not important for the energetics of Cu-Au. This conclusion is in line with the findings of Ref. 105 that the spin-orbit interaction influences the band structure but has little effect on equilibrium lattice properties. Therefore, we conclude that state-of-the-art first-principles density functional calculations do not predict $L1_2$ to be a stable $T = 0$ ground state of CuAu_3 . It is possible that van der Waals interactions, omitted by the LDA and important for large, polarizable atoms such as Au, can affect the formation energies and hence the ground states of Cu-Au.

We next analyze the possibility that the correct $T = 0$ ground state around $x = \frac{3}{4}$ is not $L1_2$ as has been assumed in the literature before. Although most compilations¹⁴ of binary alloy phase diagrams give $L1_2$ as the stable structure of CuAu_3 , the experimental evidence^{7;8;10} seems inconclusive because of the difficulties in obtaining equilibrated long-range ordered samples. X-ray studies⁸ have found superlattice peaks consistent with the cubic $L1_2$ structure, but only very broad low-order reflections have been observed. These superlattice lines could not be sharpened by any heat treatment.⁸ It is not clear to us if the X-ray reflections can be reindexed according to some other non- $L1_2$ phase. It is also possible that at elevated ($T \sim 500$ K) temperatures $L1_2$ is stabilized by the entropy (conformational and vibrational), while another transformation to the low-energy structure should occur but is kinetically inhibited below 500 K. The biggest experimental obstacles to verifying our predictions seem to be low diffusion rates below the ordering temperature of CuAu_3 , $T_c \sim 500$ K.

Next we discuss the experimental signatures of the new LDA ground state structures. MoSb_2 -type $\sqrt{2} \times \sqrt{2} \times \sqrt{2}$ CuAu_2 has a superlattice reflection at $(\frac{2}{3}00)$, but CuAu_3 (100) superlattice has reflections at (100) and $(\frac{1}{3}00)$. These reflections also manifest themselves in the predicted atomic short-range order of the disordered alloys (for details see Ref. 103).

2. Ground states of Ag-Au, Cu-Ag and Ni-Au

The ground state line of Ag-Au is shown in Figure 7(b), exhibiting $L1_2$ (Ag_3Au), $L1_0$ (AgAu) and $L1_2$ (AgAu_3) stable low-temperature phases. Experimentally, these alloys are known to be completely miscible,²⁴ and there are several indications⁶⁹ that they would order below 200 K if not for the very low diffusion rates. Theoretical transition temperatures and short-range order patterns, as well as a complete discussion are given by Lu and Zunger.⁵⁴

The calculated ground states of Cu-Ag and Ni-Au are found to be phase separation, in agreement with the experimental enthalpy data.² Neither alloy has a single ordered or disordered structure with negative enthalpy of formation and therefore there are no stable $T = 0$ ground states except the phase-separated alloy.

B. Mixing enthalpies

It is interesting to compare the calculated mixing enthalpies of disordered Cu-Au alloys with the available theoretical and experimental data. Table IV summarizes the values of $H_{mix}(x;T)$ for the completely random ($T = 1$), short-range ordered ($T = 800$ K) and completely ordered ($T = 0$ K) Cu-Au alloys at compositions $x = \frac{1}{4}, \frac{1}{2}$ and $\frac{3}{4}$. Several important points are apparent from this table:

(i) Studies^{50;48;62} which have completely neglected atomic relaxations predict a substantially positive enthalpy of formation for the completely random alloy. In our calculations, relaxations in the random alloy reduce $H_{mix}(T = 1)$ by a large amount, bringing it down to essentially zero.

(ii) Comparison of the present results for the $T = 1$ random alloys with those of Wei et al.⁵¹ shows the influence of the number of structures included in the cluster expansion. Since Wei et al. used the same FLAPW method⁸⁸, but included a set of only five high-symmetry ordered structures [$A1(\text{Cu})$, $L1_2(\text{Cu}_3\text{Au})$, $L1_0(\text{CuAu})$, $L1_2(\text{CuAu}_3)$ and $A1(\text{Au})$], the atomic relaxation effects were included incompletely. Indeed, their treatment gives much larger mixing enthalpies of the random Cu-Au alloys than the present work employing approximately 30 low-symmetry structures with large relaxations. Therefore we conclude that the Connolly-William's set of ordered structures cannot correctly capture the large decrease of the mixing enthalpy of random Cu-Au alloys caused by the atomic relaxations.

(iii) The good agreement between the relaxed (this study) and "unrelaxed" (Wei et al.⁵¹) values of H_{mix} at $T = 800$ K suggests that the short-range order in Cu-Au tends to decrease the role of the atomic relaxations. This effect can be qualitatively explained on the basis of the ordering tendency towards high-symmetry structures

TABLE IV . Calculated mixing enthalpies of disordered $\text{Cu}_{1-x}\text{Au}_x$ alloys compared with the values obtained by other studies and experimental measurements (in meV/atom). FLAPW is the full-potential linearized augmented plane wave method, LMTO { linearized muffin-tin-orbitals method, KKR { Korringa-Kohn-Rostoker multiple scattering method, ASA { atom-sphere approximation, CPA { coherent potential approximation, CW M - Connolly-Williams cluster expansion, MSCE { mixed-space cluster expansion used in this study, \Rel. { incorporating atomic relaxations, and \Unrel. { neglecting atomic relaxations.

Composition	Expt. ^f	This study FLAPW MSCE (Rel.)	Weinberger et al. ^a FLAPW CW M (Rel.)	Amador et al. ^b LMTO-ASA CW M (Unrel.)	Terakura et al. ^c ASW CW M (Unrel.)	Ruban et al. ^d LMTO-ASA CPA (Unrel.)	Weinberger et al. ^e KKR-ASA CPA (Unrel.)
$H_{\text{mix}}(T = 1)$							
$\text{Cu}_{0.75}\text{Au}_{0.25}$		+ 2:6	+ 46:3	+ 59	+ 26:9	+ 54:6	27
$\text{Cu}_{0.50}\text{Au}_{0.50}$		+ 1:6	+ 38:0	+ 61	+ 30:4	+ 44:3	57
$\text{Cu}_{0.25}\text{Au}_{0.75}$		+ 5:4	+ 18:6	+ 39	+ 20:4	+ 19:8	31
$H_{\text{mix}}(T = 800 \text{ K})$							
$\text{Cu}_{0.75}\text{Au}_{0.25}$	46 ^g	17:3		6			
$\text{Cu}_{0.50}\text{Au}_{0.50}$	53 ^g	19:3	16:9	5			
$\text{Cu}_{0.25}\text{Au}_{0.75}$	31 ^g	1:2	2:6	+ 8			
$H_{\text{mix}}(T = 0 \text{ K})$							
$\text{L}_{12} \text{ Cu}_3\text{Au}$	74	37:3	36:0		65:0	60:7	54
$\text{L}_{10} \text{ CuAu}$	91	48:2	62:9		69:7	83:4	76
$\text{L}_{12} \text{ CuAu}_3$	59	17:3	26:4		34:0	56:1	47

^aRef. 51 using the Connolly-Williams structures (relaxation of L_{10} only).

^bRef. 50.

^cRef. 48.

^dRef. 62.

^eRef. 58.

^fRef. 2.

^gValues obtained at $T = 720 \text{ K}$.

which have little or no relaxation energy (L_{12} and L_{10} in Cu-rich alloys).

(iv) The mixing enthalpies of the random alloy calculated by Weinberger et al.⁵⁸ using the coherent-potential approximation (CPA) differ strongly not only from those obtained using the cluster expansion methods,^{51;50;48} but also from the numbers given in the CPA work of Ruban, Abrikosov, and Skriver.⁶² Since the CPA of Weinberger et al.⁵⁸ neglects the (a) atomic relaxation, (b) charge transfer and (c) short-range order, which all lower the formation energies, the negative values obtained by Weinberger et al.⁵⁸ are very puzzling.

(v) There are significant discrepancies between the best calculated and experimentally measured^{15;14;2} values of H_{mix} at both $T = 0 \text{ K}$ and $T = 800 \text{ K}$. At present these discrepancies are hard to explain since the available general potential LDA calculations^{51;52;57} of $H(\text{L}_{12})$ and $H(\text{L}_{10})$ agree with each other reasonably well. On the other hand, formation energies in Cu-Au are numerically very small and present a severe test for any first-principles model of electronic exchange-correlation. It is noteworthy that several less accurate first-principles calculations, using the atom-sphere approximation (ASA), have achieved better agreement with the experimental enthalpies of formation than the state of the art general potential techniques. We consider this to be fortuitous. In all cases, LDA calculations correctly predict the relative magnitudes of H for L_{12} and L_{10} , as well as reproduce measured asymmetry in formation enthalpies towards more negative values of H_{mix} for Cu-rich al-

loys.

C. Order-disorder transition temperatures

Order-disorder transitions have been investigated at compositions ($x = \frac{1}{4}, \frac{1}{2}, \frac{2}{3}$ and $\frac{3}{4}$) using the Monte Carlo simulation technique described in Sec. IIID. The resulting transition temperatures, T_c , are given in Table V. All transitions are found to be first order, involving discontinuities in the energy and correlation functions. At $x = \frac{1}{4}$ we find a transition from the disordered state to long-range ordered $\text{L}_{12} \text{ Cu}_3\text{Au}$ at $T_c = 530 \text{ K}$, which is only 130 K lower than the experimentally observed transition temperature. For the equiatomic alloy at $x = \frac{1}{2}$ the calculated and experimental transition temperatures agree to a few degrees Kelvin. However, we do not find the CuAu II phase which exists in a narrow temperature range between 658 K and 683 K. This phase is stabilized by the free energy differences between L_{10} and long-period superstructures of L_{10} which are as small as 1 meV/atom⁵⁶ and therefore beyond the accuracy of self-consistent LDA calculations.

For $x = \frac{3}{4}$ we obtain a sequence of transformations, the first one occurring at $T = 750 \text{ K}$ from the disordered A1 phase to a coherent two-phase mixture of L_{12} and A1. Then a subsequent transition at $T = 635 \text{ K}$ takes CuAu_3 into the long-range ordered (100) superlattice which is predicted to be the stable $T = 0$ ground state at that composition (see Sec. IV A 1). The calculated transition

TABLE VI. The experimentally measured² entropy of formation $S_{\text{tot}}^{\text{form}}$, the calculated configurational entropy $S_{\text{conf}}^{\text{calc}}$ and the derived non-configurational entropy of formation, $S_{\text{non-conf}}^{\text{form}}$. All values are given in units of k_B /atom.

System	x	T (K)	$S_{\text{tot}}^{\text{form}}$	S_{ideal}	$S_{\text{conf}}^{\text{calc}}$	$S_{\text{non-conf}}^{\text{form}} = S_{\text{tot}}^{\text{form}} - S_{\text{conf}}^{\text{calc}}$
Cu-Au	0.5	800	0.73	0.69	0.57	0.16
Ag-Au	0.5	800	0.52	0.69	0.62	0.10
Cu-Ag	0.141	1052	0.77	0.41	0.40 ^a	0.37
Ni-Au	0.5	1100	1.04	0.69	0.56	0.48

^aThis value was obtained at $T = 1136$ K, since a coherent phase separation starts at lower temperatures.

TABLE V. Calculated order-disorder transition temperatures (in K) for Cu-Au. A1 denotes the configurationally disordered fcc phase, and n/a means that the transition has not been observed (either experimentally or in the Monte Carlo simulation).

Composition	Transition	Expt.	This study
Cu _{0.75} Au _{0.25}	A1 ! L1 ₂	663	530
Cu _{0.50} Au _{0.50}	A1 ! L1 ₀	683/658 ^a	660
Cu _{0.33} Au _{0.66}	A1 ! 2	n/a	735
Cu _{0.25} Au _{0.75}	A1 ! L1 ₂	500	n/a
	A1 ! 2 + A1	n/a	750
	2 + A1 ! (100)SL	n/a	680

^aCuAu undergoes a transition to CuAu-II at 683 K, subsequently transforming into L1₀ CuAu-I at 658 K.

at $x = \frac{2}{3}$ goes straight into the 2 phase at $T = 735$ K. Therefore, a two-phase 2 + A1 ecd is predicted to exist at temperatures somewhere between 635 K and 730 K and around $x = \frac{3}{4}$. These predictions reflect the LDA. As stated in Sec. IV A 1, corrections to the LDA might be significant.

D. Non-configurational entropy

The effect of the non-configurational entropy (electronic, vibrational, etc.) on the alloy phase stability has recently attracted considerable interest.^{106,116} For instance, it has been suggested^{108,115} that there are large differences in the vibrational entropies of ordering $S_{\text{ordered}}^{\text{vib}}$ and $S_{\text{disord}}^{\text{vib}}$, which should manifest themselves in shifts of the order-disorder transition temperatures. There is another important class of thermodynamic properties where the vibrational entropy may play a role, and which has often been overlooked. Namely, it is the entropy of formation with respect to the pure constituents, defined in analogy with H in Eq. (4):

$$S_{\text{tot}}^{\text{form}}(A_1 x B_x; T) = S(A_1 x B_x; T) - (1-x)S(A; T) - xS(B; T); \quad (21)$$

where $S(A; T)$ is the total entropy of the pure constituent A at temperature T . It is often assumed that the configurational entropy is the dominant contribution

to $S_{\text{tot}}^{\text{form}}(A_1 x B_x; T)$ because all other contributions cancel out in Eq. (21). The non-configurational entropy of formation,

$$S_{\text{non-conf}}^{\text{form}}(A_1 x B_x; T) = S_{\text{tot}}^{\text{form}}(A_1 x B_x; T) - S_{\text{conf}}(A_1 x B_x; T); \quad (22)$$

contributes to such important quantities as mutual solubility limits and miscibility gap temperatures.

Noble metal alloys are excellent cases to test the values of $S_{\text{non-conf}}^{\text{form}}$ since accurate experimental data on the entropies of formation, $S_{\text{tot}}^{\text{form}}$, are available, and the configurational entropy S_{conf} can be calculated accurately using the thermodynamic integration technique described in Sec. IIID. Table VI gives the measured entropies of formation for disordered solid solutions $A_1 x B_x$, $S_{\text{tot}}^{\text{form}}(x; T)$, the maximum attainable configurational entropy S_{ideal} , as well as the theoretically calculated configurational entropy $S_{\text{conf}}^{\text{calc}}$, and the derived value for the non-configurational entropy of formation, $S_{\text{non-conf}}^{\text{form}}$. It shows that the size-mismatched noble metal systems have large amounts of $S_{\text{non-conf}}^{\text{form}}$ in the disordered solid solution. Since it is unlikely that these values of $S_{\text{non-conf}}^{\text{form}}$ are of electronic or magnetic origin, we suggest that the excess entropy in the disordered solid solutions of Ni-Au, Cu-Ag and Cu-Au is vibrational. It is possible that the atomic relaxations lead to a softening of lattice vibrations, although the physical mechanism of this softening is unclear at present.

Sanchez et al.⁴⁹ in their study of the Cu-Ag system noted that even a very crude model of the vibrational entropy markedly improved the agreement with the experimental solubility data. In the case of Ni-Au, which exhibits the largest $S_{\text{non-conf}}^{\text{form}}$, it is possible to reconcile the experimentally measured and theoretically calculated miscibility gap temperatures only by taking into account the non-configurational entropy of formation.¹¹⁷

The fact that Cu-Au also has a positive $S_{\text{non-conf}}^{\text{form}}$ has little qualitative effect on the phase diagram since Cu and Au are completely miscible from total energy and configurational entropy considerations alone. Ag-Au is calculated to have a negative $S_{\text{non-conf}}^{\text{form}}$, but its value is close to the experimental uncertainty in the measurement of S .

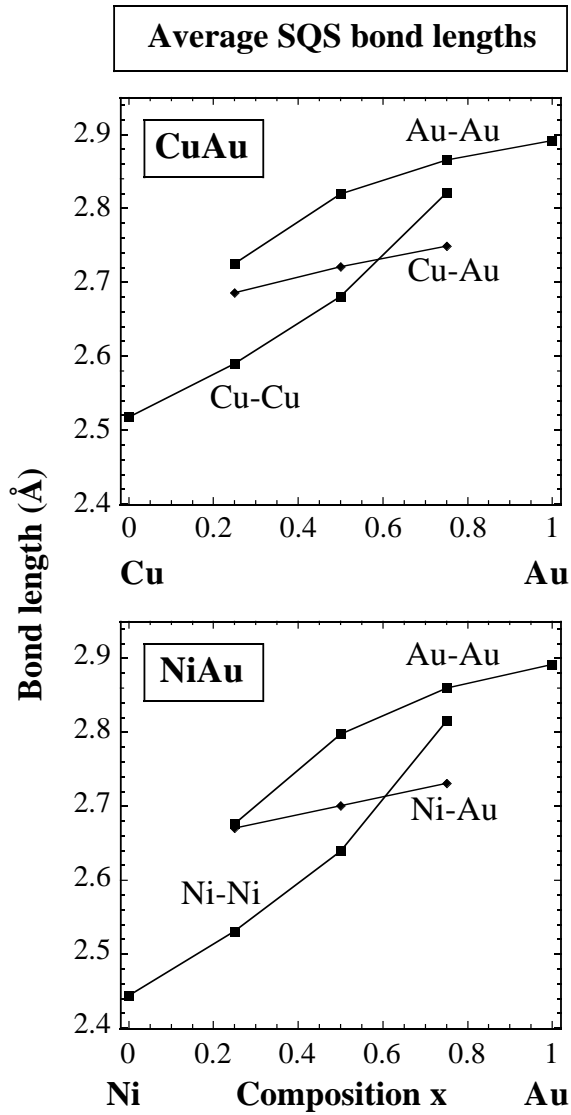


FIG. 8. SQS bond lengths for Cu-Au and Ni-Au.

E. Bond lengths in random alloys

Since recent experimental measurements of the composition-dependence of interatomic bond lengths in Cu-Au²⁴ and Ni-Au²³ have found several unusual features, it is interesting to address these trends from first-principles LDA calculations. In the present work we model the atomic positions in the random alloys using special quasirandom structures¹¹⁸ (SQS). These periodic structures are designed to reproduce the pair and multi-body correlation functions of the perfectly disordered configuration as closely as possible. It has been shown¹¹⁸ that even small unit cell SQS's can give rather accurate representation of the properties of random alloys. We have performed LDA calculations for 8 atom/cell SQS's at $x = \frac{1}{4}$ (SQS14_a), $x = \frac{1}{2}$ (SQS8_a; SQS8_b) and $x = \frac{3}{4}$ (SQS14_b). The atomic positions and cell coordinates

have been fully relaxed to minimize the total energy. The results for Cu-Au and Ni-Au interatomic bond lengths are shown in Fig. 8. The main features are:

(i) In spite of the different phase diagram properties (Ni-Au phase separates and Cu-Au orders at $T = 0$ K), the calculated behavior of bond lengths is very similar, which we attribute to the similar size mismatch in both systems (12% in Cu-Au and 15% in Ni-Au).

(ii) Our calculations give three distinct bond lengths at all compositions, which is also observed experimentally.^{23;24} Probably the most interesting feature in Fig. 8 is the crossing of $R_{BB}(x)$ and $R_{AB}(x)$ curves at $x = \frac{3}{4}$ in both systems. The measurements for Cu-Au²⁴ and Ni-Au²³ indicate that this may indeed be correct, since the deduced values around this composition are very close and have large error bars.

(iii) Another important feature, observed experimentally and reproduced by our SQS results, is that A-A bonds change much more as x varies from 0 to 1 than B-B bonds when x varies from 1 to 0, suggesting that the compressed bonds become increasingly stiffer and the expanded bonds weaken. This behavior can be explained by the asymmetry in the interatomic potential curves, which are rapidly hardening upon compression and softening upon expansion. However, our results for R_{AA} at $x = \frac{3}{4}$ and R_{BB} at $x = \frac{1}{4}$ are obtained from an average of only 4 minority bonds in the SQS14 structures, and perhaps are not representative of a wider statistical sample.

(iv) It is interesting to note that the predicted bond lengths between unlike atoms R_{AB} do not follow the linear relation $R_{AB} = R_{AA} + x(R_{BB} - R_{AA})$.

V. SUMMARY

We have showed that accurate first-principles studies of alloys with large size mismatches are now feasible using the mixed-space cluster expansion method. This method has been applied to noble metal alloys where vast amounts of experimental data and many theoretical studies are available.

(i) The mixed-space cluster expansion has been generalized to include the effects of nonlinear strain on the formation energies of long-period superlattices. We find that the elastic energy, required to lattice-match Cu and Ni to (100) surfaces of Au and Ag, is anomalously low, leading to a very low constituent strain energy of (100) superlattices. This effect is partly responsible for the stabilization of new LDA ground states of Au-rich Cu-Au alloys.

(ii) In Au-rich Cu-Au, we predict new $T = 0$ K ground states. Our LDA results place $L1_2$ (CuAu₃), previously thought of as the stable $T = 0$ state of CuAu₃, higher in energy than a family of superlattices along (100) direction. In particular, MoPt₂-type CuAu₂ [Cu₁Au₂ superlattice along (100)] and a compli-

cated $\text{Cu}_1\text{Au}_4\text{Cu}_1\text{Au}_4\text{Cu}_1\text{Au}_2\text{Cu}_1\text{Au}_2$ (100) superlattice are found to be the LDA ground states.

(iii) There are significant discrepancies (up to 50%) between the experimentally measured and calculated LDA mixing enthalpies for Cu-Au alloys. This is surprising since the experimental mixing enthalpies of Ni-Au and Ag-Au are reproduced very well.^{54;117}

(iv) The calculated order-disorder transition temperatures are in an excellent agreement with experiment. For instance, $T_c^{\text{calc}}(x = \frac{1}{4}) = 530 \text{ K}$ and $T_c^{\text{calc}}(x = \frac{1}{2}) = 660 \text{ K}$, compared with $T_c^{\text{expt}}(x = \frac{1}{4}) = 663 \text{ K}$ and $T_c^{\text{expt}}(x = \frac{1}{2}) = 683\text{--}658 \text{ K}$.

(v) From the experimentally measured entropies of formation $S_{\text{tot}}^{\text{form}}$ and the calculated configurational entropies $S_{\text{conf}}^{\text{calc}}$, we obtain large non-configurational (probably vibrational) entropies of formation in the size-mismatched systems, $S_{\text{non-conf}}^{\text{form}} = S_{\text{tot}}^{\text{form}} - S_{\text{conf}}^{\text{calc}}$. These entropies allow one to reconcile the experimental miscibility gap temperature and formation enthalpies of Ni-Au with the theoretical LDA values.¹¹⁷

(vi) Bond length distributions in Ni-Au and Cu-Au have been studied via supercell calculations employing the special quasirandom structure technique. The important qualitative features of recent EXAFS measurements^{23;24} are correctly reproduced: existence of distinct A-A, B-B and A-B bond lengths at all compositions, possible crossing of $R_{\text{AA}}(x)$ and $R_{\text{AB}}(x)$ around $x = \frac{3}{4}$ (where x is the composition of the larger constituent), softening of the shorter bond as $x \rightarrow 1$, and deviations of the bond length $R_{\text{AB}}(x)$ between unlike atoms from the linear Vegard's law.

ACKNOWLEDGMENTS

This work has been supported by the Office of Energy Research, Basic Energy Sciences, Materials Science Division, U.S. Department of Energy, under contract DE-AC36-83CH10093.

¹ Phase Diagrams of Binary Copper Alloys, eds. P. R. Subramanian, D. J. Chakrabarti, and D. E. Laughlin (ASM International, Materials Park, OH, 1994).

² R. Hultgren, P. D. Desai, D. T. Hawkins, M. Gleiser, and K. Kelley, Selected Values of the Thermodynamic Properties of Binary Alloys (American Society for Metals, Metals Park, OH, 1973).

³ M. Hansen, Constitution of Binary Alloys (Ginn, Schenectady, NY, 1985).

⁴ T. B. Massalski, Binary Alloy Phase Diagrams (ASM International, Materials Park, OH, 1990).

⁵ Noble Metal Alloys, edited by T. B. Massalski (The Metallurgical Society, Warrendale, 1986).

⁶ J. M. Cowley, J. Appl. Phys. 21, 24 (1950);

⁷ S. Ogawa and D. Watanabe, J. Appl. Phys. 22, 1502 (1951).

⁸ B. W. Bateman, J. Appl. Phys. 28, 556 (1957).

⁹ G. C. Kuczynski, M. Doyama, and M. E. Fine, J. Appl. Phys. 27, 651 (1956).

¹⁰ R. Kubiak and J. Janczak, Journal of Alloys and Compounds 176, 133 (1991).

¹¹ F. M. d'Hurle and P. Gordon, Acta Met. 9, 304 (1961).

¹² R. L. Orr, J. Luciat-Labry, and R. Hultgren, Acta Met. 8, 431 (1960).

¹³ R. A. Oriani, Acta Met. 2, 608 (1954).

¹⁴ R. A. Oriani and W. K. Murphy, J. Phys. Chem. 62, 327 (1958).

¹⁵ R. L. Orr, Acta Met. 8, 489 (1960).

¹⁶ M. Hirabayashi, S. Nagasaki, and H. Kono, J. Appl. Phys. 28, 1070 (1957).

¹⁷ M. Biazle, T. Oishi, F. Sommer, and K. Ono, Materials Transactions, JIM 33, 51 (1992).

¹⁸ M. Biazle, T. Oishi, and F. Sommer, J. of Alloys and Compounds 220, 182 (1995).

¹⁹ T. Claeson and J. B. Boyce, Phys. Rev. B 29, 1551 (1984).

²⁰ G. S. Sohal, C. Carbone, E. Kisker, S. Krummacher, A. Fattah, W. Ueselo, R. C. Albers, and P. Weinberger, Z. Phys. B - Condensed Matter 78, 295 (1990).

²¹ T. U. Nahm, K. H. Park, S.-J. Oh, S.-M. Chung, and G. K. Wertheim, Phys. Rev. B 52, 16 466 (1995).

²² T. Shinohara, S. Saitoh, F. Wagatsuma, and S. Yamaguchi, Phil. Mag. Lett. 74, 153 (1996).

²³ G. Renaud, N. Motta, F. Lancon, and M. Belakhovsky, Phys. Rev. B 38, 5944 (1988).

²⁴ A. I. Frenkel, E. A. Stern, A. Rubinstein, A. Voronel, and Yu. Rosenberg, submitted to J. de Phys. (1996).

²⁵ W. Shockley, J. Chem. Phys. 6, 130 (1938).

²⁶ J. M. Cowley, Phys. Rev. 77, 669 (1950).

²⁷ C. M. van Baal, Physica 64, 571 (1973).

²⁸ N. S. Golosov, L. E. Popov, and L. Ya. Pudan, J. Phys. Chem. Solids 34, 1149 and 1157 (1973).

²⁹ R. Kikuchi, J. Chem. Phys. 60, 1071 (1974).

³⁰ D. de Fontaine and R. Kikuchi, National Bureau of Standards SP-496, 999 (1977).

³¹ R. Kikuchi, J. M. Sanchez, D. de Fontaine, and H. Yamaguchi, Acta Met. 28, 651 (1980).

³² C. Sigli and J. M. Sanchez, Acta Met. 33, 1097 (1985).

³³ R. Kikuchi, in Noble Metal Alloys, (The Metallurgical Society, Warrendale, 1986).

³⁴ W. A. Oates, P. J. Spencer, and S. G. Fries, CALPHAD 20, 481 (1996).

³⁵ D. H. Wu and R. A. Tahir-Kheli, J. Phys. Soc. Japan 31, 641 (1971).

³⁶ B. Chakraborty and Z. Xi, Phys. Rev. Lett. 68, 2039 (1992).

³⁷ A. Chioleri, Ph.D. thesis, University of Fribourg, Switzerland, unpublished (1995).

³⁸ B. Chakraborty, Europhys. Lett. 30, 531 (1995).

³⁹ G. J. Ackland and V. Vitek, Phys. Rev. B 41, 10 324 (1990).

⁴⁰ H. M. Polatoglu and G. L. Beris, Interface Science 2, 31 (1994).

⁴¹ G. Bozzolo, J. Ferrante, and J. R. Smith, Phys. Rev. B

- 45, 493 (1992).
- ⁴² G. M. Azzone, V. Rosato, and M. Pintore, *Phys. Rev. B* 55, 837 (1997).
- ⁴³ C. Seok and D. W. Oxtoby, *J. Phys. Condens. Matter* 9, 87 (1997).
- ⁴⁴ L. G. Ferreira and M. A. Boselli, *Solid State Commun.* 96, 745 (1995).
- ⁴⁵ L. G. Ferreira and M. A. Boselli, to appear in *J. Phys. Cond. Matter* (1997).
- ⁴⁶ M. Ahlers, *Z. Phys. B* 99, 491 (1996).
- ⁴⁷ F. Cleri and V. Rosato, *Phil. Mag. Lett.* 67, 369 (1993).
- ⁴⁸ K. Terakura, T. Oguchi, T. Mohri, and K. Watanabe, *Phys. Rev. B* 35, 2169 (1987); T. Mohri, K. Terakura, S. Takizawa, and J. M. Sanchez, *Acta Met.* 39, 493 (1991).
- ⁴⁹ J. M. Sanchez, J. P. Stark, and V. L. Monuzzi, *Phys. Rev. B* 44, 5411 (1991).
- ⁵⁰ C. Amador and G. Bazzolo, *Phys. Rev. B* 49, 956 (1994).
- ⁵¹ S. H. Wei, A. A. Mbaye, L. G. Ferreira, and A. Zunger, *Phys. Rev. B* 36, 4163 (1987).
- ⁵² Z. W. Lu, S. H. Wei, A. Zunger, S. Frota-Pessoa, and L. G. Ferreira, *Phys. Rev. B* 44, 512 (1991).
- ⁵³ Z. W. Lu and A. Zunger, *Phys. Rev. B* 50, 6626 (1994).
- ⁵⁴ Z. W. Lu, B. M. Klein, and A. Zunger, *Modelling Simul. Mater. Sci. Eng.* 3, 753 (1995).
- ⁵⁵ Z. W. Lu, B. M. Klein, and A. Zunger, *Superlattices and Microstructures* 18, 161 (1995).
- ⁵⁶ A. T. Paxton and H. M. Polatoglu, *Phys. Rev. Lett.* 78, 270 (1996).
- ⁵⁷ J. W. Davenport, R. E. Watson, and M. Weinert, *Phys. Rev. B* 37, 9985 (1988).
- ⁵⁸ P. Weinberger, V. Drchal, L. Szunyogh, J. Fritscher, and B. I. Bennett, *Phys. Rev. B* 49, 13 366 (1994).
- ⁵⁹ D. D. Johnson and F. J. Pinski, *Phys. Rev. B* 48, 11 553 (1993).
- ⁶⁰ J. Kudmovsky, S. K. Bose, and O. K. Andersen, *Phys. Rev. B* 43, 4613 (1991).
- ⁶¹ I. A. Abrikosov, Yu. H. Vekilov, and A. V. Ruban, *Phys. Lett. A* 154, 407 (1991).
- ⁶² A. V. Ruban, I. A. Abrikosov, and H. L. Skriver, *Phys. Rev. B* 51, 12 958 (1995).
- ⁶³ B. Ginatempo and J. B. Staunton, *J. Phys. F: Met. Phys* 18, 1827 (1988).
- ⁶⁴ P. Hohenberg and W. Kohn, *Phys. Rev.* 136, 864 (1964); W. Kohn and L. J. Sham, *Phys. Rev. A* 136, 1133 (1965).
- ⁶⁵ D. B. Laks, L. G. Ferreira, S. Froyen, and A. Zunger, *Phys. Rev. B* 46, 12 587 (1992).
- ⁶⁶ A. Zunger, in *NATO ASI on Statics and Dynamics of Alloy Phase Transformations*, (Plenum Press, New York, 1994), p. 361.
- ⁶⁷ W. B. Pearson, *Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, Oxford, 1967).
- ⁶⁸ L. Pauling, *The Nature of the Chemical Bond*, 3rd ed. (Cornell University Press, New York, 1960), p. 93.
- ⁶⁹ B. Schonfeld, J. Traube, and G. Kosterz, *Phys. Rev. B* 45, 613 (1992); N. Norman and B. E. Warren, *J. Appl. Phys.* 22, 483 (1951); K. Ziesemer, PhD Thesis Universität Frankfurt, 1976.
- ⁷⁰ B. Velicky, S. Kirkpatrick, and H. Ehrenreich, *Phys. Rev.* 175, 747 (1968); P. Soven, *ibid.* 178, 1136 (1969).
- ⁷¹ For a review of the coherent potential approximation, see B. L. Gyor'y, D. D. Johnson, F. J. Pinski, D. M. Nicholson, and G. M. Stocks, in *Alloy Phase Stability*, edited by G. M. Stocks and A. Gonis (Kluwer, Dordrecht, 1988), p. 293.
- ⁷² F. Ducastelle, *Order and Phase Stability in Alloys* (North-Holland, New York, 1991).
- ⁷³ Z. W. Lu, S. H. Wei, and A. Zunger, *Phys. Rev. B* 45, 10 314 (1992).
- ⁷⁴ N. Mousseau and M. F. Thorpe, *Phys. Rev. B* 45, 2015 (1992).
- ⁷⁵ N. Papanikolaou, N. Stefanou, R. Zeller, and P. H. Dederichs, *Phys. Rev. B*, in press (1997); *Comp. Mat. Sci.*, in press (1997); N. Papanikolaou, N. Stefanou, R. Zeller, and P. H. Dederichs, in *Stability of Materials NATO ASI*, eds. A. Gonis, P. E. A. Turchi, and J. Kudmovsky (Plenum, New York, 1996).
- ⁷⁶ Z. W. Lu, S. H. Wei, and A. Zunger, *Phys. Rev. B* 44, 10 470 (1991).
- ⁷⁷ Z. W. Lu, S. H. Wei, and A. Zunger, *Phys. Rev. Lett.* 66, 1753 (1991); *ibid.* 68, 1961 (1992).
- ⁷⁸ J. W. D. Connolly and A. R. Williams, *Phys. Rev. B* 27, 5169 (1983).
- ⁷⁹ D. de Fontaine, in *Solid State Physics*, eds. H. Ehrenreich and D. Turnbull, Vol. 51, (Academic Press, New York, 1994).
- ⁸⁰ J. M. Sanchez, F. Ducastelle, and D. Gratias, *Physica* 128A, 334 (1984).
- ⁸¹ M. Asta, C. Wolverton, D. de Fontaine, and H. Dreyse, *Phys. Rev. B* 44, 4907 (1991).
- ⁸² J. M. Sanchez, *Phys. Rev. B* 48, 14 013 (1993).
- ⁸³ M. Born and K. Huang, *Dynamical Theory of Crystal Lattices* (Oxford Univ. Press, London and New York, 1961).
- ⁸⁴ A. A. Maradudin, E. W. Montroll, G. H. Weiss, and I. P. Ipatova, *Theory of Lattice Dynamics in the Harmonic Approximation*, in *Solid State Physics*, eds. H. Ehrenreich and D. Turnbull, Suppl. 3, (Academic Press, New York, 1971).
- ⁸⁵ S. de Gironcoli, P. Giannozzi, and S. Baroni, *Phys. Rev. Lett.* 66, 2116 (1991); M. Peressi and S. Baroni, *Phys. Rev. B* 49, 7490 (1994).
- ⁸⁶ K. Binder, D. W. Heermann, *Monte Carlo Simulation in Statistical Physics* (Springer-Verlag, Berlin, 1988).
- ⁸⁷ Z. W. Lu, D. B. Laks, S. H. Wei, and A. Zunger, *Phys. Rev. B* 50, 6642 (1994).
- ⁸⁸ S. H. Wei and H. Krakauer, *Phys. Rev. Lett.* 55, 1200 (1985), and references therein.
- ⁸⁹ E. Wigner, *Phys. Rev.* 46, 1002 (1934).
- ⁹⁰ J. P. Perdew and A. Zunger, *Phys. Rev. B* 23, 5048 (1981).
- ⁹¹ D. M. Ceperley and B. J. Alder, *Phys. Rev. Lett.* 45, 566 (1980).
- ⁹² J. P. Perdew and Y. Wang, *Phys. Rev. B* 33, 8800 (1986); 40, 3399 (1989) (E); J. P. Perdew, in *Electronic Structure of Solids '91*, eds. P. Ziesche and H. Eschrig (Akademie Verlag, Berlin, 1991), p. 11.
- ⁹³ S. Froyen, *Phys. Rev. B* 39, 3168 (1989).
- ⁹⁴ R. Yu, D. Singh, and H. Krakauer, *Phys. Rev. B* 43, 6411 (1991).
- ⁹⁵ P. Villars and L. D. Calvert, *Pearson's Handbook of Crystallographic Data for Intermetallic Phases* (American Society for Metals, Metals Park, OH, 1985).

- ⁹⁶ V. Ozolins, C. Wolverton, and A. Zunger, unpublished (1997).
- ⁹⁷ A. Zunger, in Handbook of Crystal Growth, Vol. 3, edited by D. T. J. Hurle (Elsevier, Amsterdam, 1994), p. 997.
- ⁹⁸ J. Homstra and W. J. Bartels, J. Crystal Growth 44, 513 (1978).
- ⁹⁹ E. Anastassakis, J. Appl. Phys. 68, 4561 (1990); J. of Crystal Growth 114, 647 (1991).
- ¹⁰⁰ D. J. Bottomley and P. Fons, J. of Crystal Growth 160, 406 (1996).
- ¹⁰¹ D. M. Wood, J. Vac. Sci. Technol. B 10, 1675 (1992).
- ¹⁰² A. G. Khachaturyan, Theory of Structural Transformations in Solids (Wiley, New York, 1983).
- ¹⁰³ C. Wolverton, V. Ozolins, and A. Zunger, unpublished (1997).
- ¹⁰⁴ A. H. MacDonald, W. E. Pickett, and D. D. Koelling, J. Phys. C 13, 2675 (1980); W. E. Pickett, A. J. Freeman, and D. D. Koelling, Phys. Rev. B 23, 1266 (1981).
- ¹⁰⁵ S.-H. Wei and A. Zunger, Phys. Rev. B 37, 8958 (1988).
- ¹⁰⁶ C. Wolverton and A. Zunger, Phys. Rev. B 52, 8813 (1995).
- ¹⁰⁷ R. E. Watson and M. Weinert, Phys. Rev. B 30, 1641 (1984).
- ¹⁰⁸ L. J. Nagel, L. Anthony, and B. Fultz, Phil. Mag. Lett. 72, 421 (1995).
- ¹⁰⁹ L. Anthony, J. K. Okamoto, and B. Fultz, Phys. Rev. Lett. 70, 1128 (1993).
- ¹¹⁰ B. Fultz, L. Anthony, L. J. Nagel, R. M. Nicklow, and S. Spooner, Phys. Rev. B 52, 3315 (1995).
- ¹¹¹ L. Anthony, L. J. Nagel, J. K. Okamoto, and B. Fultz, Phys. Rev. Lett. 73, 3034 (1994).
- ¹¹² B. Fultz, L. Anthony, J. L. Robertson, R. M. Nicklow, S. Spooner, and M. M. Ostoller, Phys. Rev. B 52, 3280 (1995).
- ¹¹³ L. J. Nagel, B. Fultz, J. L. Robertson, and S. Spooner, Phys. Rev. B 55, 2903 (1997).
- ¹¹⁴ G. D. Garbulsky and G. Ceder, Phys. Rev. B 49, 6327 (1994); *ibid.* 53, 8993 (1996).
- ¹¹⁵ J. D. Altho, D. Morgan, D. de Fontaine, M. A. Sta, S. M. Foiles, and D. D. Johnson, Phys. Rev. B 56, R5705 (1997).
- ¹¹⁶ J. Desplat, F. Bley, and F. Livet, Acta Mater. 44, 4961 (1996).
- ¹¹⁷ C. Wolverton and A. Zunger, Comp. Mater. Sci. 8, 107 (1997).
- ¹¹⁸ A. Zunger, S.-H. Wei, L. G. Ferreira, and J. E. Bernard, Phys. Rev. Lett. 65, 353 (1990).