

Magnetic entropy change of ErAl_2 magnetocaloric wires fabricated by a powder-in-tube method

Takafumi D. Yamamoto¹, Hiroyuki Takeya¹, Suguru Iwasaki¹, Kensei Terashima¹, Pedro Baptista de Castro^{1,2}, Takenori Numazawa¹, and Yoshihiko Takano^{1,2}

¹National Institute of Materials Science, Tsukuba, Ibaraki 305-0047, Japan

²University of Tsukuba, Tsukuba, Ibaraki 305-8577, Japan

E-mail: YAMAMOTO.Takafumi@nims.go.jp

Abstract. We report the fabrication of ErAl_2 magnetocaloric wires by a powder-in-tube method (PIT) and the evaluation of magnetic entropy change through magnetization measurements. The magnetic entropy change of ErAl_2 PIT wires exhibits similar behavior to the bulk counterpart, while its magnitude is reduced by the decrease in the volume fraction of ErAl_2 due to the surrounding non-magnetic sheaths. We find that another effect reduces the magnetic entropy change of the ErAl_2 PIT wires around the Curie temperature, and discuss its possible origin in terms of a correlation between magnetic properties of ErAl_2 and mechanical properties of sheath material.

Keywords: magnetic refrigeration, hydrogen liquefaction, intermetallic compounds, powder-in-tube method

Submitted to: *J. Phys. D: Appl. Phys.*

1. Introduction

Magnetic refrigeration is a cooling technology based on the magnetocaloric effect in which the variation in magnetic entropy (or temperature) of a magnetic material is caused by changing a magnetic field. A well-established applied technique is a cooling by adiabatic demagnetization to achieve ultra-low temperatures below 1 K [1, 2]. Since 1997, the application to room temperature refrigerators has been enthusiastically studied because magnetic refrigeration has the potential to outperform the conventional vapor-compression refrigeration concerning energy efficiency and environmental friendliness [3, 4]. Many great efforts have been made up to date on the development of working materials with a large magnetocaloric effect near room temperature [5–7] (*e.g.*, $\text{Gd}_5\text{Si}_2\text{Ge}_2$ discovered by Pecharsky and Gschneidner [8]) and efficient refrigeration systems such as an active magnetic regenerator (AMR) [9–11].

A newly attracting potential application of magnetic refrigeration is the hydrogen liquefaction. Hydrogen is one of the cleanest energy sources to replace fossil fuels [12]. For the use in society, it is efficient and economical to transport and store hydrogen in a liquid state because liquid hydrogen is denser than gaseous hydrogen. In this context, high-efficient liquefaction technology is required. One of the authors has confirmed >50% liquefaction efficiency in a test apparatus of the Carnot magnetic refrigerator worked around the hydrogen liquefaction temperature (20.3 K) [13]. On the other hand, in the practical liquefaction process, it is necessary to pre-cool the hydrogen gas from the temperature of a heat sink, such as liquid nitrogen, to nearly 20.3 K by using a multistage AMR cycle [14–16]. What should be noted here is that the magnetocaloric material must be processed into a specific shape suitable for each refrigeration system. For example, spherical particles or thin plates have been employed for AMR systems to gain better heat exchange efficiency between the working material and the heat-exchanger fluid [17, 18].

Candidate materials for hydrogen magnetic refrigeration are often found in intermetallic compounds containing heavy rare-earth elements. A representative example is the lanthanide (R) Laves phase RT_2 ($T = \text{Al, Co, and Ni}$) [19–21], which exhibits a large magnetic entropy change in the temperature range from 20 to 80 K. However, these compounds are difficult to be shaped due to their poor ductility and malleability. Moreover, these materials are quite brittle, leading to a risk of damage by the friction between them during the refrigeration cycle operation. Such mechanical properties prevent these candidate materials from being used as magnetic refrigerants. Besides, they are known to easily absorb hydrogen, resulting in the degradation of the refrigerants and their performance. A coating for protection is a typical way to solve this issue, but this takes extra effort in addition to the shaping process for producing magnetic refrigerants.

Very recently, Funk et al. reported [22] a way for producing magnetocaloric wire by a PIT method in $\text{La}(\text{Fe, Co, Si})_{13}$, which is a promising material for the room temperature magnetic refrigeration [23, 24]. The PIT method is a conventional and simple technology that has been developed in the field of superconducting wires [25, 26], in which a powdered raw material is filled into a metal tube and then formed into wire-shaped by various metal

workings. This approach is attractive because of many advantages in applying the PIT method to the candidate materials for hydrogen magnetic refrigeration as follows: (1) This method is available even for the difficult-to-process materials since raw materials can be powder. (2) The metal sheath surrounding the magnetic refrigerants protects them from the friction wear or the hydrogen embrittlement. (3) As Funk et al. have pointed out, the wires provide the possibility of various arrangements of magnetic refrigerants. Besides, it should be noted that recent works have focused on wire-shaped magnetocaloric materials because they have been suggested to show superior performance as magnetic refrigerants to conventional spherical or plate-like materials [27–29].

In this paper, we investigate the effects of a PIT process on the magnetocaloric properties in a well-studied compound ErAl_2 that exhibits a second-order ferromagnetic transition at $T_c \sim 14$ K [19, 30, 31]. We have confirmed that the magnetic entropy change ΔS_M is similar in the ErAl_2 PIT wires and the bulk counterpart, while it decreases in magnitude for the former due to a reduction of volume fraction of ErAl_2 in the wires. We have further found that another effect causes an additional decrease of ΔS_M near T_c , which depends on the sheath material. This is the first report to apply the PIT method for fabricating magnetocaloric wire for the hydrogen liquefaction.

2. Experimental details

ErAl_2 single-core wires were fabricated by an *ex-situ* PIT method without any heat treatment. ErAl_2 raw powder with a diameter of less than $50 \mu\text{m}$ was prepared by a gas-atomization process. The powder was filled into several metal tubes with 50 mm in length, an outer diameter (d_o) of 6 mm, and inner diameter (d_i) of 4 or 5 mm (hereafter, referred to 6×4 tube and 6×5 tube respectively). The tubes were plugged on both sides by cylinders 7 mm in length made of the same material as each tube. Thus-made initial rods were first groove-rolled into wires with a size of 2 mm stepwisely. Then the wires were cut into about 70 mm and further groove-rolled into those with a size of 1 mm stepwisely. The resulting PIT wires were 260–300 mm in length. Cu, Al, and Brass were employed as the sheath materials because they are non-magnetic and show relatively high thermal conductivity.

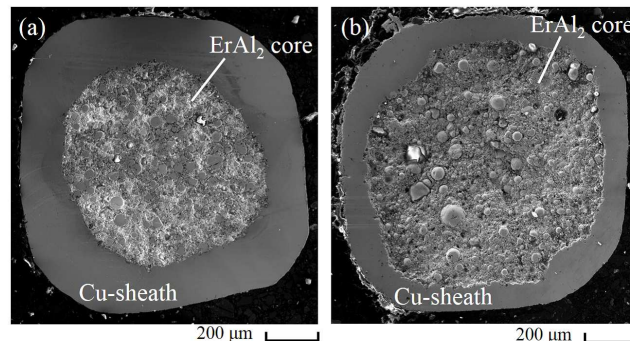


Figure 1. Cross-sectional SEM images of ErAl_2/Cu PIT wires fabricated from (a) 6×4 and (b) 6×5 tubes (see the text). The size is about 1 mm each.

The cross-sectional observations for the fabricated PIT wires were carried out using a JEOL JSM-6010LA scanning electron microscope (SEM) operated at 15 kV. The cross-sectional area was evaluated using an image analysis software Image-J (National Institute of Health, US). Figures 1(a) and 1(b) show SEM images of ErAl₂/Cu PIT wires fabricated from the 6×4 and 6×5 tubes, respectively. These images indicate that the ErAl₂ powder is uniformly filled inside the Cu-sheath as a core material. The cross-section ratios of the ErAl₂ core to the whole wire were evaluated to be 0.437 from Fig. 1(a) and 0.655 from Fig. 1(b), which are comparable to the theoretical filling rate, defined as d_1^2/d_0^2 , expected for each initial tube (0.444 for the 6×4 tube and 0.694 for the 6×5 tube). This result implies that the core and the sheath material were deformed at the same proportion during the rolling process. We have found the same features in ErAl₂/Al and ErAl₂/Brass PIT wires.

Magnetization measurements were performed by a Quantum Design magnetic property measurement system. Temperature (T) dependence of magnetization (M) of the ErAl₂ powder and the PIT wires was measured between 2 and 60 K at a temperature sweep rate of 0.5 K/min under various magnetic fields ($\mu_0 H$) ranging from 0.1 to 5 T in zero-field cooling (ZFC) process. The magnetic fields were applied along the longitudinal direction of each PIT wire with 5-7 mm in length. For the powder sample, field dependence of magnetization was collected between 0 and 5 T in the temperature range of $2 \leq T \leq 40$ K.

The magnetic entropy change is often evaluated from the isothermal magnetization (M - $\mu_0 H$) measurements by using one of Maxwell's relations

$$\Delta S_M(T, \mu_0 \Delta H) = \mu_0 \int_{H_i}^{H_f} \left(\frac{\partial M}{\partial T} \right)_H dH, \quad (1)$$

where H_i and H_f is the initial and final magnetic field, and $\Delta H = H_f - H_i$. However, this way requires us to collect lots of magnetization curves at various temperatures for correct evaluation, which is somewhat time-consuming and makes it difficult to obtain in detail the temperature dependence of ΔS_M . So we first examined how to efficiently and accurately evaluate ΔS_M from the isofield magnetization (M - T) measurements in the ErAl₂ powder. Then the validity of this unconventional method was verified by comparing the results obtained from this and the often-used method. In the following, H_i is set to zero.

3. Results and discussion

Figure 2(a) shows the M - T curves of the ErAl₂ powder. One finds the features typical of a second-order ferromagnetic transition with T_c of 12 K, defined as the temperature at which $|\partial M/\partial T|$ at 0.1 T takes a maximum. The slight discrepancy with the T_c in the literatures may be because that the ErAl₂ powder was made by the gas-atomization process in which where the material is quenched. Similar M - T curves have been observed in all the ErAl₂ PIT wires (not shown). To calculate ΔS_M correctly from M - T measurements, one should select the measuring magnetic fields properly. As shown in Fig. 2(b), $|\partial M/\partial T|$ calculated from Fig. 2(a) exhibit a non-monotonic field dependence, especially around T_c : it steeply increases and reaches the highest point below 1 T, followed by a gradual decrease under higher fields. Since $\Delta S_M(T, \mu_0 \Delta H)$ at a fixed T is equivalent to the area in the $\partial M/\partial T$ - $\mu_0 H$

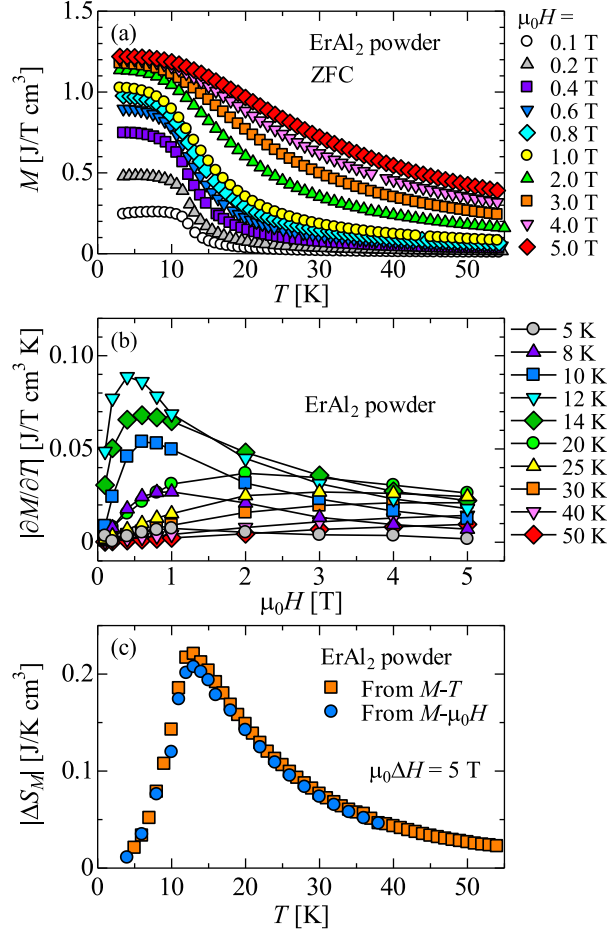


Figure 2. (Color Online) (a) Temperature dependence of magnetization and (b) field dependence of the temperature derivative of magnetization for the ErAl₂ powder. (c) Magnetic entropy change for $\mu_0 \Delta H = 5$ T as a function of temperature evaluated from $M-T$ (square) and $M-\mu_0 H$ (circle) measurements.

plane, this peak structure can largely affect the evaluated value of ΔS_M . Accordingly, it is essential to finely collect the $M-T$ curves under magnetic fields in which the peak of $|\partial M/\partial T|$ appears [32]. Figure 2(c) shows $\Delta S_M(T, \mu_0 \Delta H = 5$ T) of the ErAl₂ powder evaluated using Eq. (1) based on $\partial M/\partial T-\mu_0 H$ data calculated from the $M-T$ curves and the $M-\mu_0 H$ curves (see the supplementary data), respectively. Two ΔS_M curves almost agree with each other and peaks at T_c . This result indicates that the magnetic entropy change can be correctly evaluated through the isofield magnetization measurements. ΔS_M of the PIT wires were evaluated by the same procedure.

Figures 3 (a) and 3 (b) represent the temperature dependence of $|\Delta S_M|$ for $\mu_0 \Delta H = 5$ T per total volume of 1 cm³ in various ErAl₂ PIT wires fabricated from the 6×4 and 6×5 tubes. The data for the ErAl₂ powder is also shown for the comparison. The magnetic entropy change of the PIT wires exhibits qualitatively similar characteristics as those of the powder sample, while the magnitude is decreased by about 60-70%. This result is not surprising because the volume fraction of ErAl₂ is reduced in the PIT wires. In that sense, the data for

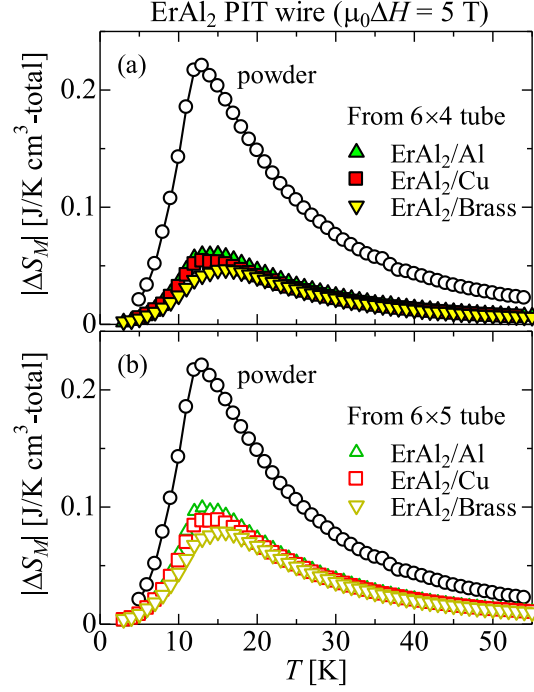


Figure 3. (Color Online) Temperature dependence of $|\Delta S_M|$ for $\mu_0\Delta H = 5$ T in various ErAl_2 PIT wires fabricated from (a) 6×4 and (b) 6×5 tubes, along with the data for the ErAl_2 powder. For the PIT wires, $|\Delta S_M|$ represents the magnetic entropy change of the wire with a total volume of 1 cm^3 .

the powder sample can be regarded as $|\Delta S_M|$ of a hypothetical wire with 100% ErAl_2 core material. Indeed, $|\Delta S_M|$ becomes larger in the case of the PIT wire fabricated from the 6×5 tube, namely, the larger filling rate of the core material. Furthermore, when the filling rate is the same, at the temperatures above 30 K, $|\Delta S_M|$ does not depend on the sheath material. These facts suggest that the volume fraction of the ErAl_2 core material mainly determines the magnetic entropy change of the PIT wires. On the other hand, we should notice the difference in $|\Delta S_M|$ between the PIT wires at around T_c , where the $|\Delta S_M|$ of the $\text{ErAl}_2/\text{Brass}$ wire is significantly decreased. A possible origin of which is discussed below.

Here let us evaluate the ratios of the magnetic entropy change in each PIT wire ($|\Delta S_M^{\text{wire}}|$) to that in the ErAl_2 powder ($|\Delta S_M^{\text{powder}}|$), which should correspond to the volume fraction of the core material. Figures 4(a) and 4(b) show the temperature dependence of $|\Delta S_M^{\text{wire}}/\Delta S_M^{\text{powder}}|$ calculated for the PIT wires made from the 6×4 and 6×5 tubes. One finds that the ratios take constant values at temperatures above 30 K. This makes sense because the volume fraction should not change at any temperature. On that account, we employ the mean value of the temperature-independent $|\Delta S_M^{\text{wire}}/\Delta S_M^{\text{powder}}|$ as the actual volume fraction of ErAl_2 in the PIT wires, being ~ 0.30 for the wires made from the 6×4 tube and ~ 0.49 for those made from the 6×5 tube. These values are about 70-75% of the theoretical volume fraction expected from the SEM images assuming no voids. Funk et al. have reported that the volume fraction of $\text{La}(\text{Fe}, \text{Si}, \text{Co})_{13}$ core is about 85% of the theoretical one, even though pre-compacted raw materials were filled into a metal tube [22]. In contrast, ErAl_2 powder was filled without any treatments

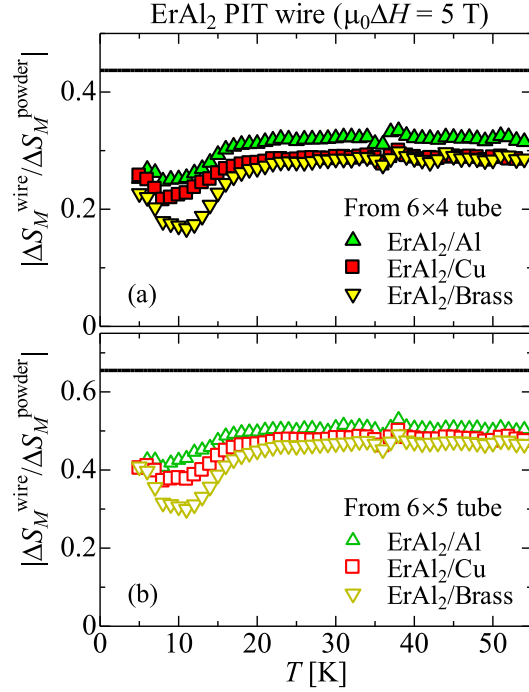


Figure 4. (Color Online) Temperature dependence of $|\Delta S_M^{\text{wire}}/\Delta S_M^{\text{powder}}|$ for the ErAl_2 PIT wires made from (a) 6×4 and (b) 6×5 tubes (see the text). Solid lines depict the theoretical volume fraction of the core material expected from Fig. 1 with assuming no voids.

in this study, implying that there can be more voids in our PIT wires compared with the $\text{La}(\text{Fe}, \text{Si}, \text{Co})_{13}$ PIT wire. Accordingly, the obtained values of the ErAl_2 core volume fraction seem to be reasonable. With further decreasing temperature, $|\Delta S_M^{\text{wire}}/\Delta S_M^{\text{powder}}|$ gradually decreases and exhibits a dip structure near T_c , whose characteristic is noticeable with $\text{ErAl}_2/\text{Brass}$ wires. This behavior suggests that there is another contribution that affects the magnetic entropy change of ErAl_2 itself in the PIT wires, in addition to the decrease in the volume fraction of the core material.

Now we will discuss a possible origin of the extra reduction of $|\Delta S_M|$ around T_c observed in the PIT wires. According to Eq. (1), a decrease in ΔS_M results from a decrease in $(\partial M/\partial T)_H$, which occurs when M decreases without changing the temperature dependence and/or when the temperature dependence itself becomes more gradual. To clarify this point, we plot $M/M_{50\text{ K}}$ at 5 T as a function of temperature in Fig. 5 for the ErAl_2 powder and the PIT wires made from the 6×5 tube. The magnetizations show the same temperature dependence down to 30 K for all the samples, but the rise in M of the PIT wires is suppressed with decreasing temperature, the trend is most significant in the $\text{ErAl}_2/\text{Brass}$ wire. This mild temperature variation does be the cause of the decrease in $(\partial M/\partial T)_H$ for the PIT wires. The difference in M - T curves observed here resembles those found in ferromagnetic materials with a uniaxial magnetic anisotropy [33–35], in which $(\partial M/\partial T)_H$ becomes smaller in the direction perpendicular to an easy axis of the magnetization. Thus, the extra reduction of $|\Delta S_M|$ around T_c implies that the PIT process induces a magnetic anisotropy in the ErAl_2 core material with an easy axis perpendicular to the longitudinal direction of the wire.

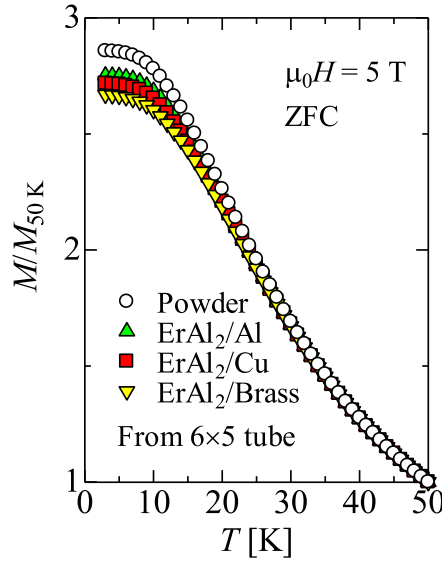


Figure 5. (Color Online) Temperature dependence of magnetization at 5 T normalized by the magnetization at 50 K for ErAl_2 powder and PIT wires made from the 6×5 tube.

It is well known that a rolling process causes a kind of magnetic anisotropy in magnetic materials [36–39]. This magnetic anisotropy is known to increase as the mechanical deformation increases, and the latter usually increases with the stress on magnetic material during rolling. On the other hand, in several studies on superconducting PIT wires [40, 41], it has been pointed out that the higher the hardness of sheath material, the stronger the stress on core material during cold working. From these facts, the magnetic anisotropy induced by rolling is expected to be large in the use of the harder tube in a PIT process. In fact, since Vickers hardness is higher in the order of Al, Cu, and Brass, the expectation is consistent with the result that $|\Delta S_M|$ around T_c is most decreased in the $\text{ErAl}_2/\text{Brass}$ PIT wires. Therefore, we conclude that the PIT process affects the magnetocaloric properties of the ErAl_2 core material through the induced uniaxial magnetic anisotropy. However, the exact nature of the magnetic anisotropy remains unclear at the present stage. To get more insight, it is desirable to investigate the effect of annealing that may control the plastic deformation.

4. Conclusion

We have fabricated the magnetocaloric wires of ErAl_2 clad by non-magnetic metal sheaths by using a powder-in-tube method combined with groove rolling. These PIT wires exhibit magnetic entropy changes similar to that of the powder sample, with their magnitude reduced due to the decrease in the volume fraction of the ErAl_2 core. We propose that the PIT process affects the magnetocaloric properties of the core material through a kind of the induced uniaxial magnetic anisotropy and causes the extra reduction of the magnetic entropy change around T_c . There is still room for improvement of the magnetocaloric properties in the PIT wires by annealing process and additional processes that increase the volume fraction of the core. We believe that the wire-shaped magnetocaloric materials prepared by a PIT

method would be of benefit to the development of magnetic refrigerators for the hydrogen liquefaction.

Acknowledgments

This work was supported by JST-Mirai Program Grant Number JPMJMI18A3, Japan.

References

- [1] Debye P 1926 *Ann. Phys.* **81** 1154.
- [2] Giauque W F 1927 *J. Am. Chem.* **49** 1864.
- [3] Zimm C, Jastrab A, Sternberg A, Pecharsky V, Gschneidner Jr K, Osborne M, and Anderson I 1998 *Adv. Cryog. Eng.* **43** 1759.
- [4] Brück E 2005 *J. Phys. D: Appl. Phys.* **38** R381.
- [5] Gschneidner Jr K A, Pecharsky V K, and Tsokol A O 2005 *Rep. Prog. Phys.* **68** 1479.
- [6] Tishin A M 2007 *J. Magn. Magn. Mater.* **316** 351.
- [7] Franco V, Blázquez J S, Ipus J J, Law J Y, Moreno-Ramírez L M, Conde A 2018 *Prog. Mater. Sci.* **93** 112.
- [8] Pecharsky V K and Gschneidner Jr K A 1997 *Phys. Rev. Lett.* **78** 4494.
- [9] Barclay J A and Steyert W A 1982 *U. S. Patent* 4 332 135.
- [10] Gschneidner Jr K A and Pecharsky V K 2008 *Int. J. Ref.* **31** 945.
- [11] Nielsen K K, Tusek J, Engelbrecht K, Schopfer S, Kitanovski A, Bahl C R H, Smith A, Pryds N, Peredos A 2011 *Int. J. Ref.* **34** 603.
- [12] Jones L W 1971 *Science* **174** 367.
- [13] Kamiya K, Takahashi H, Numazawa T, Nozawa H, and Yanagitani T 2007 *Cryocooler* **14** 637.
- [14] Utaki T, Kamiya K, Nakagawa T, Yamamoto T A, and Numazawa T 2007 *Cryocooler* **14** 645.
- [15] Matsumoto K, Kondo T, Yoshioka S, Kamiya K, and Numazawa T 2009 *J. Phys.: Conf. Ser.* **150** 012028.
- [16] Numazawa T, Kamiya K, Utaki T, Matsumoto K 2014 *Cryogenics* **62** 185.
- [17] Yu B, Liu M, Egolf P W, and Kitanovski A 2010 *Int. J. Ref.* **33** 1029.
- [18] Tušek J, Kitanovski A, and Poredoš A 2013 *Int. J. Ref.* **36** 1456.
- [19] Hashimoto T, Matsumoto K, Kurihara T, Numazawa T, Tomokiyo A, Yayama H, Goto T, Todo S, and Sahashi M 1986 *Adv. Cryog. Eng. Mater.* **32** 279.
- [20] Tomokiyo A, Yayama H, Wakabayashi H, Kuzuhara T, Hashimoto T, Sahashi M, and Inomata K 1986 *Adv. Cryog. Eng. Mater.* **32** 295.
- [21] Zhu T, Asamoto K, Nishimura Y, Kouen T, Abe S, Matsumoto K, and Numazawa T 2011 *Cryogenics* **51** 494.
- [22] Funk A, Freundenberger J, Waske A, and Krautz M 2018 *Mater. Today Ener.* **9** 223.
- [23] Hu F X, Shen B G, Sun J R, Cheng Z H, Rao G H, and Zhang X X 2001 *Appl. Phys. Lett.* **78** 3675.
- [24] Fujieda S, Fujita A, and Fukamichi K 2002 *Appl. Phys. Lett.* **81** 1276.
- [25] Kunzler J E, Buehler E, Hsu F S L, and Wernick J H 1961 *Phys. Rev. Lett.* **6** 89.
- [26] Kunzler J E 1961 *Rev. Mod. Phys.* **33** 501.
- [27] Shen H X, Xing D W, Sánchez Liamazares J L, Sánchez-Valdés C F, Belliveau H, Wang H, Qin F X, Liu Y F, Sun J F, Srikanth H, and Phan M H 2016 *Appl. Phys. Lett.* **108** 092403.
- [28] Kondo M, Ueno K, Takeuchi K, Nomura R, and Kizaki T 2017 *Fujikura Tech. Rev.* **47** 47.
- [29] Vuarnoz D and Kawanami T 2012 *Appl. Therm. Eng.* **37** 388.
- [30] Nereson N, Olisen C, and Arnold G, 1968 *J. Appl. Phys.* **39** 4605.
- [31] Pecharsky V K and Gschneidner Jr K A 1999 *J. Appl. Phys.* **86** 565.
- [32] This magnetic field range corresponds to that in which the magnetization at a sufficiently low temperature increases rapidly and almost saturates in the M - $\mu_0 H$ plane. (see the supplementary data)
- [33] Zhang X X, Wei H L, Zhang Z Q, and Zhang L 2001 *Phys. Rev. Lett.* **87** 157203.

- [34] Luis F, Bartolomé F, Petroff F, Bartolomé J, García L M, Deranlot C, Jaffrés H, Martínez M J, Bencok P, Wilhelm F, Rogalev A, and Brookes N B 2006 *Europhys. Lett.* **76** 142.
- [35] Liu Y and Petrovic C 2019 *Phys. Rev. Mat.* **3** 014001.
- [36] Chikazumi S 1958 *J. Appl. Phys.* **29** 346.
- [37] Chikazumi S, Suzuki K, and Iwata H 1960 *J. Phys. Soc. Jpn.* **15** 250.
- [38] Chin G Y, Nesbitt E A, Wernick J H, and Vanskike L L 1967 *J. Appl. Phys.* **38** 2623.
- [39] Morita H, Fujimori H, and Obi Y 1979 *Jpn. J. Appl. Phys.* **18** 683.
- [40] Grasso G, Malagoli A, Ferdeghini C, Roncallo S, Braccini V, and Cimberle M R, 2001 *Appl. Phys. Lett.* **79** 230.
- [41] Kumakura H, Matsumoto A, Fujii H, Kitaguchi H, Togano K, 2002 *Physica C* **382** 93.